

Article

Self-Organized TiO₂–MnO₂ Nanotube Arrays for Efficient Photocatalytic Degradation of Toluene

María C. Nevárez-Martínez ^{1,2}, Marek P. Kobylański ³, Paweł Mazierski ^{3,*}, Jolanta Wólkiewicz ⁴, Grzegorz Trykowski ⁴, Anna Malankowska ³, Magda Kozak ³, Patricio J. Espinoza-Montero ² and Adriana Zaleska-Medynska ^{3,*}

¹ Facultad de Ingeniería Química y Agroindustria, Escuela Politécnica Nacional, Ladrón de Guevara E11-253, P.O. Box 17-01-2759, Quito 170525, Ecuador; ma.cristina.nevarez@gmail.com

² Centro de Investigación y Control Ambiental “CICAM”, Departamento de Ingeniería Civil y Ambiental, Facultad de Ingeniería Civil y Ambiental, Escuela Politécnica Nacional, Ladrón de Guevara E11-253, P.O. Box 17-01-2759, Quito 170525, Ecuador; patricio.espinoza@epn.edu.ec

³ Department of Environmental Technology, Faculty of Chemistry, University of Gdansk, 80-308 Gdansk, Poland; marek.kobylanski@phdstud.ug.edu.pl (M.P.K.); anna.malankowska@ug.edu.pl (A.M.); magda.kozak@ug.edu.pl (M.K.)

⁴ Faculty of Chemistry, Nicolaus Copernicus University, 87-100 Torun, Poland; jolanta.wolkiewicz@umk.pl (J.W.); tryki@umk.pl (G.T.)

* Correspondences: pawel.mazierski@phdstud.ug.edu.pl (P.M.); adriana.zaleska@ug.edu.pl (A.Z.-M.); Tel.: +48-58-523-52-29 (P.M.); +48-58-523-52-20 (A.Z.-M.)

Academic Editor: Pierre Pichat

Received: 3 February 2017; Accepted: 28 March 2017; Published: 31 March 2017

Abstract: Vertically oriented, self-organized TiO₂–MnO₂ nanotube arrays were successfully obtained by one-step anodic oxidation of Ti–Mn alloys in an ethylene glycol-based electrolyte. The as-prepared samples were characterized by scanning electron microscopy (SEM), energy-dispersive X-ray spectroscopy (EDX), UV-Vis absorption, photoluminescence spectroscopy, X-ray diffraction (XRD), and micro-Raman spectroscopy. The effect of the applied potential (30–50 V), manganese content in the alloy (5–15 wt. %) and water content in the electrolyte (2–10 vol. %) on the morphology and photocatalytic properties was investigated for the first time. The photoactivity was assessed in the toluene removal reaction under visible light, using low-powered LEDs as an irradiation source ($\lambda_{\max} = 465$ nm). Morphology analysis showed that samples consisted of auto-aligned nanotubes over the surface of the alloy, their dimensions were: diameter = 76–118 nm, length = 1.0–3.4 μm and wall thickness = 8–11 nm. It was found that the increase in the applied potential led to increase the dimensions while the increase in the content of manganese in the alloy brought to shorter nanotubes. Notably, all samples were photoactive under the influence of visible light and the highest degradation achieved after 60 min of irradiation was 43%. The excitation mechanism of TiO₂–MnO₂ NTs under visible light was presented, pointing out the importance of MnO₂ species for the generation of e[−] and h⁺.

Keywords: TiO₂–MnO₂ nanotubes; visible light induced photocatalysis; alloys; toluene degradation; anodization

1. Introduction

TiO₂-based photocatalysis is an effective technique for pollutant removal from both gas and liquid phase [1–7]. In fact, applications of TiO₂ are not limited only to photodegradation reactions, but it offers the facility to drive many others such as organic synthesis [8], water splitting [9,10], disinfection [11], CO₂ reduction [10,12], self-cleaning or antimicrobial surfaces [13,14], and dye-sensitized solar cells [10,15,16]. Due to the environmentally-friendly nature of TiO₂, its chemical and biological inertness, low cost, availability, and excellent photoactivity, this semiconductor material has become

of great interest [17]. Nevertheless, some drawbacks as the rapid charge recombination of the photogenerated electrons and holes, and the wide bandgap (3.0 eV for rutile and 3.2 eV for anatase), which restricts photoabsorption to only ultraviolet region (ca. 5% of solar spectrum), need to be overcome in order to extend the practical application of TiO₂ photocatalysts for solar or interior light driven photoreactions at large scale [18].

Bandgap engineering in addition to tuning strategies have been studied over last decades with a common aim: shifting the absorption wavelength range of TiO₂ to the visible region. Since 1980s, TiO₂ has been modified by platinization [19–21]. So far, numerous approaches as ion (either cation or anion) doping [22–25], coupling with a narrower-bandgap semiconductor [26], with noble metals [27,28], with either organic or inorganic dyes [29] have been presented by a large number of research groups. Synthesizing composites with oxide semiconductors has become a promising way to enhance the photoactivity of TiO₂ by promoting the absorption of visible light and inhibiting the fast recombination of charge carriers [18,30]. Recent studies have focused on TiO₂–MnO₂ system due to the MnO₂ features as non-toxicity and earth abundance. These composites have been used mainly for capacitance applications [31,32], and despite the narrow bandgap of MnO₂ (0.26–2.7 eV), which could allow the absorption of visible and theoretically even infrared light [33–38], there exist just few reports in literature about the application of this system in photocatalysis. Xue, et al. [39] synthesized mesoporous MnO₂/TiO₂ nanocomposite, photoactive for the visible light-driven degradation of MB. They attributed the improved photocatalytic efficiency to the effective separation of photogenerated electrons and holes.

However, the industrial usage of photocatalysts is still in need of improvements to maximize the overall efficiency which also depends on mass and charge transfer processes. Therefore, TiO₂ nanostructures like zero-dimensional (nanoparticles), one-dimensional (nanowires, rods, and tubes), two dimensional (layers and sheets), and three dimensional (hierarchical spheres) have been widely synthesized, and used [40]. Since the discovery of carbon nanotubes in 1991 by Iijima [41], 1D morphologies as nanotubes (NTs) have become attractive materials due to the efficient separation of charge carriers, shape selectivity in chemical processes, high surface area to volume ratio, high electron mobility, mechanical strength [40,42], and high photoactivity in air purification [43]. Many approaches as sol-gel, template assisted, hydro/solvothermal and electrochemical have achieved to prepare TiO₂ NTs. Among these techniques, the electrochemical anodization of a suitable metal or alloy is the simplest, cheapest, and the most direct to grow self-highly-organized-nanotube arrays under specific electrochemical conditions which permit to control the properties of the fabricated NTs [44]. It was reported previously that MnO₂–TiO₂ NTs composite could be successfully formed by one-step anodic oxidation of Ti–Mn alloy [22,37]. Mohapatra, et al. [45] synthesized ordered arrays of mixed oxide NTs by anodization of Ti/Mn alloys, under ultrasonication in the presence of a fluoride-containing ethylene glycol solution. They pointed out that before calcination, the as-formed NTs showed a stoichiometry of (Ti,Mn)O₂, while annealing at 500 °C resulted in formation of nanotubes composed of anatase and rutile phases of TiO₂ and Mn₂O₃. Ning, Wang, Yu, Li, and Zhao [32] electrochemically prepared mixed oxide NTs from Ti–Mn alloys which showed enhanced capacitive properties compared with those of pristine TiO₂ NTs.

Herein, this work aims to anodically grow TiO₂–MnO₂ NTs in a fluoride-containing ethylene glycol-based electrolyte, and their application in the photodegradation of a model gaseous pollutant. According to our best knowledge, photocatalytic properties of nanotubes made of titania and manganese oxide mixtures have been investigated in this work for the first time. Moreover, parameters as the applied voltage (30–50 V), manganese content in the alloy (5–15 wt. %), and water content (2–10 vol. %) in the electrolyte have been also studied for the first time to analyze their effect on the morphology and photoactivity of the obtained NT arrays. Photodegradation tests in the gas phase were conducted with toluene as the model pollutant, and a possible mechanism of visible-light driven decomposition over the TiO₂–MnO₂ NTs was proposed as well.

2. Results and Discussion

2.1. Morphology and Growth Mechanism

One-step anodization processes were conducted for 60 min to synthesize pristine TiO_2 and $\text{TiO}_2\text{-MnO}_2$ nanotube layers from technical grade Ti sheets and Ti-Mn alloys under specific conditions, which are summarized in Table 1. SEM technique was used to analyze the effect of the applied voltage (30, 40 and 50 V), manganese content in the alloy (5, 10 and 15 wt. %) and water content in the electrolyte (2, 5 and 10 vol. %) on the morphology of the as-prepared samples. Figure 1 shows the top and cross-sectional SEM images which indicate that all synthesized nanotubes were uniform and vertically oriented. Pristine TiO_2 NTs presented smooth and uniform walls while $\text{TiO}_2\text{-MnO}_2$ NTs had ripples on their walls, which was also observed by Mohapatra, et al. [45] in samples anodized from Ti-8Mn alloys. It is well known that the dimensions of the nanotubes can be easily tuned by changing the preparation parameters [25]. Length and diameter increased with increasing the applied voltage, starting from $d = 81 \pm 9$ nm and $l = 1.5 \pm 0.1$ μm (Ti_30V); and reaching values of $d = 120 \pm 12$ nm and $l = 16.2 \pm 0.2$ μm (Ti_50V) for pristine TiO_2 NTs. The influence of anodization voltage was studied keeping constant the manganese content in the alloy (10 wt. %) and the water content in the electrolyte solution (2 vol. %). This way, dimensions of samples synthesized from $\text{Ti}_{90}\text{Mn}_{10}$ alloy also were bigger as the applied potential was higher, starting from $d = 76 \pm 9$ nm and $l = 1.0 \pm 0.1$ μm ($\text{Ti}_{90}\text{Mn}_{10}$ _30V) and rising to $d = 118 \pm 4$ nm and $l = 2.8 \pm 0.1$ μm ($\text{Ti}_{90}\text{Mn}_{10}$ _50V). Similar behavior of morphological results were reported by Macak, et al. [46]. They performed a systematic study of the factors influencing the two-step anodization of Ti foils in ammonium fluoride-containing glycerol/water mixtures. They prepared NT layers with diameters in the range of 20–300 nm for the potentials 2–40 V, while the thickness of the NT layers, tube length, was in the range of 150 nm up to 3 μm . This dependence of the dimensions, diameter, and length, with the applied potential is in well agreement with the present work. However, herein, the electrolyte media (EG-based) favored longer tubes in the case of pristine TiO_2 NTs. Furthermore, a complementary discussion about the anodization voltage effect on the diameter of NT arrays has been reported by Macak, et al. [47]. They stated that, particularly for TiO_2 NTs, the diameter strongly depends on the applied potential and electrolyte media, and consequently a wide variety of nanotube diameters can be obtained.

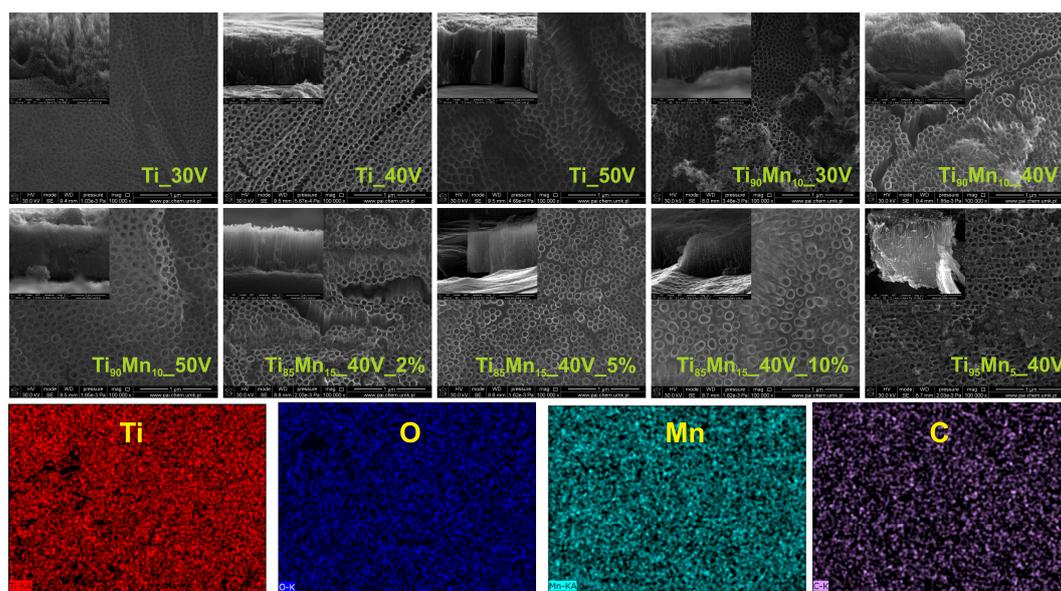


Figure 1. Top-view and cross-sectional SEM images of pristine TiO_2 and $\text{TiO}_2\text{-MnO}_2$ NTs (the effect of applied voltage, manganese content in the Mn/Ti alloy, and water content in the electrolyte on the morphology of formed nanotubes) and EDX mapping of the $\text{Ti}_{90}\text{Mn}_{10}$ _30V sample.

Table 1. Sample labels, preparation conditions, and selected properties of pristine TiO₂ and TiO₂-MnO₂ nanotubes.

Sample Label	Preparation Parameters	External Diameter (nm)	Tube Length (μm)	Wall Thickness (nm)	Average Crystallite Size (nm)	EDX Analysis			
	Electrolyte, Applied Voltage					Ti (wt. %)	Mn (wt. %)	C (wt. %)	O (wt. %)
Ti_30V	EG 98% (v/v), H ₂ O 2% (v/v), NH ₄ F 0.09 M, 30 V	81 ± 9	1.5 ± 0.1	10 ± 2	33	71.47	0	0.19	28.34
Ti_40V	EG 98% (v/v), H ₂ O 2% (v/v), NH ₄ F 0.09 M, 40 V	100 ± 7	5 ± 0.4	13 ± 2	34	66.73	0	0.03	33.24
Ti_50V	EG 98% (v/v), H ₂ O 2% (v/v), NH ₄ F 0.09 M, 50 V	120 ± 12	16.2 ± 0.2	18 ± 3	38	67.69	0	0.03	32.28
Ti ₉₀ Mn ₁₀ _30V	EG 98% (v/v), H ₂ O 2% (v/v), NH ₄ F 0.09 M, 30 V	76 ± 9	1 ± 0.1	8 ± 3	31	76.15	8.91	0.01	14.83
Ti ₉₀ Mn ₁₀ _40V	EG 98% (v/v), H ₂ O 2% (v/v), NH ₄ F 0.09 M, 40 V	92 ± 8	1.5 ± 0.1	9 ± 3	32	82.73	7.77	0.01	9.51
Ti ₉₀ Mn ₁₀ _50V	EG 98% (v/v), H ₂ O 2% (v/v), NH ₄ F 0.09 M, 50 V	118 ± 4	2.8 ± 0.1	9 ± 2	34	68.79	6.46	0.03	24.72
Ti ₈₅ Mn ₁₅ _40V_2%	EG 98% (v/v), H ₂ O 2% (v/v), NH ₄ F 0.09 M, 40 V	94 ± 11	1.3 ± 0.1	9 ± 2	31	77.20	11.14	0.01	11.67
Ti ₈₅ Mn ₁₅ _40V_5%	EG 95% (v/v), H ₂ O 5% (v/v), NH ₄ F 0.09 M, 40 V	90 ± 7	1.3 ± 0.1	9 ± 2	35	79.94	12.40	0.01	7.66
Ti ₈₅ Mn ₁₅ _40V_10%	EG 90% (v/v), H ₂ O 10% (v/v), NH ₄ F 0.09 M, 40 V	115 ± 8	1.1 ± 0.1	11 ± 2	34	61.76	9.11	1.18	27.95
Ti ₉₅ Mn ₅ _40V	EG 98% (v/v), H ₂ O 2% (v/v), NH ₄ F 0.09 M, 40 V	94 ± 8	3.4 ± 0.3	9 ± 1	32	70.89	2.10	0.03	27.00

The samples fabricated at 40 V from $\text{Ti}_{85}\text{Mn}_{15}$ alloy in electrolytes with different water content (2–10 vol. %) reported smaller length (1.1–1.3 μm) than that of the analogous non-modified ($\text{Ti}_{40\text{V}}$, $5.0 \pm 0.4 \mu\text{m}$). As it was mentioned in previous works [44,46], the increase of water in the electrolyte, provoked the increase in the formation of ripples in the tube walls. The sample prepared from the alloy with 5 wt. % of Mn showed the longest modified nanotubes ($3.4 \pm 0.3 \mu\text{m}$), presumably due to the low content of Mn in the alloy which allowed a better stabilization of the nanotube matrix by TiO_2 species. Detailed information is displayed in Table 1. As it can be seen, all TiO_2 – MnO_2 NTs were shorter, with smaller wall thickness than their pristine analog. Their length decreased with increasing the manganese content in the alloy. This could be attributed to the increase in the dissolution rate in phases with higher manganese content [32,45].

Table 1 also presents the results from EDX analysis which is in accordance with the composition of the alloys and no elements different from Ti, Mn, C, and O were found. Figure 1 presents also the EDX mapping of a selected sample where all elements are well dispersed and thus, there was not aggregation of Ti and Mn which guaranteed chemically homogeneous nanotube arrays.

A possible growth mechanism was proposed in Figure 2, based on the obtained results from SEM images of the sample $\text{Ti}_{95}\text{Mn}_5_{40\text{V}}$ anodized during 4, 15 and 60 min and information provided in literature. It is possible to observe that the current density-time curves recorded for TiO_2 – MnO_2 NTs resemble those corresponding to pristine TiO_2 NTs. The characteristic exponential decay of current density during the first stage indicates the formation of the oxide layer composed of TiO_2 and MnO_2 [45]. Progressively, the chemical etching induces the apparition of initial random pits in the mixed oxide layer due to its dissolution through the formation of the fluoride complexes $[\text{TiF}_6]^{2-}$ and $[\text{MnF}_6]^{2-}$ [48,49]. Consequently, the resistive field decreases, allowing the current density to increase along the second stage. Finally, throughout the third stage, an equilibrium is established between oxidation and chemical dissolution, leading to the self-organized nanotube growth under steady state conditions [47] allowing the auto-alignment of the nanotubes.

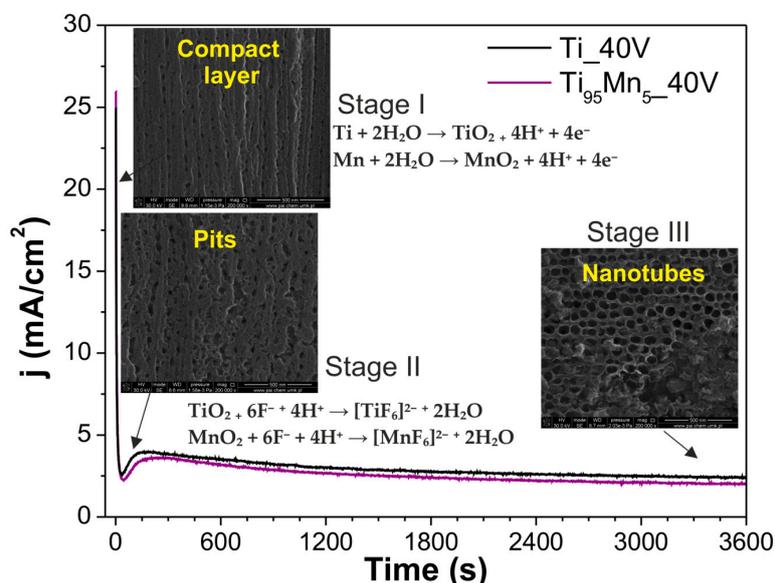


Figure 2. Proposed growth mechanism of TiO_2 – MnO_2 NTs.

2.2. Structural Properties

The XRD patterns of the as-obtained NTs are presented in Figure 3. As it can be seen, obtained pristine and TiO_2 – MnO_2 NTs consisted mainly of pure anatase TiO_2 , while the peaks of Ti came from Ti substrate. Five common planes of anatase were found, namely (101), (004), (200), (105) and (211). The intensity of anatase diffraction peaks increased with increasing the anodization potential as a result

of thicker NT layer. It was possible to observe just one characteristic peak ascribed to MnO_2 at about 58° [50,51]. The absence of any other band corresponding to the signature of MnO_2 can be related to the small content and good dispersion of manganese oxide in the TiO_2 NT layer, as it was mentioned in previous reports [32,39,52]. However, the constant diffraction peak positions indicate that the structure of TiO_2 was not changed through the anodization of Ti–Mn alloy.

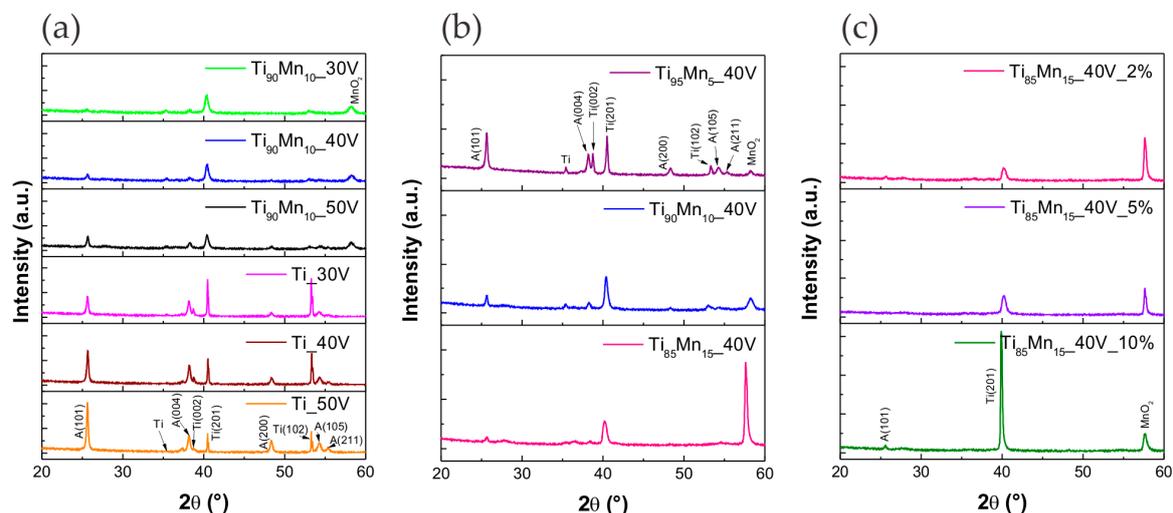


Figure 3. XRD spectra of pristine TiO_2 and TiO_2 – MnO_2 NTs. Effect of (a) anodization potential; (b) manganese content in the alloy; and (c) water content in the electrolyte.

The calculated average crystallite size for pristine and modified TiO_2 NTs is summarized in Table 1. The average crystallite size was calculated using the Scherrer equation, based on (101) diffraction peak. The largest crystallite size was observed for pristine TiO_2 NTs and varied from 33 (30 V) to 38 nm (50 V). Among Ti–Mn series, crystallite sizes tended to be smaller than those of pristine TiO_2 NTs. This can be correlated to the wall thickness, as mentioned above, wall thickness of TiO_2 – MnO_2 NTs was smaller than that of pristine TiO_2 NTs, thus there is less space to allow the growth of grain.

To further analyze the structure of the synthesized photocatalysts, micro-Raman spectroscopy was performed using a 532 nm laser as excitation light. Figure 4 displays the recorded spectra of pristine TiO_2 and TiO_2 – MnO_2 NTs. As it can be seen, the spectra of the samples obtained from alloys with 5 and 10% of Mn mainly presented the signature peaks of anatase phase which are sharper in the spectra of pristine TiO_2 NTs. These peaks at approximately 150 , 396 , 515 , and 636 cm^{-1} can be attributed to the E_g (TiO_2 symmetry), B_{1g} (O–Ti–O bending), $A_{1g} + B_{1g}$ (T–O stretching), and E_g modes of anatase as it was exposed in previous reports [53]. The presence of MnO_2 in these samples decreased the intensity and broadened the anatase bands. On the other hand, the characteristic peaks of MnO_2 at around 521 and 644 cm^{-1} , assigned to the stretching mode of octahedral MnO_6 [54], overlapped the anatase peak at 636 cm^{-1} in the spectra of the samples prepared from $\text{Ti}_{85}\text{Mn}_{15}$ alloys, making it broaden to a range of 575 – 650 cm^{-1} [52]. These spectra also showed weak bands at about 260 and 420 cm^{-1} originated from the bending modes of the metal–oxygen chain of Mn–O–Mn in the MnO_2 octahedral lattice [55–57].

2.3. Optical Properties

Figure 5 shows the absorption spectra of pristine TiO_2 and TiO_2 – MnO_2 NTs. All the samples synthesized from the Ti–Mn alloy exhibited absorption in the full visible range due to the presence of MnO_2 as it was previously reported for TiO_2 NTs coated by MnO_2 [58]. The absorption band edge of pure TiO_2 NTs at about 400 nm registered a red-shift at about 500 nm which is easier to appreciate in samples prepared from alloys with 15% of Mn. This was also observed in the case

of mesoporous structured $\text{MnO}_2/\text{TiO}_2$ nanocomposites [39]. As it was stated by Ding, et al. [59], $\text{TiO}_2\text{-MnO}_2$ NTs could be used for solar-light driven photocatalysis owing to their absorption in the UV and visible region.

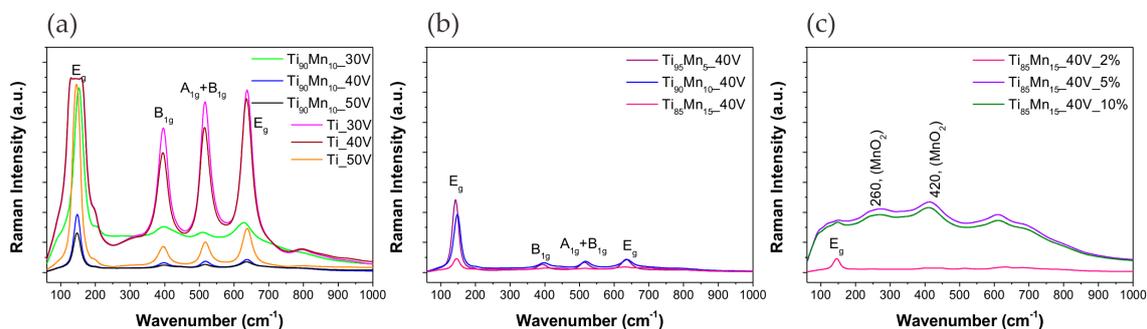


Figure 4. Raman spectra of pristine TiO_2 and $\text{TiO}_2\text{-MnO}_2$ NTs. Effect of (a) anodization potential; (b) manganese content in the alloy; and (c) water content in the electrolyte.

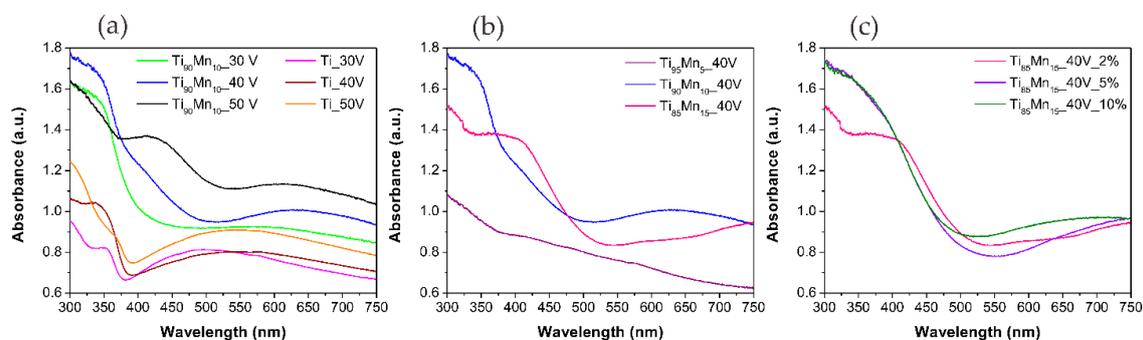


Figure 5. UV-Vis spectra of pristine TiO_2 and $\text{TiO}_2\text{-MnO}_2$ NTs. Effect of (a) anodization potential; (b) manganese content in the alloy; and (c) water content in the electrolyte.

Figure 6 shows photoluminescence (PL) spectra of both: pristine TiO_2 and $\text{TiO}_2\text{-MnO}_2$ NTs. Four emission peaks were detected among all series of photocatalysts. First one, at approximately 420 nm can be ascribed to the existence of self-trapped excitons from TiO_6^{8-} octahedron, while the second and third peaks at 450 and 485 nm are associated with the presence of surface defects and oxygen vacancies. The last peak at approximately 525 nm is associated with radiative recombination of charge carriers [60,61].

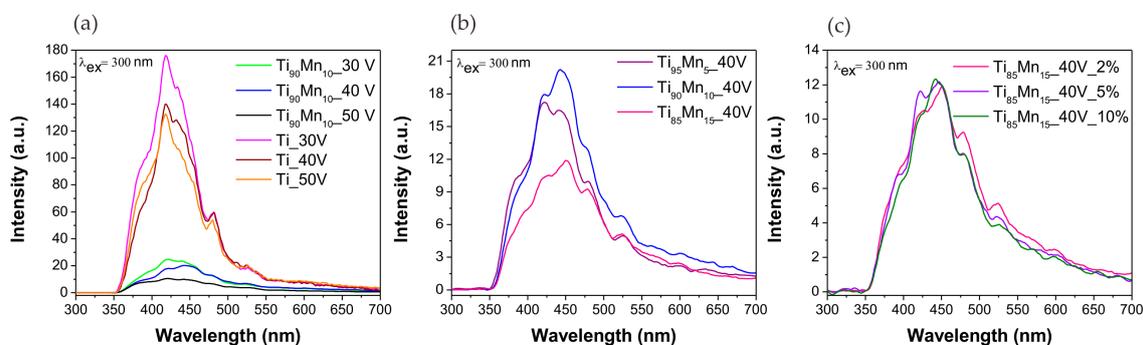


Figure 6. Photoluminescence spectra of pristine TiO_2 and $\text{TiO}_2\text{-MnO}_2$ NTs. Effect of (a) anodization potential; (b) manganese content in the alloy; and (c) water content in the electrolyte.

2.4. Photocatalytic Performance

The photoactivity of the prepared samples was tested in the visible-light-driven photodegradation of toluene (200 ppmv) from an air mixture. The irradiation source consisted of a LED array with $\lambda_{\max} = 465$ nm. The effect of anodization voltage, manganese content in the alloy and water content in the electrolyte was systematically studied. Figure 7 presents the degradation curves in the presence of obtained NT photocatalysts and a reference curve in the absence of any photocatalyst, to test photolysis. It is clearly showed that in the reference curve, degradation was not achieved. Pristine TiO_2 NTs exhibited insignificant toluene removal (about 5%) while all of the samples were photoactive towards the degradation of the model pollutant. Figure 7a shows that the highest degradation after 60 min of irradiation was achieved in the presence of the $\text{Ti}_{90}\text{Mn}_{10}$ -30V sample (43%). The samples anodized from $\text{Ti}_{90}\text{Mn}_{10}$ alloys at 40 V and 50 V reported similar toluene removal, 28% and 33% respectively. The results displayed in Figure 7b indicate that the manganese content in the alloy inversely affected the photoactivity, the higher the manganese content in the alloy was, the less degradation was achieved. This way, samples prepared from alloys with 5, 10 and 15 wt. % of manganese reached a degradation of 29%, 28%, and 24%, respectively. This was also observed by Xue, Huang, Wang, Wang, Gao, Zhu, and Zou [39] in the dye-mediated photodegradation of MB under visible light in the presence of mesoporous $\text{MnO}_2/\text{TiO}_2$ nanocomposites. They attributed the lower degradation to the accumulation of MnO_2 on the surface of TiO_2 which increased the transfer rate of photogenerated electrons within MnO_2 , overall weakening the effect of improving the photoactivity. The photoactivity of the samples from the series with different water content in the electrolyte was similar between each other (Figure 7c), the highest toluene removal (28%) was accomplished by the sample with 10% of water in the electrolyte. The other two samples exhibited 24% of toluene removal. The kinetic parameters of each photocatalyst are included in Table 2.

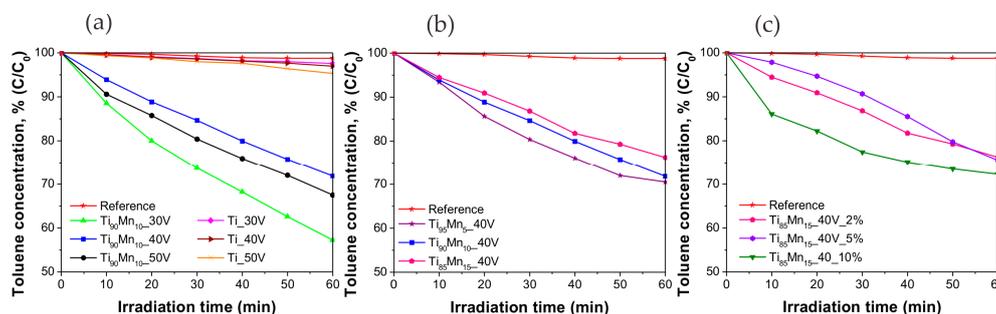


Figure 7. Photoactivity of pristine TiO_2 and $\text{TiO}_2\text{-MnO}_2$ NTs in gas phase degradation of toluene under Vis light irradiation ($\lambda_{\max} = 465$ nm). Effect of (a) applied voltage; (b) manganese content in the alloy, and (c) water content in the electrolyte.

Table 2. Initial reaction rate and reaction rate constant for the gas phase degradation of toluene (200 ppmv) under Vis light irradiation (25-LED array, $\lambda_{\max} = 465$ nm, irradiation intensity = $14.5 \text{ mW}\cdot\text{cm}^{-2}$) in the presence of pristine TiO_2 and $\text{TiO}_2\text{-MnO}_2$ NTs.

Sample Label	Photocatalytic Toluene Degradation	
	Initial Reaction Rate $\times 10^2$ ($\mu\text{mol}\cdot\text{dm}^{-3}\cdot\text{min}^{-1}$)	Reaction Rate Constant $\times 10^3$ (min^{-1})
Ti_30V	0.37 ± 0.09	0.42 ± 0.10
Ti_40V	0.43 ± 0.09	0.49 ± 0.10
Ti_50V	0.64 ± 0.04	0.72 ± 0.04
$\text{Ti}_{90}\text{Mn}_{10}$ -30V	8.54 ± 0.53	9.57 ± 0.59
$\text{Ti}_{90}\text{Mn}_{10}$ -40V	4.97 ± 0.30	5.57 ± 0.33
$\text{Ti}_{90}\text{Mn}_{10}$ -50V	6.04 ± 0.08	6.77 ± 0.09
$\text{Ti}_{85}\text{Mn}_{15}$ -40V_2%	4.18 ± 0.77	4.69 ± 0.87
$\text{Ti}_{85}\text{Mn}_{15}$ -40V_5%	3.79 ± 0.43	4.24 ± 0.48
$\text{Ti}_{85}\text{Mn}_{15}$ -40V_10%	5.84 ± 1.61	6.54 ± 1.81
$\text{Ti}_{95}\text{Mn}_5$ -40V	5.76 ± 0.12	6.45 ± 0.14

The highest initial reaction rate ($8.54 \pm 0.53 \times 10^{-2} \mu\text{mol}\cdot\text{dm}^{-3}\cdot\text{min}^{-1}$) and reaction rate constant ($9.57 \pm 0.59 \times 10^{-3} \text{min}^{-1}$) were observed for the toluene degradation over the $\text{Ti}_{90}\text{Mn}_{10}\text{-30V}$ sample and they were more than 23 times higher compared with those of pristine TiO_2 NTs obtained by anodization at 30 V ($0.37 \pm 0.09 \times 10^{-2} \mu\text{mol}\cdot\text{dm}^{-3}\cdot\text{min}^{-1}$ and $0.42 \pm 0.10 \times 10^{-3} \text{min}^{-1}$).

As shown in Table 2, the most photoactive sample, $\text{Ti}_{90}\text{Mn}_{10}\text{-30V}$, was used to analyze the effect of the irradiation wavelength ($\lambda_{\text{max}} = 375, 415$ and 465 nm) in the same degradation reaction. As evident from Figure 8a, the maximum toluene removal (43%) was reached under 465 nm while under 375 nm (UV light) and 415 nm (25% and 20% of degradation, respectively) the sample was less active. This can be explained by a synergistic effect of MnO_2 and TiO_2 in the NT matrix. As it was formerly reported [58], MnO_2 has lower photoactivity than TiO_2 under UV light irradiation, and thereby, this narrow-bandgap semiconductor reduced the overall photoactivity of the composite in this wavelength range because of a synergistic effect in the composite. This behavior under UV light was also exposed by Xue, et al. [39] who indicated that the transferring of photoexcited electrons (generated in TiO_2) within MnO_2 can correspond to an internal dissipation able to suppress the photocatalytic activity. On the other hand, Xu, et al. [58] reported improved visible light-photoactivity for NTs electrodeposited with MnO_2 . Therefore, we can conclude that the presence of MnO_2 in TiO_2 NTs favored the conditions for the degradation of toluene in gas phase under visible light (longer wavelength of irradiation) owing to the ability of MnO_2 species to absorb visible light irradiation and promote the enhancement of the charge transfer rate.

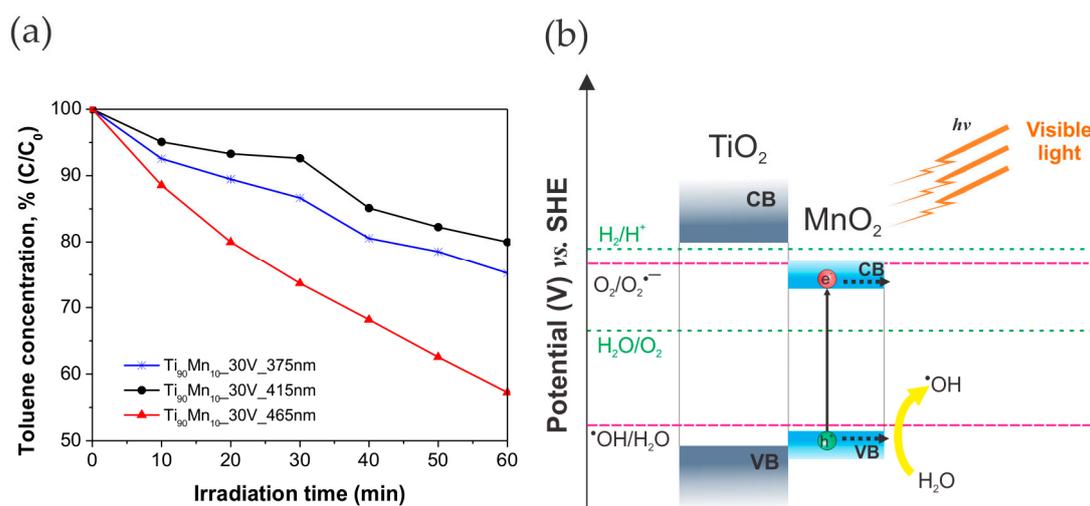


Figure 8. (a) Photoactivity of $\text{Ti}_{90}\text{Mn}_{10}\text{-30V}$ sample in gas phase degradation of toluene under different wavelengths of irradiation ($\lambda_{\text{max}} = 375, 415, 465 \text{ nm}$) and (b) possible excitation mechanism of $\text{TiO}_2\text{-MnO}_2$ NTs under Vis light irradiation.

Additionally, a possible excitation mechanism of $\text{TiO}_2\text{-MnO}_2$ NTs under Vis light was proposed and diagrammed in Figure 8b. The conduction band and valence band edge values of MnO_2 were calculated to be 0.57 and 2.34 eV, respectively [34]. Thus, it is likely that photogenerated holes from the valence band (VB) of MnO_2 could be involved in the formation of hydroxyl radicals (OH^{\bullet}), while electrons from the CB of MnO_2 can participate indirectly in the degradation of toluene, considering that the potential of photogenerated electrons is not high enough to generate other reactive oxygen species, such as $\text{O}_2^{\bullet-}$, H_2O_2 , and HO_2^{\bullet} radicals.

3. Materials and Methods

3.1. Materials

Acetone, isopropanol, and methanol were purchased from P.P.H. "STANLAB" Sp. J. (Lublin, Poland), while ethylene glycol (EG) from CHEMPUR and ammonium fluoride from ACROS ORGANICS. Technical grade Ti foils and Ti–Mn alloys with 5, 10 and 15 wt. % of manganese content were provided by HMW-Hauner Metallische Werkstoffe (Röttenbach, Germany). Deionized (DI) water with conductivity of 0.05 μS was used to prepare all aqueous solutions.

3.2. Synthesis of Pristine TiO_2 and TiO_2 – MnO_2 Nanotubes

Ti foils as well as Ti–Mn alloys were ultrasonically cleaned in acetone, isopropanol, methanol, and deionized water for 10 min, respectively. Then, foils were dried in an air stream. The anodization processes were carried out at room temperature, in an electrochemical cell consisting of a platinum mesh as counter electrode, and the Ti foils or the Ti–Mn alloy (2.5 cm \times 2.5 cm) as working electrode. A reference electrode of Ag/AgCl connected to a digital multimeter (BRYMEN BM857a) was used to control and record information about the actual potential and current on the alloy. The anodization was conducted in an electrolyte composed of EG, water and NH_4F 0.09 M, during 60 min with a voltage in the range of 30–50 V applied with a programmable DC power supply (MANSON SDP 2603). Three electrolyte solutions with different water content were used (volume ratios of EG:water of 98:2, 95:5 and 90:10). The obtained samples were rinsed with deionized water, sonicated in deionized water (1 min), dried in air (80 $^\circ\text{C}$ for 24 h), and calcined (450 $^\circ\text{C}$, heating rate 2 $^\circ\text{C}/\text{min}$) for 1 h.

3.3. Characterization of Pristine TiO_2 and TiO_2 – MnO_2 Nanotubes

The morphology of synthesized pristine TiO_2 and TiO_2 – MnO_2 nanotubes was determined by using scanning electron microscopy (SEM, FEI QUANTA 3D FEG, FEI Company, Brno, Czech Republic). Energy-dispersive X-ray spectroscopy (EDX) analysis were performed with a scanning electron microscope (SEM, Zeiss, Leo 1430 VP, Carl Zeiss, Oberkochen, Germany) coupled to an energy-dispersive X-ray fluorescence spectrometer (EDX) Quantax 200 with the XFlash 4010 (Bruker AXS, Karlsruhe, Germany) detector. The crystal structure of the samples was determined from X-ray diffraction patterns recorded in the range of $2\theta = 20^\circ$ – 90° , using an X-ray diffractometer (X'Pert Pro, Panalytical, Almelo, The Netherlands) with $\text{Cu K}\alpha$ radiation. The crystallite size was calculated based on the Scherrer formula. Raman spectra were measured with a micro-Raman spectrometer (Senterra, Bruker Optik, Billerica, MA, USA) with a 532 nm excitation laser. The UV-Vis absorbance spectra were registered with the UV-VIS Spectrophotometer, SHIMADZU UV-2600, in the wavelength range of 300–800 nm equipped with an integrating sphere. The baseline was determined with barium sulfate as reference, the scanning speed was 250 nm/min at room temperature. The photoluminescence (PL) spectra were recorded at room temperature with a LS-50B Luminescence Spectrometer equipped with a Xenon discharge lamp, as an excitation source, and a R928 photomultiplier as detector. The excitation radiation (300 nm) was directed on the surface of the samples at an angle of 90° .

3.4. Measurement of Photocatalytic Activity

Photocatalytic activity of the as-prepared NTs was analyzed, for the first time, in the purification of air from toluene which was used as a model pollutant. The photodegradation experiments were carried out in a stainless steel reactor of a volume of ca. 35 cm^3 . The reactor included a quartz window, two valves and a septum. The light source consisting of an array of 25 LEDs ($\lambda_{\text{max}} = 375, 415$ and 465 nm, Optel, Opole, Poland) was located above the sample. The anodized foil was placed at the bottom side of the reactor and it was closed with the quartz window. A gas mixture (toluene, 200 ppmv) was passed through the reactor for 1 min, then the valves were closed and the reactor was kept in dark for 30 min in order to achieve the equilibrium. Before starting the irradiation, a reference toluene

sample was taken. The concentration was determined by using a gas chromatograph (TRACE 1300, Thermo Scientific, Waltham, MA, USA), equipped with an ionization flame detector (FID) and an Elite-5 capillary column. The samples (200 μL) were dosed with a gas-tight syringe each 10 min. Irradiation intensity was measured by an optical power meter (HAMAMATSU, C9536-01, Hamamatsu, Japan) and reached 14.7, 14.1 and 14.5 mW/cm^2 for LEDs with $\lambda_{\text{max}} = 375, 415$ and 465 nm, respectively.

4. Conclusions

The analysis of the effect of applied potential, manganese content in the alloy and water content in the electrolyte on the morphology and visible-light photocatalytic activity of $\text{TiO}_2\text{-MnO}_2$ NTs obtained from one-step anodic oxidation of Ti-Mn alloys in a fluoride-containing EG-based electrolyte was reported here for the first time. All fabricated samples were described as vertically-oriented, self-organized nanotube arrays with a diameter of 76–115 nm and length of 1–3.4 μm . Diameter and length were directly influenced by the applied voltage while the manganese content led to obtain shorter tubes than those prepared from Ti sheets. The as-prepared $\text{TiO}_2\text{-MnO}_2$ arrays exhibited improved optical and photocatalytic properties in comparison with those of pristine TiO_2 NTs. The photoactivity assessment was carried out towards the degradation of toluene (200 ppmv) in gas phase under Vis light irradiation (LEDs, $\lambda_{\text{max}} = 465$ nm). The highest degradation after 60 min of irradiation corresponded to 43% and the initial reaction rate reached values of $3.79\text{--}8.54 \times 10^{-2} \mu\text{mol}\cdot\text{dm}^{-3}\cdot\text{min}^{-1}$. A wavelength dependence exploration was performed as well, MnO_2 modified NTs showed the highest activity under visible light irradiation and therefore, a possible mechanism of excitation was presented. These findings suggest that $\text{TiO}_2\text{-MnO}_2$ mixed oxide nanotube arrays, activated by low-powered LEDs, could be a promising material for air purification systems. Moreover, the electrochemical approach is a successful way to obtain these highly-organized nanostructures from Ti-Mn alloys. Consequently, the industrially-oriented application of photocatalysis for air treatment using LEDs, as a low-cost and suitable irradiation source, follows the trends of green chemistry and environmentally friendly performance.

Acknowledgments: This research was financially supported by the Polish National Science Center (research grant, Ordered TiO_2/MxOy nanostructures obtained by electrochemical method; contract No. NCN 2014/15/B/ST5/00098).

Author Contributions: A.Z.-M. supervised and directed the project; A.Z.-M. and P.M. conceived the concept; M.C.N.-M., P.M., M.P.K., A.M., M.K., J.W., G.T. performed the experiments; M.C.N.-M., P.M., and M.K. analyzed the data; M.C.N.-M., P.M., and M.P.K. contributed reagents/materials/analysis tools; M.N.-M., P.M., P.J.E.-M. and A.Z.-M. wrote the paper.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Gaya, U.I.; Abdullah, A.H. Heterogeneous photocatalytic degradation of organic contaminants over titanium dioxide: A review of fundamentals, progress and problems. *J. Photochem. Photobiol. C Photochem. Rev.* **2008**, *9*, 1–12.
2. Pichat, P. *Photocatalysis and Water Purification: From Fundamentals to Recent Applications*; John Wiley & Sons: Hoboken, NJ, USA, 2013.
3. Schneider, J.; Bahnemann, D.; Ye, J.; Puma, G.L.; Dionysiou, D.D. *Photocatalysis: Fundamentals and Perspectives*; Royal Society of Chemistry: Cambridge, UK, 2016.
4. Dionysiou, D.D.; Puma, G.L.; Ye, J.; Schneider, J.; Bahnemann, D. *Photocatalysis: Applications*; Royal Society of Chemistry: Cambridge, UK, 2016.
5. Pichat, P. *Photocatalysis: Fundamentals, Materials and Potential*; MDPI: Basel, Switzerland, 2016.
6. Colmenares Quintero, J.C.; Xu, Y.-J. *Heterogeneous Photocatalysis: From Fundamentals to Green Applications*; Springer: Berlin/Heidelberg, Germany, 2016; Volume VIII, p. 416.
7. Mazierski, P.; Nadolna, J.; Lisowski, W.; Winiarski, M.J.; Gazda, M.; Nischk, M.; Klimczuk, T.; Zaleska-Medynska, A. Effect of irradiation intensity and initial pollutant concentration on gas phase photocatalytic activity of TiO_2 nanotube arrays. *Catal. Today* **2017**, *284*, 19–26. [[CrossRef](#)]

8. Zavahir, S.; Xiao, Q.; Sarina, S.; Zhao, J.; Bottle, S.; Wellard, M.; Jia, J.; Jing, L.; Huang, Y.; Blinco, J.P.; et al. Selective oxidation of aliphatic alcohols using molecular oxygen at ambient temperature: Mixed-valence vanadium oxide photocatalysts. *ACS Catal.* **2016**, *6*, 3580–3588. [[CrossRef](#)]
9. Kang, D.; Kim, T.W.; Kubota, S.R.; Cardiel, A.C.; Cha, H.G.; Choi, K.S. Electrochemical synthesis of photoelectrodes and catalysts for use in solar water splitting. *Chem. Rev.* **2015**, *115*, 12839–12887. [[CrossRef](#)] [[PubMed](#)]
10. Highfield, J. Advances and recent trends in heterogeneous photo(electro)-catalysis for solar fuels and chemicals. *Molecules* **2015**, *20*, 6739–6793. [[CrossRef](#)] [[PubMed](#)]
11. Sethi, D.; Jada, N.; Tiwari, A.; Ramasamy, S.; Dash, T.; Pandey, S. Photocatalytic destruction of escherichia coli in water by V₂O₅/TiO₂. *J. Photochem. Photobiol. B* **2015**, *144*, 68–74. [[CrossRef](#)] [[PubMed](#)]
12. Low, J.; Cheng, B.; Yu, J. Surface modification and enhanced photocatalytic CO₂ reduction performance of TiO₂: A review. *Appl. Surf. Sci.* **2017**, *392*, 658–686. [[CrossRef](#)]
13. Wang, R.; Hashimoto, K.; Fujishima, A.; Chikuni, M.; Kojima, E.; Kitamura, A.; Shimohigoshi, M.; Watanabe, T. Light-induced amphiphilic surfaces. *Nature* **1997**, *388*, 431–432. [[CrossRef](#)]
14. Pichat, P. Self-cleaning materials based on solar photocatalysis. In *New and Future Developments in Catalysis: Solar Photocatalysis*; Suib, S.L., Ed.; Elsevier: Amsterdam, The Netherlands, 2013; Volume 7 “Solar catalysis”, pp. 167–190.
15. Ye, M.; Zheng, D.; Wang, M.; Chen, C.; Liao, W.; Lin, C.; Lin, Z. Hierarchically structured microspheres for high-efficiency rutile TiO₂-based dye-sensitized solar cells. *ACS Appl. Mater. Interfaces* **2014**, *6*, 2893–2901. [[CrossRef](#)] [[PubMed](#)]
16. Wang, Z.; Ma, W.; Chen, C.; Zhao, J. Sensitization of titania semiconductor: A promising strategy to utilize visible light. In *Photocatalysis and Water Purification*; Pichat, P., Ed.; Wiley-VCH: Weinheim, Germany, 2013; pp. 199–240.
17. Zhang, H.; Banfield, J.F. Structural characteristics and mechanical and thermodynamic properties of nanocrystalline TiO₂. *Chem. Rev.* **2014**, *114*, 9613–9644. [[CrossRef](#)] [[PubMed](#)]
18. Banerjee, S.; Pillai, S.C.; Falaras, P.; O’Shea, K.E.; Byrne, J.A.; Dionysiou, D.D. New insights into the mechanism of visible light photocatalysis. *J. Phys. Chem. Lett.* **2014**, *5*, 2543–2554. [[CrossRef](#)] [[PubMed](#)]
19. Sato, S.; White, J.M. Photodecomposition of water over Pt/TiO₂ catalysts. *Chem. Phys. Lett.* **1980**, *72*, 83–86. [[CrossRef](#)]
20. Ohtani, B.; Osaki, H.; Nishimoto, S.; Kagiya, T. A novel photocatalytic process of amine N-alkylation by platinumized semiconductor particles suspended in alcohols. *J. Am. Chem. Soc.* **1986**, *108*, 308–310. [[CrossRef](#)]
21. Pichat, P. Surface-properties, activity and selectivity of bifunctional powder photocatalysts. *New J. Chem.* **1987**, *11*, 135–140.
22. Choi, W.; Termin, A.; Hoffmann, M.R. The role of metal ion dopants in quantum-sized TiO₂: Correlation between photoreactivity and charge carrier recombination dynamics. *J. Phys. Chem.* **1994**, *98*, 13669–13679. [[CrossRef](#)]
23. Asahi, R.; Morikawa, T.; Ohwaki, T.; Aoki, K.; Taga, Y. Visible-light photocatalysis in nitrogen-doped titanium oxides. *Science* **2001**, *293*, 269–271. [[CrossRef](#)] [[PubMed](#)]
24. Mazierski, P.; Lisowski, W.; Grzyb, T.; Winiarski, M.J.; Klimczuk, T.; Mikołajczyk, A.; Flisikowski, J.; Hirsch, A.; Kołakowska, A.; Puzyn, T.; et al. Enhanced photocatalytic properties of lanthanide-TiO₂ nanotubes: An experimental and theoretical study. *Appl. Catal. B Environ.* **2017**, *205*, 376–385. [[CrossRef](#)]
25. Mazierski, P.; Nischk, M.; Gołkowska, M.; Lisowski, W.; Gazda, M.; Winiarski, M.J.; Klimczuk, T.; Zaleska-Medynska, A. Photocatalytic activity of nitrogen doped TiO₂ nanotubes prepared by anodic oxidation: The effect of applied voltage, anodization time and amount of nitrogen dopant. *Appl. Catal. B Environ.* **2016**, *196*, 77–88. [[CrossRef](#)]
26. Ouyang, J.; Chang, M.; Li, X. CdS-sensitized ZnO nanorod arrays coated with TiO₂ layer for visible light photoelectrocatalysis. *J. Mater. Sci.* **2012**, *47*, 4187–4193. [[CrossRef](#)]
27. Diak, M.; Grabowska, E.; Zaleska, A. Synthesis, characterization and photocatalytic activity of noble metal-modified TiO₂ nanosheets with exposed {001} facets. *Appl. Surf. Sci.* **2015**, *347*, 275–285. [[CrossRef](#)]
28. Nischk, M.; Mazierski, P.; Wei, Z.; Siuzdak, K.; Kouame, N.A.; Kowalska, E.; Remita, H.; Zaleska-Medynska, A. Enhanced photocatalytic, electrochemical and photoelectrochemical properties of TiO₂ nanotubes arrays modified with Cu, AgCu and Bi nanoparticles obtained via radiolytic reduction. *Appl. Surf. Sci.* **2016**, *387*, 89–102. [[CrossRef](#)] [[PubMed](#)]

29. Chatterjee, D.; Mahata, A. Demineralization of organic pollutants on the dye modified TiO₂ semiconductor particulate system using visible light. *Appl. Catal. B Environ.* **2001**, *33*, 119–125. [[CrossRef](#)]
30. Paramasivam, I.; Nah, Y.C.; Das, C.; Shrestha, N.K.; Schmuki, P. WO₃/TiO₂ nanotubes with strongly enhanced photocatalytic activity. *Chemistry* **2010**, *16*, 8993–8997. [[CrossRef](#)] [[PubMed](#)]
31. Zhou, H.; Zhang, Y. Electrochemically self-doped TiO₂ nanotube arrays for supercapacitors. *J. Phys. Chem. C* **2014**, *118*, 5626–5636. [[CrossRef](#)]
32. Ning, X.; Wang, X.; Yu, X.; Li, J.; Zhao, J. Preparation and capacitance properties of Mn-doped TiO₂ nanotube arrays by anodisation of Ti–Mn alloy. *J. Alloys Compd.* **2016**, *658*, 177–182. [[CrossRef](#)]
33. Islam, A.K.M.F.U.; Islam, R.; Khan, K.A. Studies on the thermoelectric effect in semiconducting MnO₂ thin films. *J. Mater. Sci. Mater. Electron.* **2005**, *16*, 203–207. [[CrossRef](#)]
34. Zhao, J.; Nan, J.; Zhao, Z.; Li, N.; Liu, J.; Cui, F. Energy-efficient fabrication of a novel multivalence Mn₃O₄–MnO₂ heterojunction for dye degradation under visible light irradiation. *Appl. Catal. B Environ.* **2017**, *202*, 509–517. [[CrossRef](#)]
35. Pinaud, B.A.; Chen, Z.; Abram, D.N.; Jaramillo, T.F. Thin films of sodium birnessite-type MnO₂: Optical properties, electronic band structure, and solar photoelectrochemistry. *J. Phys. Chem. C* **2011**, *115*, 11830–11838. [[CrossRef](#)]
36. Chen, Z.; Jaramillo, T.F.; Deutsch, T.G.; Kleiman-Shwarsctein, A.; Forman, A.J.; Gaillard, N.; Garland, R.; Takanabe, K.; Heske, C.; Sunkara, M.; et al. Accelerating materials development for photoelectrochemical hydrogen production: Standards for methods, definitions, and reporting protocols. *J. Mater. Res.* **2011**, *25*, 3–16. [[CrossRef](#)]
37. Sherman, D.M. Electronic structures of iron(III) and manganese(IV) (hydr)oxide minerals: Thermodynamics of photochemical reductive dissolution in aquatic environments. *Geochim. Cosmochim. Acta* **2005**, *69*, 3249–3255. [[CrossRef](#)]
38. Sakai, N.; Ebina, Y.; Takada, K.; Sasaki, T. Photocurrent generation from semiconducting manganese oxide nanosheets in response to visible light. *J. Phys. Chem. B* **2005**, *109*, 9651–9655. [[CrossRef](#)] [[PubMed](#)]
39. Xue, M.; Huang, L.; Wang, J.Q.; Wang, Y.; Gao, L.; Zhu, J.H.; Zou, Z.G. The direct synthesis of mesoporous structured MnO₂/TiO₂ nanocomposite: A novel visible-light active photocatalyst with large pore size. *Nanotechnology* **2008**, *19*, 185604. [[CrossRef](#)] [[PubMed](#)]
40. Roy, P.; Berger, S.; Schmuki, P. TiO₂ nanotubes: Synthesis and applications. *Angew. Chem. Int. Ed. Engl.* **2011**, *50*, 2904–2939. [[CrossRef](#)] [[PubMed](#)]
41. Iijima, S. Helical microtubules of graphitic carbon. *Nature* **1991**, *354*, 56–58. [[CrossRef](#)]
42. Kubacka, A.; Fernandez-Garcia, M.; Colon, G. Advanced nanoarchitectures for solar photocatalytic applications. *Chem. Rev.* **2012**, *112*, 1555–1614. [[CrossRef](#)] [[PubMed](#)]
43. Pichat, P. Are TiO₂ nanotubes worth using in photocatalytic purification of air and water? *Molecules* **2014**, *19*, 15075–15087. [[CrossRef](#)] [[PubMed](#)]
44. Lee, K.; Mazare, A.; Schmuki, P. One-dimensional titanium dioxide nanomaterials: Nanotubes. *Chem. Rev.* **2014**, *114*, 9385–9454. [[CrossRef](#)] [[PubMed](#)]
45. Mohapatra, S.K.; Raja, K.S.; Misra, M.; Mahajan, V.K.; Ahmadian, M. Synthesis of self-organized mixed oxide nanotubes by sonoelectrochemical anodization of Ti–8Mn alloy. *Electrochim. Acta* **2007**, *53*, 590–597. [[CrossRef](#)]
46. Macak, J.M.; Hildebrand, H.; Marten-Jahns, U.; Schmuki, P. Mechanistic aspects and growth of large diameter self-organized TiO₂ nanotubes. *J. Electroanal. Chem.* **2008**, *621*, 254–266. [[CrossRef](#)]
47. Macak, J.M.; Tsuchiya, H.; Ghicov, A.; Yasuda, K.; Hahn, R.; Bauer, S.; Schmuki, P. TiO₂ nanotubes: Self-organized electrochemical formation, properties and applications. *Curr. Opin. Solid State Mater. Sci.* **2007**, *11*, 3–18. [[CrossRef](#)]
48. Helmholz, L.; Russo, M.E. Spectra of manganese(IV) hexafluoride ion (MnF₆^{2−}) in environments of O_h and D_{3d} symmetry. *J. Chem. Phys.* **1973**, *59*, 5455–5470. [[CrossRef](#)]
49. Pourbaix, M. *Atlas of Electrochemical Equilibria in Aqueous Solutions*; Pergamon Press: New York, NY, USA, 1966.
50. Devaraj, S.; Munichandraiah, N. Effect of crystallographic structure of MnO₂ on its electrochemical capacitance properties. *J. Phys. Chem. C* **2008**, *112*, 4406–4417. [[CrossRef](#)]
51. Li, J.; Chen, J.; Ke, R.; Luo, C.; Hao, J. Effects of precursors on the surface Mn species and the activities for NO reduction over MnO_x/TiO₂ catalysts. *Catal. Commun.* **2007**, *8*, 1896–1900. [[CrossRef](#)]

52. Liao, J.-Y.; Higgins, D.; Lui, G.; Chabot, V.; Xiao, X.; Chen, Z. Multifunctional TiO₂-C/MnO₂ core-double-shell nanowire arrays as high-performance 3D electrodes for lithium ion batteries. *Nano Lett.* **2013**, *13*, 5467–5473. [[CrossRef](#)] [[PubMed](#)]
53. Borbón-Nuñez, H.A.; Dominguez, D.; Muñoz-Muñoz, F.; Lopez, J.; Romo-Herrera, J.; Soto, G.; Tiznado, H. Fabrication of hollow TiO₂ nanotubes through atomic layer deposition and MWCNT templates. *Powder Technol.* **2017**, *308*, 249–257. [[CrossRef](#)]
54. Jana, S.; Basu, S.; Pande, S.; Ghosh, S.K.; Pal, T. Shape-selective synthesis, magnetic properties, and catalytic activity of single crystalline β-MnO₂ nanoparticles. *J. Phys. Chem. C* **2007**, *111*, 16272–16277. [[CrossRef](#)]
55. Wei, M.; Konishi, Y.; Zhou, H.; Sugihara, H.; Arakawa, H. Synthesis of single-crystal manganese dioxide nanowires by a soft chemical process. *Nanotechnology* **2005**, *16*, 245–249. [[CrossRef](#)] [[PubMed](#)]
56. Jana, S.; Pande, S.; Sinha, A.K.; Sarkar, S.; Pradhan, M.; Basu, M.; Saha, S.; Pal, T. A green chemistry approach for the synthesis of flower-like Ag-doped MnO₂ nanostructures probed by surface-enhanced raman spectroscopy. *J. Phys. Chem. C* **2009**, *113*, 1386–1392. [[CrossRef](#)]
57. Luo, J.; Zhu, H.T.; Fan, H.M.; Liang, J.K.; Shi, H.L.; Rao, G.H.; Li, J.B.; Du, Z.M.; Shen, Z.X. Synthesis of single-crystal tetragonal α-MnO₂ nanotubes. *J. Phys. Chem. C* **2008**, *112*, 12594–12598. [[CrossRef](#)]
58. Xu, X.; Zhou, X.; Li, X.; Yang, F.; Jin, B.; Xu, T.; Li, G.; Li, M. Electrodeposition synthesis of MnO₂/TiO₂ nanotube arrays nanocomposites and their visible light photocatalytic activity. *Mater. Res. Bull.* **2014**, *59*, 32–36. [[CrossRef](#)]
59. Ding, S.; Liyong, W.; Shaoyan, Z.; Qiuxiang, Z.; Yu, D.; Shujuan, L.; Yanchao, L.; Quanying, K. Hydrothermal synthesis, structure and photocatalytic property of nano-TiO₂-MnO₂. *Sci. China Ser. B* **2003**, *46*, 542. [[CrossRef](#)]
60. Tang, H.; Berger, H.; Schmid, P.E.; Lévy, F. Optical properties of anatase (TiO₂). *Solid State Commun.* **1994**, *92*, 267–271. [[CrossRef](#)]
61. Knorr, F.J.; Mercado, C.C.; McHale, J.L. Trap-state distributions and carrier transport in pure and mixed-phase TiO₂: Influence of contacting solvent and interphasial electron transfer. *J. Phys. Chem. C* **2008**, *112*, 12786–12794. [[CrossRef](#)]

Sample Availability: Samples of the compounds are available from the authors.



© 2017 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).