

Article

Modeling the Effect of Composition and Temperature on the Conductivity of Synthetic Copper Electrorefining Electrolyte

Taina Kalliomäki *, Jari Aromaa and Mari Lundström

Department of Materials Science and Engineering, School of Chemical Technology, Aalto University, P.O. Box 16200, Aalto FI-00076, Finland; jari.aromaa@aalto.fi (J.A.); mari.lundstrom@aalto.fi (M.L.)

* Correspondence: Taina.Kalliomaki@aalto.fi; Tel.: +358-40-734-8658

Academic Editor: William Skinner

Received: 1 March 2016; Accepted: 13 June 2016; Published: 24 June 2016

Abstract: The physico-chemical properties of the copper electrolyte significantly affect the energy consumption of the electrorefining process and the quality of the cathode product. Favorable conditions for electrorefining processes are typically achieved by keeping both the electrolyte conductivity and diffusion coefficient of Cu(II) high, while ensuring low electrolyte viscosity. In this work the conductivity of the copper electrorefining electrolyte was investigated as a function of temperature (50–70 °C) and concentrations of copper (Cu(II), 40–60 g/L), nickel (Ni(II), 0–20 g/L), arsenic (As(III), 0–30 g/L) and sulfuric acid (160–220 g/L). In total 165 different combinations of these factors were studied. The results were treated using factorial analysis, and as a result, four electrolyte conductivity models were built up. Models were constructed both with and without arsenic as the presence of As(III) appeared to cause non-linearity in some factor effects and thus impacted the conductivity in more complex ways than previously detailed in literature. In all models the combined effect of factors was shown to be minor when compared to the effect of single factors. Conductivity was shown to increase when copper, nickel and arsenic concentrations were decreased and increase with increased temperature and acidity. Moreover, the arsenic concentration was shown to decrease the level of conductivity more than previously suggested in the literature.

Keywords: copper electrorefining electrolyte; conductivity; conductivity model

1. Introduction

Copper electrorefining is the most common method for producing high-purity copper [1]. The first refinery (Pembrey Copper Works) was established in 1869 following the first patent for commercial electrorefining developed by James Elkington in 1865 [2,3]. Since then, the process has been developed further as the result of both research and improved industrial practices [2]. In the copper electrorefining process, copper is dissolved from impure copper anodes into the electrolyte bath and then subsequently deposited on to cathodes as high-purity copper [4].

Industrial copper refining electrolytes mainly consist of water, copper sulfate, sulfuric acid, with additional leveling/grain-refining agents—to obtain smoother and denser cathode deposits—and process impurities [4,5]. These impurities commonly consist of nickel, arsenic and iron, along with smaller amounts of bismuth, antimony and chloride that dissolve into the electrolyte from the anode.

The physico-chemical properties of the copper electrolyte significantly affect the yield of cathodic copper in the electrorefining process and include four main physico-chemical properties: conductivity, density, viscosity and the diffusion coefficient of the cupric ion (Cu(II)) [5–11]. The best yield of copper can be obtained by keeping the electrolyte viscosity low [5] while ensuring a high diffusion coefficient [7] and electrical conductivity [5]. These properties of the copper electrolyte are strongly

influenced by composition and temperature: Increased temperature, for example, lowers electrolyte density and viscosity [6] while enhancing the rate of chemical reactions [4]. On the other hand, a too-high temperature results in unnecessary energy costs and excessive electrolyte bath evaporation [4]. In contrast, an electrolyte composition with a high concentration of Cu(II), Ni(II) and sulfuric acid makes the electrolyte denser and more viscous [6,12]. An increase in viscosity decreases the diffusion coefficient of Cu(II) but a high concentration of Cu(II) also increases the limiting current density [7], giving the possibility for a higher deposition rate. Moreover, an increase in the concentration of sulfuric acid leads to enhanced conductivity [5–7]. As a result, it is important to thoroughly determine the effects of these parameters in order to optimize the yield of cathode copper.

Conductivity is an important solution property [13] as it affects the electrical energy consumption of the electrorefining process [5,6]. Therefore, when optimizing the refining process by altering the temperature or composition, conductivity is a good value to be controlled either by measuring it or defining it with an applicable model.

The aim of this study is to construct accurate mathematical models for the conductivity, taking into account the effect of temperature as well as solution sulfuric acid and metal concentrations. Furthermore, a particular focus is also paid to the effect of typical impurities such as nickel and arsenic, originating from increasingly impure raw materials in addition to copper. The design of experiments is carried out with full factorial design by MODDE software (MKS Data Analytics Solutions, Malmö, Sweden) in order to build up a model that reflects copper electrorefining conductivity as a function of all the previously mentioned parameters.

2. Materials and Methods

Electrolytes were prepared from copper sulfate ($\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$, min. 98%, VWR Chemicals, Radnor, PA, USA), nickel sulfate ($\text{NiSO}_4 \cdot 6\text{H}_2\text{O}$, min. 98%, VWR Chemicals), sulfuric acid (H_2SO_4 , 95%–98%, Sigma-Aldrich, St. Louis, MO, USA), arsenic acid solution (from Boliden Harjavalta Copper electrorefinery, Harjavalta, Finland, containing $[\text{As}] = 151,700 \text{ mg/L}$, $[\text{Cu}] = 4794 \text{ mg/L}$, $[\text{Sb}] = 3954 \text{ mg/L}$, $[\text{Ni}] = 1688 \text{ mg/L}$, $[\text{Bi}] = 6.2 \text{ mg/L}$, $[\text{Te}] = 18.6 \text{ mg/L}$, $[\text{Pb}] = 29 \text{ mg/L}$, $[\text{Ag}] = 0.16 \text{ mg/L}$) and distilled water. Cu and Ni contents in arsenic acid were also taken into account when preparing the electrolytes. Table 1 summarizes the experimental factors and solution parameters studied, 33 different solution parameter combinations were investigated at five different temperatures and in total 165 different combinations were studied. No extra additives such as glue, thiourea or chloride ions were used.

Table 1. Parameters investigated affecting copper electrorefining electrolyte—factors ($[\text{Cu(II)}]$, $[\text{H}_2\text{SO}_4]$, $[\text{Ni(II)}]$, $[\text{As(III)}]$ and temperature, T) and their levels. Arsenic was adjusted by arsenic acid (Cu(II) and Ni(II) in acid taken into account).

Factor	Levels	
Cu(II)	40; 50; 60	g/L
H ₂ SO ₄	160; 180; 200; 220	g/L
Ni(II)	0; 10; 20	g/L
As(III)	0; 15; 30	g/L
T	50; 55; 60; 65; 70	°C

Conductivity measurements were carried out using a Knick Portamess® 913 Cond conductivity meter produced by Knick Elektronische Messgeräte GmbH & Co. KG (Berlin, Germany). The meter was used with a four-electrode sensor (ZU 6985) which has glass/platinum measuring system and glass casing tube. All electrolytes were heated prior to measurement in a jacketed cell using a MGW Lauda MT/M3 circulating water bath (Figure 1) (LAUDA, Lauda-Königshofen, Germany). During the heating or between the measurements, the cell was completely covered and all the holes in the

lid were plugged to prevent evaporation and consequently water loss. The electrolyte was stirred at 400 rpm using a magnetic stirrer.

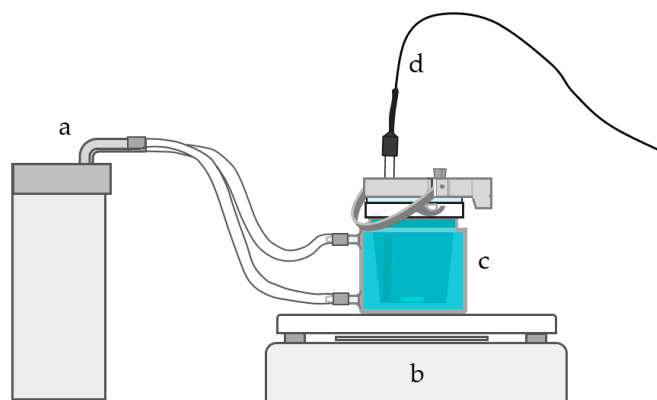


Figure 1. Schematic of the experimental set-up used for conductivity measurements: (a) water bath; (b) magnetic stirrer; (c) jacketed cell; and (d) conductivity sensor.

Data analysis and experiment design were carried out using the Modeling and design tool MODDE 8 software (MKS Data Analytics Solutions, Malmö, Sweden) for design of experiments (DOE) and multivariate data analysis. The experiments were designed by defining factors, responses and levels of the factors using the full factorial design.

Prior to modeling, the raw data was explored and evaluated with scatter plots and histograms. The models were constructed according to the data and evaluated using regression analysis tools summary of fit, analysis of variance (ANOVA) and normal probability plot of residuals. In addition, the designs were checked to ensure a low enough condition number, i.e., the ratio of the minimum and maximum singular values of the factors. For a good design this value is less than 3, whereas in a bad design it is over 6 [14]. The effect of the changes in the models after refining was also determined by comparison of the change in value of the condition number.

In summary, the parameters that describe the model are goodness of fit (R^2), goodness of prediction (Q^2), model validity and reproducibility. Model validity is based on the lack of fit which is a statistical F-test where the model error is compared to replicate error [14]. In a valid model there is no lack of fit, and consequently the model validity is high. The reproducibility describes the variabilities in the replicates [14]. The models were refined to maximize these correlation coefficients as well as minimize the difference between the R^2 and Q^2 values [14]. In a good model the Q^2 , the model validity and the reproducibility are larger than 0.5, 0.25 and 0.5, respectively [14]. In addition, the difference between the R^2 and Q^2 in a good model is less than 0.2–0.3 [14].

3. Results and Discussion

The histogram of the measured conductivity data is shown in Figure 2 and it can be seen that the histogram of the conductivity data is slightly skewed. The model validity and efficiency of data analysis are better when the data in the histogram plot is less skewed. Scatter plots of the raw data (Figure 3) showed both linearity and non-linearity which suggests that the relationship between some factors and the response might be curved, as well as the possibility that there may be interactions between the factors. Nevertheless, these scatter plots only give an approximate estimation of how the factors can influence the conductivity.

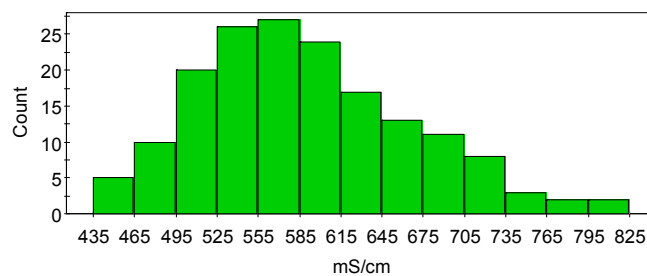


Figure 2. Histogram of conductivity values of synthetic copper electrorefining electrolytes (for Model 1).

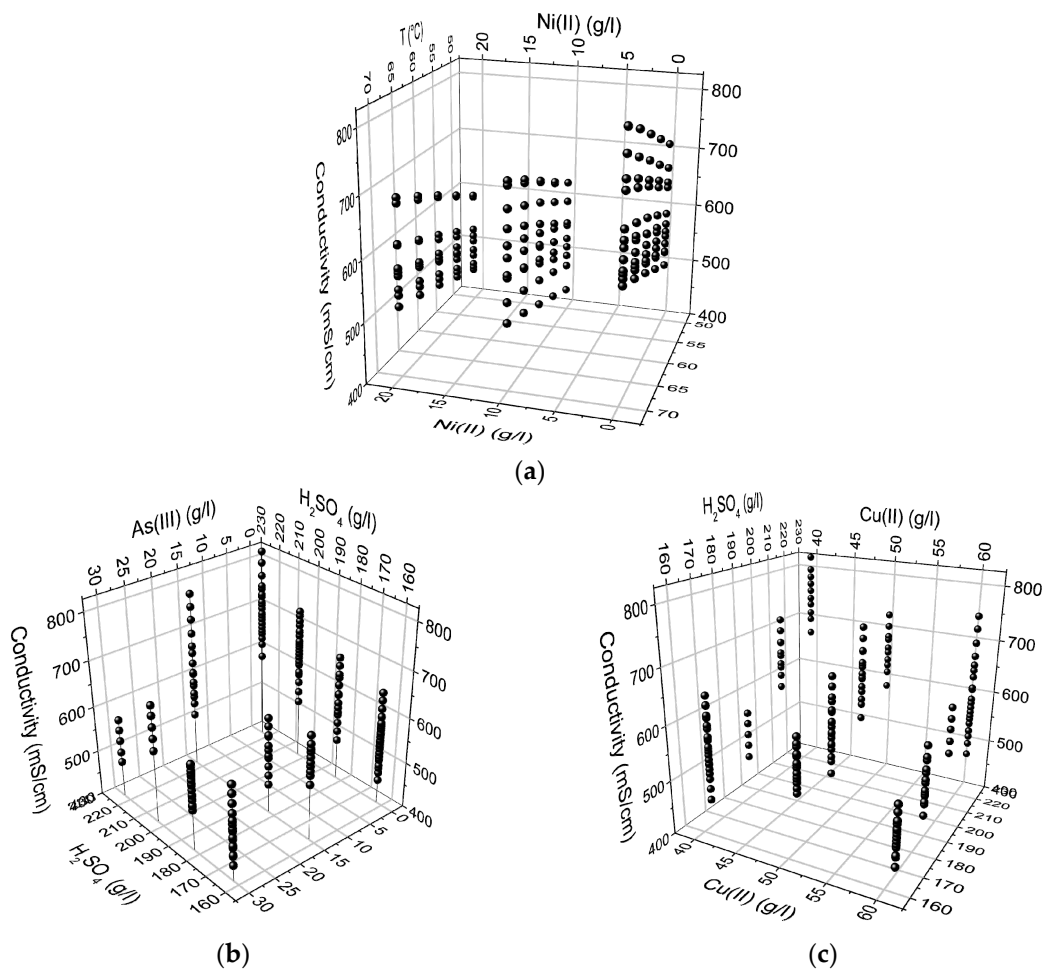


Figure 3. Scatter plots of the raw data for synthetic copper electrolyte with factors (a) T and Ni(II) concentration; (b) H_2SO_4 and As(III) concentration; and (c) H_2SO_4 and Cu(II) concentration.

3.1. Conductivity Model 1—Untreated Data with Terms of $[\text{H}_2\text{SO}_4]^2$ and T^2

In order to build up the first model that describes copper electrolyte conductivity, unscaled conductivity data was used. The model was constructed from the raw data despite the slightly skewed nature of the data (Figure 2).

Coefficients for unrefined synthetic copper electrolyte conductivity (Model 1) are shown in Figure 4. It can be seen that in addition to the factors studied, the combined effect of two factors (product) is also investigated. Terms with a high p -value (probability value), in which the error bars extend over the zero line, need to be excluded from further analysis, e.g., the terms $\text{Cu(II)} \cdot \text{H}_2\text{SO}_4$ and

Cu(II)·T for Model 1. The summary of fit for Model 1 showed that the R^2 , Q^2 and reproducibility were at a good level, but the model validity was found to be poor.

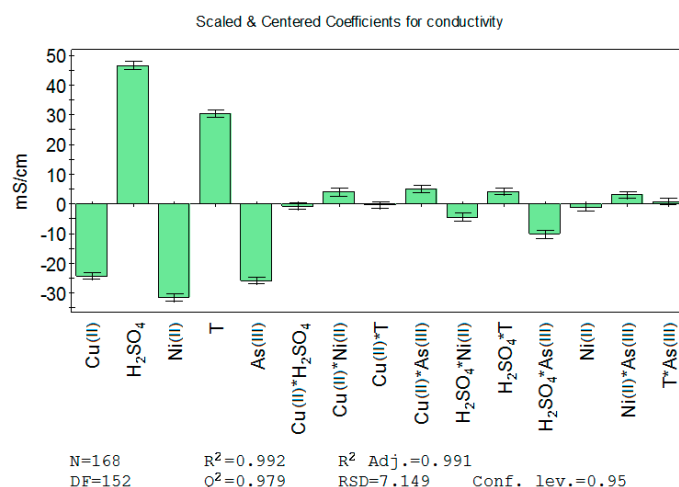


Figure 4. Coefficients for unrefined synthetic copper electrolyte conductivity in Model 1. Adj. = adjusted, Conf. lev. = confidence level, DF = degrees of freedom, RSD = residual standard deviation.

Model validity was improved by adding the squares of the terms to the model. Using squares $[\text{H}_2\text{SO}_4]^2$ and T^2 , the irregularities of the normal probability plot could be reduced, although this was seen not to improve the model validity. Two result series (with a maximum amount of H_2SO_4 , Cu(II) and Ni(II) as well as a maximum and medium amount of As(III)) were removed from the model, as it was suspected that these electrolytes were supersaturated and thus responsible for the skewness in the results.

These modifications resulted in a reasonable model validity as well as slightly higher R^2 and Q^2 ; however, the condition number increased from 2.427 (with the unrefined data) to 4.517—slightly high but below 6—as a result of adding the terms $[\text{H}_2\text{SO}_4]^2$ and T^2 . The model had no lack of fit in this phase and the summary of fit indicated that the model is valid (Table 2).

Table 2. R^2 , Q^2 , model validity and reproducibility values of the models.

Model	1	2	3	4
R^2	0.9978	0.9985	0.9972	0.9984
Q^2	0.9876	0.9959	0.9661	0.9739
Model validity	0.3016	0.4598	0.2609	0.4194
Reproducibility	0.9997	0.9996	0.9996	0.9996

Equation (1) for conductivity Model 1 was compiled according to unscaled coefficients.

$$\begin{aligned} \kappa = & 97.72 - 3.581 [\text{Cu(II)}] + 0.4736 [\text{Ni(II)}] + 0.596 [\text{As(III)}] + 2.945 [\text{H}_2\text{SO}_4] + \\ & 0.02396 [\text{Cu(II)}][\text{Ni(II)}] + 0.006713 [\text{Cu(II)}][\text{As(III)}] + 0.01219 [\text{Ni(II)}][\text{As(III)}] - \\ & 0.02297 [\text{H}_2\text{SO}_4][\text{Ni(II)}] - 0.02166 [\text{H}_2\text{SO}_4][\text{As(III)}] - 0.01899 [\text{Ni(II)}]T + 0.01768 T[\text{As(III)}] + \\ & 0.02754 [\text{H}_2\text{SO}_4]T + 2.743 T - 0.005364 [\text{H}_2\text{SO}_4]^2 - 0.02946 T^2 \end{aligned} \quad (1)$$

where the concentrations are in g/dm^3 , T is in $^\circ\text{C}$ and κ is in mS/cm .

The equation has many terms, and all the effects of the factors are not fully seen in the equation coefficients. Nonetheless, factors with low p -values indicate that at least H_2SO_4 seems to have a

combined effect with Ni(II), temperature and As(III). Data used for Model 1 indicated that Cu(II), Ni(II) and As(III) lower the conductivity of the electrolyte while temperature and H₂SO₄ increase it, which is in line with the literature [5,6].

3.2. Conductivity Model 2—Logarithmic Data with Terms of [H₂SO₄]² and T²

In order to avoid the skewness in Model 1 with untreated data, the second model was constructed using logarithmic values of conductivity and this resulted in a more normally distributed histogram. Terms with a high *p*-value were removed along with the two result series of the presumably supersaturated electrolytes determined from Model 1. As before, the term squares T² and [H₂SO₄]² were added to reduce the irregularities of the normal probability plot.

Equation (2) for the logarithm of the conductivity was compiled using unscaled coefficients. The strongest combined effects based on low *p*-values were shown to be with H₂SO₄·T, H₂SO₄·As(III) and T·As(III); however, as with Model 1, the combined effects were minor compared to the single effects of factors.

$$\begin{aligned} \log_{10}(\kappa) = & 2.17388 - 0.0023479 [\text{Cu(II)}] - 0.0027733 [\text{Ni(II)}] - 0.00073729 [\text{As(III)}] + \\ & 0.0037764 [\text{H}_2\text{SO}_4] - 1.0649 \times 10^{-5} [\text{H}_2\text{SO}_4][\text{As(III)}] + 2.1627 \times 10^{-5} T[\text{As(III)}] + \\ & 8.8019 \times 10^{-6} [\text{H}_2\text{SO}_4]T + 0.0051846 T - 6.9222 \times 10^{-6} [\text{H}_2\text{SO}_4]^2 - 3.2506 \times 10^{-5} T^2, \end{aligned} \quad (2)$$

Model 2 was regarded as reasonable and better with respect to Model 1, due to the improved model validity and Q² value, and Q² was almost equal to R² (Table 2). However, the condition number 4.456 was over 3, as was the condition number of Model 1, but not over 6, which would indicate a poor model. The condition number of this model was, however, lower than in Model 1.

3.3. Conductivity Model 3—Untreated Data without Arsenic

The third conductivity model was constructed without the experiments containing arsenic and it was found out that the data was quite normally distributed (Figure 5). Scatter plots without arsenic did not vary remarkably from the corresponding plots with arsenic. Analogously, according to these plots, Cu(II) and Ni(II) were shown to lower the conductivity while temperature and H₂SO₄ were shown to increase it. This model, however, seems to have slightly better linearity in the relationships between the factors and the response than that observed in Models 1 and 2 which include the effect of As(III). Thus, As(III) seems to cause non-linearity in the model and also affects the conductivity in more complex ways than would be expected from the literature [5,6,10].

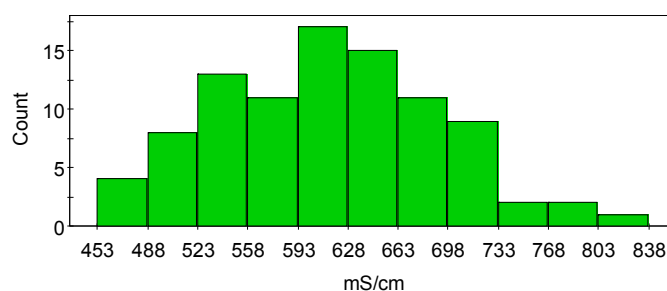


Figure 5. Histogram of conductivity values of synthetic copper electrorefining electrolytes without the effect of arsenic (for Model 3).

Model 3 was refined like Model 1 and compiled according to unscaled coefficients. The combined effect of H₂SO₄·Ni(II) and H₂SO₄·T was shown to affect the conductivity value; however, the single parameters (Cu(II), H₂SO₄, Ni(II) and T) had the biggest impact on conductivity. The sign (±) of an individual variable or combined effect of variables in the equation should not be interpreted

individually, but as a combined effect of all variables that have an effect in the equation. Figure 6 shows the effect of Ni(II) and T on the conductivity according to Equation (3), which indicates increased conductivity with increased temperature and decreased nickel concentration. Model validity was good according to the summary of fit (Table 2).

$$\begin{aligned} \kappa = & 307.9 - 1.583 [\text{Cu(II)}] + 2.737 [\text{Ni(II)}] + 1.285 [\text{H}_2\text{SO}_4] - 0.02776 [\text{H}_2\text{SO}_4][\text{Ni(II)}] - \\ & 0.008774 [\text{Cu(II)}][\text{H}_2\text{SO}_4] - 0.02087 [\text{Ni(II)}]T + 0.02919 [\text{H}_2\text{SO}_4]T - 1.17 T \end{aligned} \quad (3)$$

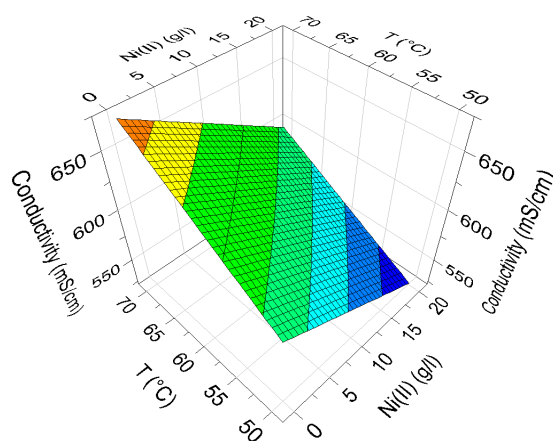


Figure 6. The effect of temperature and Ni(II) concentration on copper electrorefining electrolyte using Model 3, with $[\text{Cu(II)}] = 50.51 \text{ g/L}$ and $[\text{H}_2\text{SO}_4] = 182.842 \text{ g/L}$.

3.4. Conductivity Model 4—Without Arsenic and with Terms of $[\text{H}_2\text{SO}_4]^2$ and T^2

The fourth conductivity model was constructed without arsenic data and by adding extra terms of $[\text{H}_2\text{SO}_4]^2$ and T^2 , identical to Models 1 and 2.

$$\begin{aligned} \kappa = & 31.863 - 1.3594 [\text{Cu(II)}] + 1.835 [\text{Ni(II)}] + 2.9789 [\text{H}_2\text{SO}_4] - 0.022681 [\text{H}_2\text{SO}_4][\text{Ni(II)}] - \\ & 0.010403 [\text{Cu(II)}][\text{H}_2\text{SO}_4] - 0.021408 [\text{Ni(II)}]T + 0.02975 [\text{H}_2\text{SO}_4]T + 2.7297 T - \\ & 0.0044364 [\text{H}_2\text{SO}_4]^2 - 0.032787 T^2 \end{aligned} \quad (4)$$

Both Models 3 and 4 were shown to be valid according to the summary of fit (Table 2), with model validity being better than that of Model 3. Conversely, the condition number, 1.375, was better in Model 3 when compared to the value of 4.322 in Model 4. In contrast, the condition number of the unrefined design was 1.838.

3.5. Summary of the Models

The defined Equations (1)–(4) are relatively complex due to the interactions of the factors, and thus the effects of the factors are impossible to directly see in the equations. The effects of Cu(II) and H_2SO_4 on electrolyte conductivity containing the median amount of As(III) and Ni(II) at medium temperature, defined with Model 1, are presented in Figure 7a. Analogously, the effects of As and temperature containing a high amount of Cu(II), a low amount of H_2SO_4 and a medium amount of Ni(II) are displayed in Figure 7b.

Figure 8 presents the measured and predicted electrolyte conductivity values. It can be seen that the models predict the data with high correlation, with R^2 varying from 0.9972 to 0.9985. In addition, the R^2 , Q^2 , model validity and reproducibility values of the models are presented in Table 2.

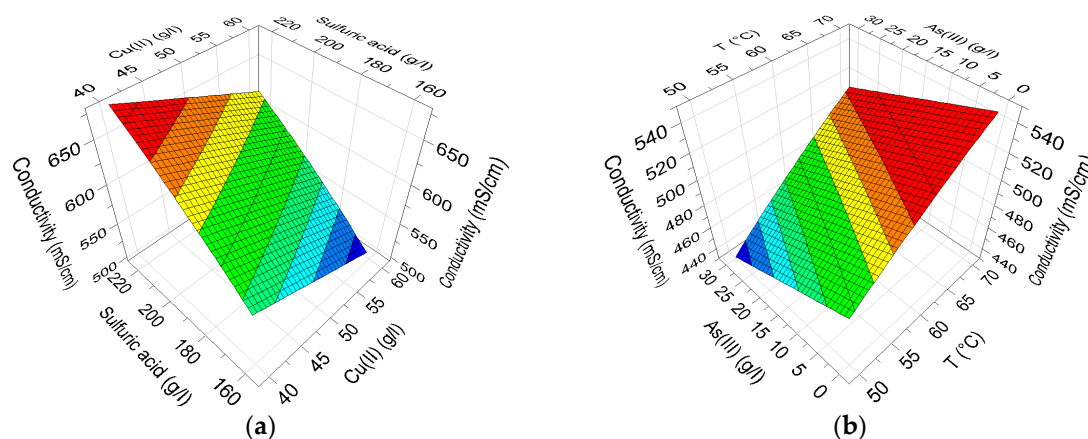


Figure 7. The effect of Cu(II) and H₂SO₄ concentrations (a) as well as As(III) concentration and temperature (b) on copper electrorefining electrolyte (Model 1), with T = 60 °C, [Ni(II)] = 10.102 g/L and [As(III)] = 15 g/L (a) and [Cu(II)] = 60.6125 g/L, [H₂SO₄] = 162.519 g/L and [Ni(II)] = 10.102 g/L (b).

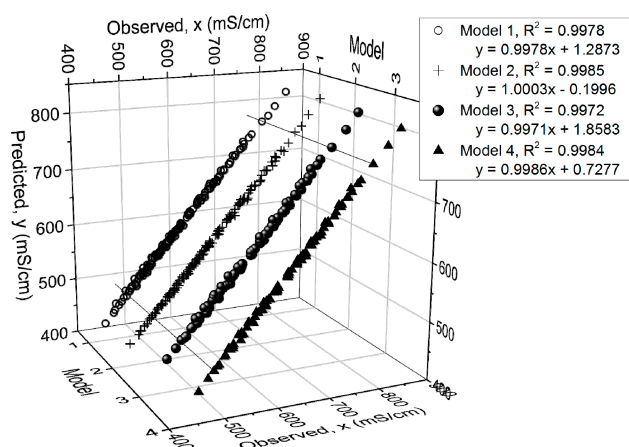


Figure 8. Observed (x) versus predicted (y) copper electrolyte conductivity values using Models 1–4.

The effects of temperature, Cu(II), As(III) and Ni(II) on conductivity are presented in Figures 9–11. In addition to conductivity data calculated by Models 1–4, these figures present the corresponding literature values and in Figure 10 five measured values are also shown. The equation defined by Subbaiah and Das [8] was, however, not used in these comparisons, since it did not reproduce the values they presented in their paper even when their own parameters were used. This is probably due to the fact that their equation did not contain a Cu term, which possibly caused the discrepancy as that error was at minimum at low Cu(II) concentrations.

Conductivity results obtained in this work were shown to be in good agreement with the previous research work of Price and Davenport [6]. Nevertheless, arsenic was shown to affect the conductivity slightly more and temperature less than determined by previous works [6,10]. Comparison of the results from this work to the equivalent results of Price and Davenport [6], Kern and Chang [10] and Devochkin et al. [12] shows that there were some differences between them. The conductivity values were seen to be lower in [12] than in the other studies. Conversely, the effect of temperature seemed to be similar according to [12] and this work. These comparisons are presented in Figure 9, where the equation by Devochkin et al. has been corrected due to an error in the sign of the Cu(II) concentration, which was noticed when testing the equation with their parameters and comparing the results to their measured values.

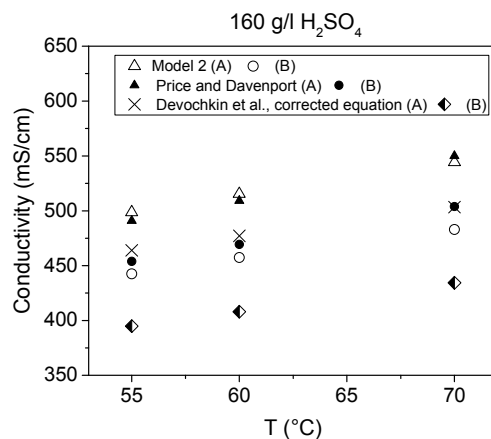


Figure 9. Effects of Cu(II), Ni(II) and temperature according to Model 2 from this work compared to results of Price and Davenport [6] and Devochkin et al. [12]. (A) 50 g/L Cu(II), 18 g/L Ni(II) and (B) 65 g/L Cu(II), 24 g/L Ni(II).

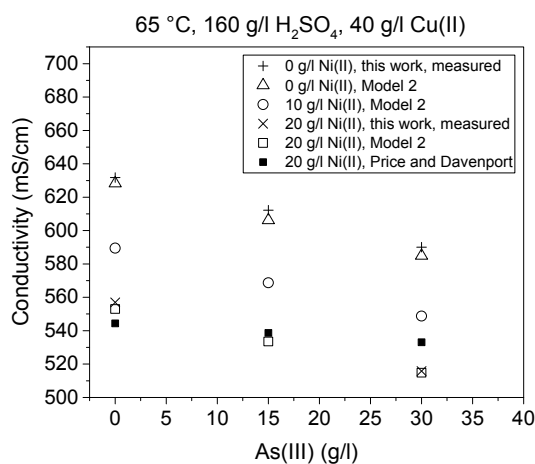


Figure 10. Effects of Ni(II) and As(III) according to measured values and Model 2 from this work compared to results of Price and Davenport [6].

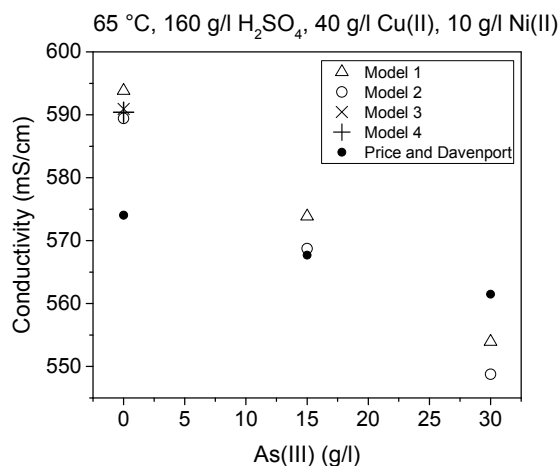


Figure 11. Effects of As(III) on copper electrorefining electrolyte conductivity defined using Models 1–4 from this work and compared to values of Price and Davenport [6].

Table 3 presents a comparison of values calculated with Models 1–4 and the model of Price and Davenport [6], Devochkin et al. [12] and measurements of Kern and Chang [10]. The model of Devochkin et al. was designed to determine conductivity from electrolytes without As(III) and with a constant Cu(II)/Ni(II) ratio; therefore, for that reason, their model was not used with all parameter combinations. The conductivity value determined using their model was lower than the other equivalent values, as can be observed in Figure 7. The values predicted by Models 1–4 were in good agreement with the values measured (Figure 8).

Table 3. Comparison of values defined with Models 1–4 to equivalent values from Price and Davenport [6], Devochkin et al. [12] and to measured values from Kern and Chang [10].

T (°C)	Concentration (g/L)				κ (mS/cm)						
					Model				Price and Davenport	Kern and Chang	Devochkin et al.
	H ₂ SO ₄	Cu(II)	Ni(II)	As(III)	1	2	3	4			
55	135	35	0	0	538.4	534.0	536.9	528.3	527.3	530.7	-
55	135	35	30	0	453.4	440.9	472.1	456.1	458.4	444.0	-
55	135	35	0	30	504.8	498.9	-	-	516.7	523.1	-
55	135	35	0	40	493.6	487.7	-	-	513.2	519.4	-
55	150	50	18	0	478.0	475.0	485.8	479.9	477.8	-	446.13

Furthermore, it can be seen that the values defined using the models detailed in this work also show a good correlation with both Kern and Chang's results [10] and Price and Davenport (who reported a good agreement the results of Kern and Chang) [6]. According to this research, arsenic decreases conductivity and an improved model can be constructed.

4. Conclusions

In this work the conductivity of the copper electrorefining electrolyte was investigated as a function of temperature (50–70 °C) and concentrations of copper (Cu(II), 40–60 g/L), nickel (Ni(II), 0–20 g/L), arsenic (As(III), 0–30 g/L) and sulfuric acid (160–220 g/L). In total, 165 different combinations of these factors were studied.

The measured data showed that conductivity was increased by a decrease in Cu(II), Ni(II) and As(III) concentration and increased with increasing temperature and acidity. As(III) appeared to affect the conductivity in more complicated ways than would be expected based on findings from the literature. In addition, it was observed that the untreated measured data was shown to be slightly skewed.

The results were treated using factorial analysis, and as a result four different electrolyte conductivity models were created. Conductivity was measured reliably, and thus the models from the conductivity results were constructed directly. Combined effects were also detected, but the effects were minor compared to the effects of single factors.

Model 1 was constructed from untreated conductivity data with terms of $[\text{H}_2\text{SO}_4]^2$ and T^2 . Model 2 was constructed from logarithmic values of conductivity, also with additional terms of $[\text{H}_2\text{SO}_4]^2$ and T^2 . Models 3 and 4 were constructed from untreated data by neglecting the measurement series with arsenic, and Model 4 with additional terms of $[\text{H}_2\text{SO}_4]^2$ and T^2 . The four models constructed were all valid and had high correlation coefficients. In addition, the reproducibility was good, and the models did not suffer from a lack of fit. The most accurate models based on the best R^2 , Q^2 and model validity were Model 2 and Model 4 (Figure 8 and Table 2).

Overall, this work provides improved models for copper electrolyte conductivity both in the presence and absence of arsenic. In particular, As(III) is shown to cause slight non-linearity and decrease conductivity more than previously reported, whereas temperature is shown to affect the electrolyte conductivity slightly less.

Acknowledgments: This research has been performed within the SIMP (System Integrated Metal Production) project of FIMECC (Finnish Metals and Engineering Competence Cluster Ltd. (Tampere, Finland)).

Author Contributions: Taina Kalliomäki performed the experiments and analyzed the data as part of her Master's thesis; Jari Aromaa counseled in experimental and theoretical matters as an instructor of the thesis; Mari Lundström and Taina Kalliomäki wrote the paper. All authors have read and approved the manuscript.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Davenport, W.G.; King, M.; Schlesinger, M.; Biswas, A.K. Overview. In *Extractive Metallurgy of Copper*, 4th ed.; Elsevier Science Ltd.: Amsterdam, The Netherlands, 2002.
2. Wraith, A.E.; Mackey, P.J.; Jones, R.P. Origins of electrorefining: Birth of the technology and the world's first commercial electrolytic. In *Proceedings of Copper 2013; The Chilean Institute of Mining Engineers*: Santiago, Chile, 2013.
3. Moats, M.S.; Hiskey, J.B. How anodes passivate in copper electrorefining. In *The Copper 2010-Proceedings*; GDMB: Hamburg, Germany, 2010; Volume 4.
4. Davenport, W.G.; King, M.; Schlesinger, M.; Biswas, A.K.; Robinson, T. Electrolytic Refining. In *Extractive Metallurgy of Copper*, 4th ed.; Elsevier Science Ltd.: Amsterdam, The Netherlands, 2002; pp. 265–288.
5. Price, D.C.; Davenport, W.G. Densities, electrical conductivities and viscosities of $\text{CuSO}_4/\text{H}_2\text{SO}_4$ solutions in the range of modern electrorefining and electrowinning electrolytes. *Metall. Trans. B* **1980**, *11*, 159–163. [[CrossRef](#)]
6. Price, D.C.; Davenport, W.G. Physico-chemical properties of copper electrorefining and electrowinning electrolytes. *Metall. Trans. B* **1981**, *12*, 639–643. [[CrossRef](#)]
7. Moats, M.S.; Hiskey, J.B.; Collins, D.W. The effect of copper, acid, and temperature on the diffusion coefficient of cupric ions in simulated electrorefining electrolytes. *Hydrometallurgy* **2000**, *56*, 255–268. [[CrossRef](#)]
8. Subbaiah, T.; Das, S.C. Physico-chemical properties of copper electrolytes. *Metall. Trans. B* **1989**, *20*, 375–380. [[CrossRef](#)]
9. Jarjoura, G.; Muinonen, M.; Kipouros, G.J. Physicochemical properties of nickel copper sulfate solutions. *Can. Metall. Q.* **2003**, *42*, 281–288. [[CrossRef](#)]
10. Kern, E.F.; Chang, M.Y. Conductivity of copper refining electrolytes. In *Proceedings of the 41st General Meeting of the American Electrochemical Society*, Baltimore, MD, USA, 28 April 1922.
11. Skowronski, S.; Reinoso, E.A. The specific resistivity of copper refining electrolytes and method of calculation. In *Proceedings of the 51st General Meeting of the American Electrochemical Society*, Philadelphia, PA, USA, 30 April 1927.
12. Devochkin, A.I.; Kuzmina, I.S.; Salimzhanova, E.V.; Petukhova, L.I. The study of sulfate copper electrolyte physicochemical properties depending on its components and temperature. *Tsvetnye Met.* **2015**, *2015*, 67–71. [[CrossRef](#)]
13. Zhang, X.; Hu, Y.; Peng, X.; Yue, W. Conductivities of several ternary electrolyte solutions and their binary subsystems at 293.15, 298.15, and 303.15 K. *J. Solut. Chem.* **2009**, *38*, 1295–1306. [[CrossRef](#)]
14. Eriksson, L.; Johansson, E.; Kettaneh-Wold, N.; Wikström, C.; Wold, S. *Design of Experiments: Principles and Applications*; MKS Umetrics AB: Malmö, Sweden, 2008.



© 2016 by the authors; licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC-BY) license (<http://creativecommons.org/licenses/by/4.0/>).