

Article

A Microwave-Assisted Boudouard Reaction: A Highly Effective Reduction of the Greenhouse Gas CO₂ to Useful CO Feedstock with Semi-Coke

Huan Dai ^{1,2}, Hong Zhao ^{1,*} , Siyuan Chen ³ and Biao Jiang ^{3,*}

¹ Green Chemical Engineering Research Center, Shanghai Advanced Research Institute, Chinese Academy of Sciences, Shanghai 201210, China; daihuan2018@sari.ac.cn

² University of Chinese Academy of Sciences, Beijing 100049, China

³ Shanghai Green Chemical Engineering Research Center, Shanghai Institute of Organic Chemistry, Chinese Academy of Sciences, Shanghai 200032, China; chensy@sioc.ac.cn

* Correspondence: zhaoh@sari.ac.cn (H.Z.); jiangb@sioc.ac.cn (B.J.)

Abstract: The conversion of CO₂ into more synthetically flexible CO is an effective and potential method for CO₂ remediation, utilization and carbon emission reduction. In this paper, the reaction of carbon-carbon dioxide (the Boudouard reaction) was performed in a microwave fixed bed reactor using semi-coke (SC) as both the microwave absorber and reactant and was systematically compared with that heated in a conventional thermal field. The effects of the heating source, SC particle size, CO₂ flow rate and additives on CO₂ conversion and CO output were investigated. By microwave heating (MWH), CO₂ conversion reached more than 99% while by conventional heating (CH), the maximum conversion of CO₂ was approximately 29% at 900 °C. Meanwhile, for the reaction with 5 wt% barium carbonate added as a promoter, the reaction temperature was significantly reduced to 750 °C with an almost quantitative conversion of CO₂. Further kinetic calculations showed that the apparent activation energy of the reaction under microwave heating was 46.3 kJ/mol, which was only one-third of that observed under conventional heating. The microwave-assisted Boudouard reaction with catalytic barium carbonate is a promising method for carbon dioxide utilization.

Keywords: microwave heating; CO₂ conversion; semi-coke; Boudouard reaction



Citation: Dai, H.; Zhao, H.; Chen, S.; Jiang, B. A Microwave-Assisted Boudouard Reaction: A Highly Effective Reduction of the Greenhouse Gas CO₂ to Useful CO Feedstock with Semi-Coke. *Molecules* **2021**, *26*, 1507. <https://doi.org/10.3390/molecules26061507>

Academic Editor: Ionel Mangalagiu

Received: 31 January 2021

Accepted: 3 March 2021

Published: 10 March 2021

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.




Copyright: © 2021 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

In the face of climate change due to global warming, converting carbon dioxide into synthetic, flexible and useful molecules rather than capturing CO₂ for storage is the most attractive approach to climate change mitigation solutions (Scheme 1) [1]. Nevertheless, the dynamics and thermodynamic stability of CO₂ severely limit conversion. Efficient reducing agents and precious metal catalysts are required to facilitate its conversion into useful chemicals [2]. A simple and well-known response is the Boudouard reaction (C + CO₂ = 2CO) in which CO₂ reacts with carbon to produce carbon monoxide [3]. CO is not only the feedstock for Fischer–Tropsch's synthetic oils and waxes but also a raw material of carbonylation reactions to synthesize a number of fine chemicals [4] and it provides important hydrogen energy through water-gas shift reactions [5].

However, the Boudouard reaction is a highly endothermic gas-solid reaction with a large positive enthalpy (172 kJ/mol at 298 K) in which very high temperatures, typically above 700 °C, are required to shift the equilibrium towards CO production [3]. Over the past decade, interest in using microwaves to activate chemical reactions has become widespread, creating significant advantages in the field of heterogeneous catalysis [6]. In particular, high-temperature microwaves have a special advantage in inducing chemical reactions derived from heterogeneous catalysts with unique opportunities to control the energy input [7]. Therefore, the ideal microwave catalyst has a dual role both as a catalyst for chemical reactions and as an efficient converter of the thermal energy required for

the event and reaction activation from microwave energy [8]. Carbonaceous materials are known as excellent microwave receptors [9] and the high temperatures required for the Boudouard reaction could be provided by microwave irradiation [10]. Microwave-enhanced CO₂ gasification of oil palm shell char [11,12], coconut shell char [13] and sewage sludge waste has been studied [14]. The results showed that microwave radiation was more effective than conventional heating and the reaction temperature was reduced by approximately 200 °C in a short time. The reactivity of biochar was found to be dependent on the pore structure of the char and its morphology, the catalytic activity of the associated ash, the availability of carbon active sites as well as catalytic active sites on the char, the thermal history of the char during pyrolysis and the type of carbon source.

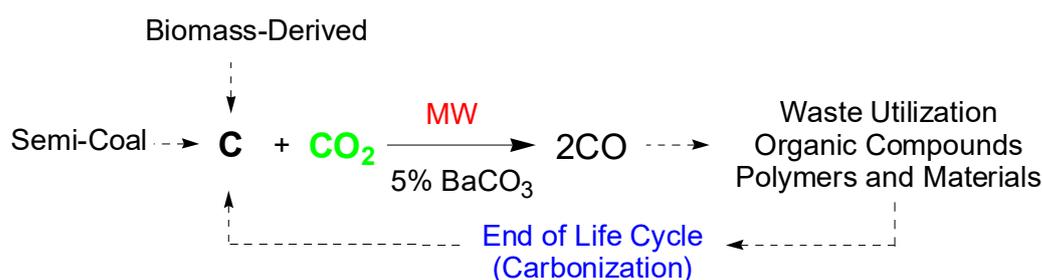

Scheme 1. The Boudouard reaction in sustainable total carbon recycling.

China is a coal-rich country and implementing carbon neutrality is the country's strategy for mitigating climate change. Semi-coke, named blue coal, is prepared from Jurassic low-quality coal with reserves of 100 billion tons in China [15]. As a new type of carbon material with its high fixed carbon content, high chemical activity and low ash content, semi-coke can replace char (metallurgical coke) and is widely used in the chemical, smelting, gasification and other industries. In this paper, we report the results of an investigation specifically focused on the conversion of CO₂ into CO with semi-coke under microwave irradiation and catalysis. To the best of our knowledge, similar data are not found in the literature and the Boudouard reaction was carried out with a CO₂ conversion rate of 99% at 900 °C with an excellent microwave absorption performance of the semi-coke. When barium carbonate was added as a promoter, the reaction temperature was significantly reduced to 750 °C with an almost quantitative conversion of CO₂.

2. Results and Discussions

2.1. Temperature Correction of the Microwave Fixed Bed Reactor

The application of microwave irradiation to a gas-solid reaction has been studied for more than 20 years. However, due to the practical difficulties of the temperature measurement and uniform temperature distribution in the microwave (MW) field, comparing reaction performances under conventional heating (CH) and microwave heating (MWH) always would be explained as the formation of hot spots in the reaction system as a consequence of MWH. In this paper, we obtained a relatively even temperature field in the microwave fixed bed by using three silicon carbide (SiC) rings with a width of 0.5 cm as thermal loads that were sheathed outside the quartz tube. Moreover, three optical radiation pyrometers were used to monitor the surface temperature of the bed. Before the Boudouard reaction experiments, we corrected the heating temperature and confirmed the constant temperature area in the microwave fixed bed reactor. We used a silicon carbide rod with a length of 13 cm and a diameter of 3.5 cm as a heat carrier for the temperature range correction (SiC is an excellent microwave absorber material [16,17]). Figure 1 shows the temperature distribution of the bed with an error of ±10 °C, identifying the uniformity of the temperature distribution. After that, we measured the temperature distribution using semi-coke (SC) as the heat carrier. The SC bed exhibited a relatively even temperature zone ranging from about ±3 cm from the center of the temperature zone, which met the needs

of our experiments. The temperature distribution of the fixed bed is shown in Figure 1 and its error was within ± 25 °C, which also met the needs of our experiments.

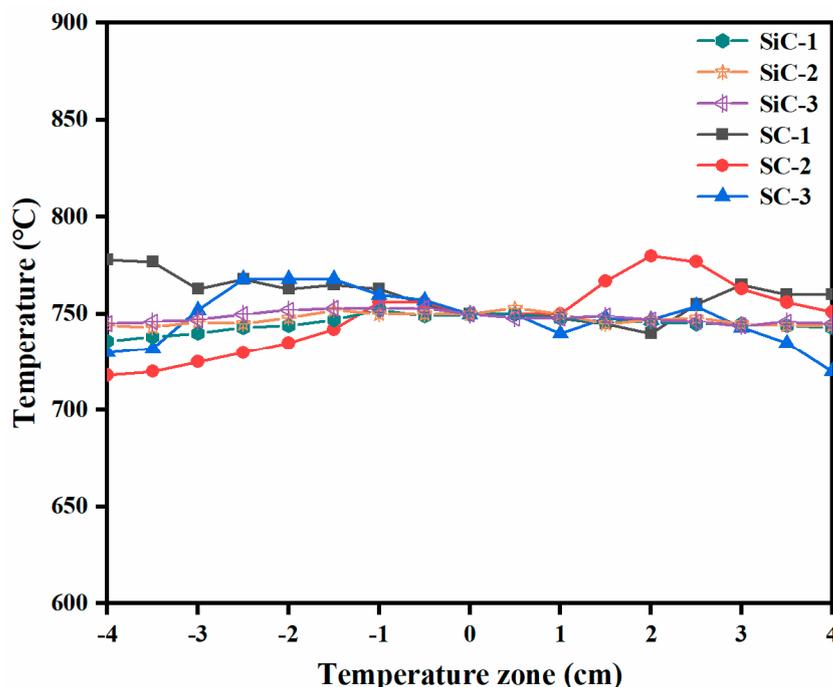


Figure 1. Temperature correction diagram of silicon carbide (SiC) and semi-coke (SC).

2.2. The Boudouard Reaction in Both Microwave and Conventional Thermal Fields

To investigate the characteristics of the CO₂ gasification of SC in both microwave and conventional thermal fields, typical experiments were conducted with an SC particle size of 0.200–0.450 mm and a CO₂ space velocity of 3.20 m³/(m³(SC)·h) at 750 °C. The effect of the temperature on the Boudouard reaction in both fields is shown in Figure 2a,b. As we can see from Figure 2a, the CO₂ conversion and SC conversion by conventional heating increased slowly with an increase in temperature but were at a low level. CO₂ conversion increased from 5.0% at 800 °C to 10.3%, 14.4% and 29.1% at 850 °C, 900 °C and 950 °C, respectively. The results were consistent with the strong endotherm of the Boudouard reaction. The high temperature pushed the balance to CO production when heated by conventional methods. Figure 2b shows the experimental results when heated by microwave irradiation. Clearly, when the reaction temperature was 750 °C, the CO₂ conversion rate was 77.2%, which was much higher than that carried out at 950 °C by conventional heating. When the reaction temperature increased to 900 °C, the CO₂ conversion increased to 99.7%. In addition, Figure 2c compares the CO output of the two heating sources. From Figure 2c, it can be clearly seen that by conventional heating, the CO output ranged from 8.1 mmol at 800 °C to 59.1 mmol at 950 °C while by microwave heating the CO output increased from 1163 mmol at 750 °C to 2000 mmol at 900 °C, which was more than 60 times than that obtained by conventional heating. The clear CO output at 950 °C was only approximately one-twentieth of that carried out in the microwave reactor at 750 °C. We know that SC is a good heating conductor and the possible temperature gradient derived from the characteristics of microwave heating would not be great enough to cause such a distinct Boudouard reaction performance between the two thermal fields. Therefore, the obviously higher CO₂ conversion and CO output obtained in the microwave reactor were not caused by incorrect temperature measurements or uneven temperature distributions in the microwave reactor. The fact that the Boudouard reaction under microwave heating proceeded more easily suggested a great enhancement of the Boudouard reaction with microwave heating.

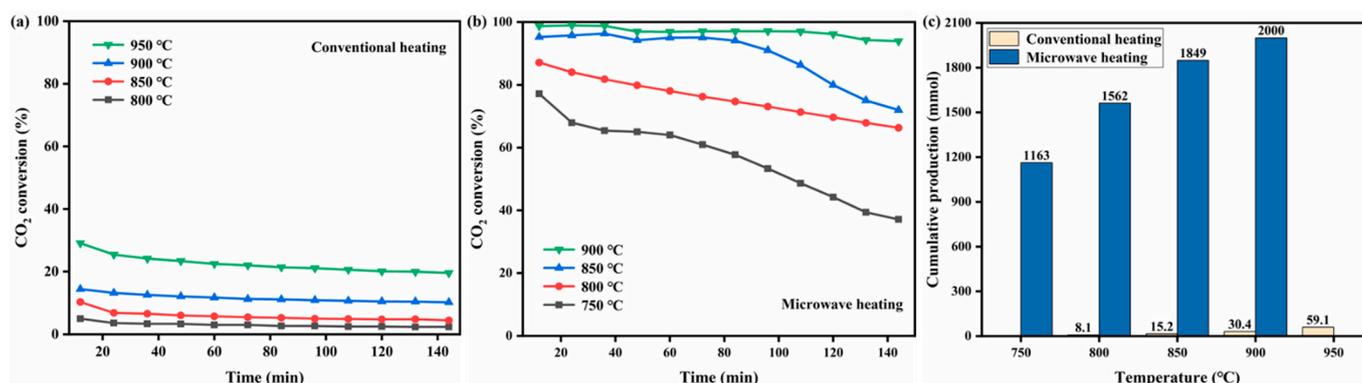


Figure 2. (a) Effect of gasification temperature under conventional heating; (b) Effect of gasification temperature under microwave heating; (c) Production of CO under microwave heating and conventional heating with the reaction times of 144 min.

This superior performance of microwaves is believed to be related to the mechanism of microwave heating [18]. SC is an excellent material for absorbing microwaves that can be firmly coupled with microwaves to carry out chemical reactions. When the microwave acted on the SC, the microwave energy could directly couple with carbon molecules so that the dielectric heating effect of the microwave could effectively heat the raw material. This is different from conventional heating in that the main mechanism of microwave absorption in dielectric materials is to excite electronic oscillations at the frequency of the microwave source.

2.3. Influence of the SC Particle Size

The effect of the SC particle size on CO₂ conversion and CO output in the microwave reactor was investigated at a temperature of 800 °C and a CO₂ flow rate of 125 mL/min. As shown in Figure 3a, the CO₂ conversion improved from 83.0% for particles in the range of 0.850–1.400 mm to 98.0% for particles in the range of 0.200–0.450 mm; at the same time, the CO₂ conversion was maintained above 90%. As the particle size of the SC decreased, the gasification reactivity improved. This is because in the gasification process, the smaller particles of SC have better heat and mass transfer processes. Within a certain particle size range, the decreased SC particle size would give a larger contact area between CO₂ and SC, causing a more complete reaction. In addition, the reduced SC particle size was helpful in reducing the effects of internal diffusion, which could also increase the gasification reaction rate. It can be seen that the CO₂ conversion of the SC particle size < 0.200 mm was generally lower than that of the SC particle size 0.200–0.450 mm as the reaction time increased and this may be because too small a particle size would give a larger external diffusion resistance and the CO₂ reactant would be more difficult to evenly diffuse into the SC bed. Figure 3b shows the effect of different particle sizes on the CO output. We can see that the CO output also shows the same trend as the CO₂ conversion. When the SC particle size was 0.200–0.450 mm, the maximum CO output was 1371 mmol.

2.4. Influence of the CO₂ Gas Flow Rate

Figure 3c shows the influence of the CO₂ gas flow rate on the CO₂ conversion of SC. The CO₂ conversion decreased from 97.3% to 67.2% when the CO₂ flow increased from 125 mL/min to 200 mL/min. This was because the increase in the CO₂ flow shortened the residence time of CO₂ gas in the carbon bed and then reduced the chance of CO₂ conversion therefore causing a significant drop in CO₂ conversion. Figure 3d shows the CO output under the different gas flows. The results indicated that the CO output increased from 1462 mmol to 1581 mmol when the CO₂ flow increased from 125 mL/min to 200 mL/min. However, with the increase in CO₂ flow, the output of CO was not obviously changed. This might be due to the increase in CO₂ flow, resulting in the reduction in the CO₂ external

diffusion resistance and the increase in CO₂ diffusion into SC particles, which intensified the CO₂ conversion reaction.

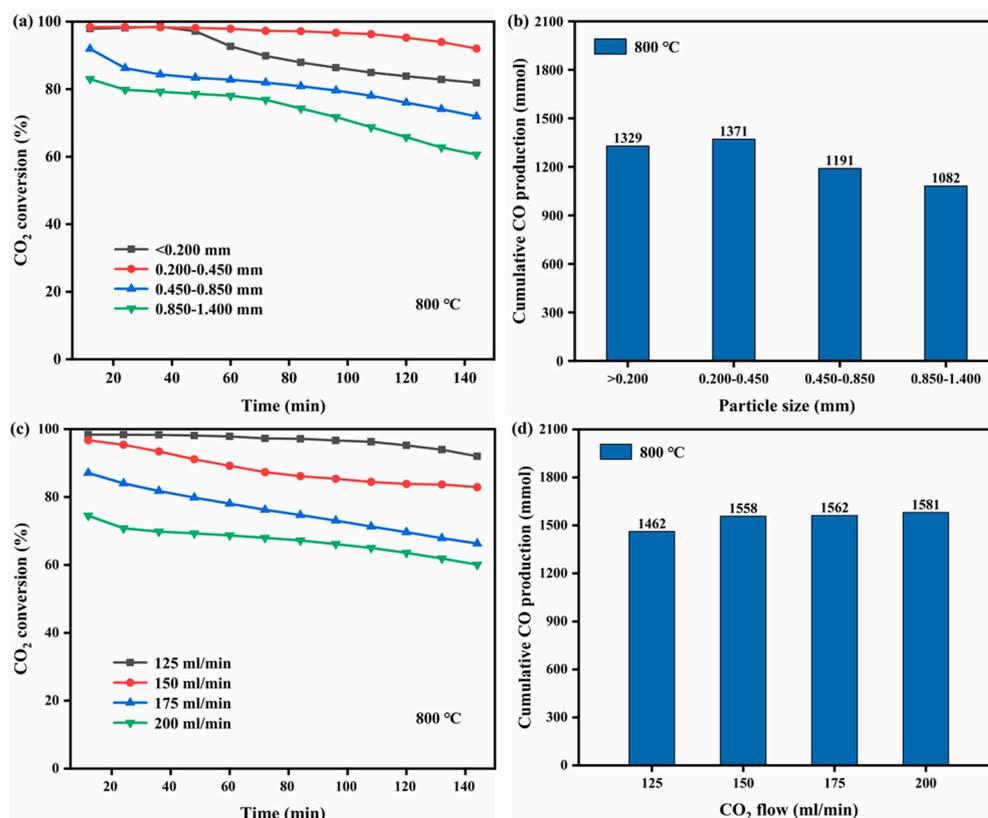


Figure 3. (a) Effect of SC particle size on CO₂ conversion; (b) CO output at different particle sizes. Reaction conditions: the CO₂ flow was 125 mL/min, the reaction temperature was 800 °C, the reaction time was 144 min; (c) Effect of gas flow rate on CO₂ conversion; (d) CO output at different gas flow rates. Reaction conditions: the SC particle size was 0.200–0.450 mm, the reaction temperature was 800 °C, the reaction time was 144 min.

2.5. Influence of the Catalyst

It has been reported that the salts of alkali metals and alkaline earth metals such as Na, K and Ca have a good catalytic performance for char gasification reactions [19–21] but the effect of barium salt on the Boudouard reaction has been scarcely investigated. Here, BaCO₃ was used as a catalyst and compared with CaO in the gasification reaction of SC and CO₂ under microwave radiation. Figure 4a exhibits the CO₂ conversion of the SC with/without 5 wt% CaO and a BaCO₃ addition at a reaction temperature of 750 °C and a CO₂ flow rate of 175 mL/min under microwave heating. Without a catalyst, the initial CO₂ conversion at 750 °C was 86.2% and then decreased quickly to approximately 40% after 144 min. Under the catalysis of BaCO₃ and CaO, the initial CO₂ conversion was 99.9% but BaCO₃ exhibited a better catalytic life. Figure 4b shows that the CO output also increased significantly from 1689 mmol to 2392 mmol and 2520 mmol when CaO and BaCO₃ were used as catalysts. The experimental results indicated that BaCO₃ and CaO had an excellent catalytic performance for the Boudouard reaction and reduced the reaction temperature. The reason for the higher reactivity of SC catalyzed by BaCO₃ would be that BaCO₃ improved the adsorption capacity of SC for CO₂, thereby obtaining a higher reactivity.

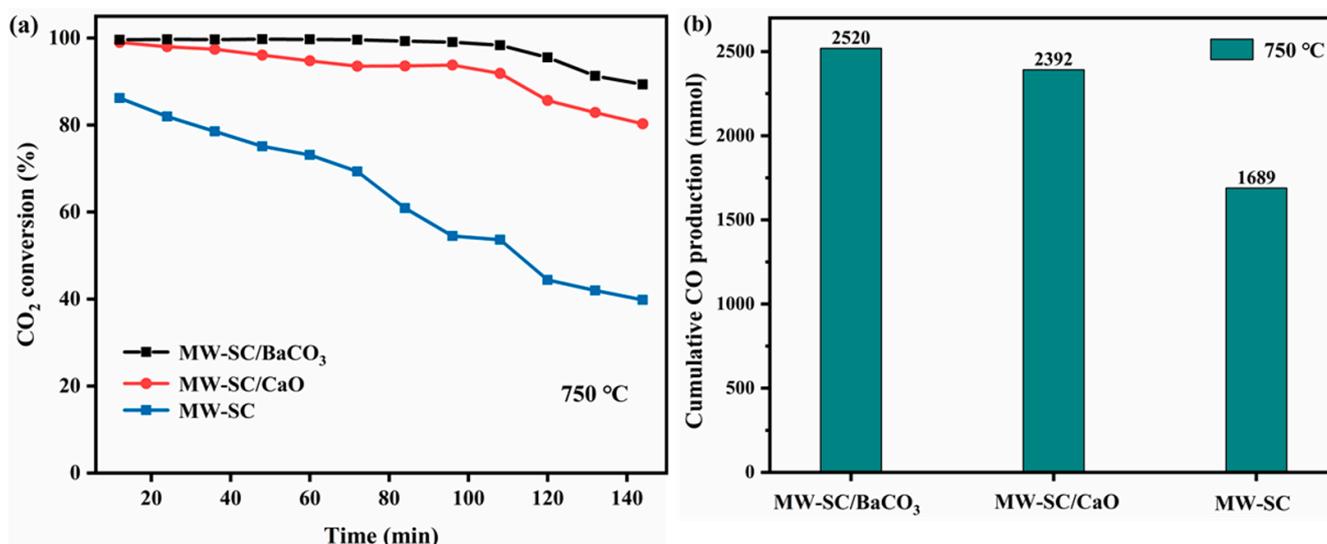


Figure 4. (a) Comparison of SC, SC/BaCO₃ and SC/CaO gasification reactivity under a microwave (MW) at 750 °C; (b) CO output at different experiment reactions with the reaction times of 144 min.

Figure 5 shows the surface morphologies of gasified SC before and after a reaction under different reaction conditions. It can be seen from Figure 5a that the un-gasified SC had a relatively smooth surface and the carbon layer structure was complete and without obvious pores inside the bulk SC particles. By conventional heating, the SC particles shown in Figure 5b exhibited an inconspicuous lamellar structure with a few large pores and the carbon layer structure was relatively complete. The possible reason is that gasified SC hardly occurs at low temperatures in conventional heating. The morphology of gasified SC under microwave radiation is shown in Figure 5c. The surface of the SC was obviously damaged and a few large pores were formed. As shown in Figure 5d, BaCO₃ particles on gasified SC obtained at 750 °C showed that the carbon layer structure was further destroyed and the surface carbon structure was more uniformly distributed. The results indicated that the reaction rate of CO₂ on the surface of SC was more intense in the presence of barium salt. Table 1 shows the specific surface areas and volume pores for SCs heated by different techniques. The specific surface area and pore volume of raw SC were 2.16 m²/g and 1.30 × 10^{−3} cm³/g, respectively. After conventional and microwave heating, the specific surface area was increased from 2.16 m²/g to 3.60 m²/g for CH-SC, 18.2 m²/g for MW-SC and 14.3 m²/g for MW-SC/BaCO₃ while the pore volume also showed the same trend. The results indicated that microwaves enhanced the reactivity of SC, resulting in a higher CO₂ conversion and CO output.

2.6. Analysis of Gasification Kinetics

In order to compare the reaction performances in both thermal fields, the gasification kinetics in the two thermal fields were studied based on the experimental data exhibited in Section 2.2. Both diffusional and mass transfer influences were ruled out. We know that the volume reaction model is a commonly used kinetic model in the Boudouard reaction. The volume reaction model (VRM) assumes that the gasification reaction occurs at the active site and is evenly distributed throughout the carbon particles [22–25]. By the kinetic analysis of the isothermal gasification experiment and then the conversion of the first-order kinetics into the Arrhenius relationship, the kinetics of several coal conversion processes could be represented. Therefore, we performed kinetic calculations on the experimental results under conventional and microwave (non-catalysis) thermal fields. The reaction rate equation was expressed as follows:

$$r = \frac{dX}{dt} = k_{VRM}(1 - X). \quad (1)$$

$$\ln(1 - X) = -k_{VRM}t. \quad (2)$$

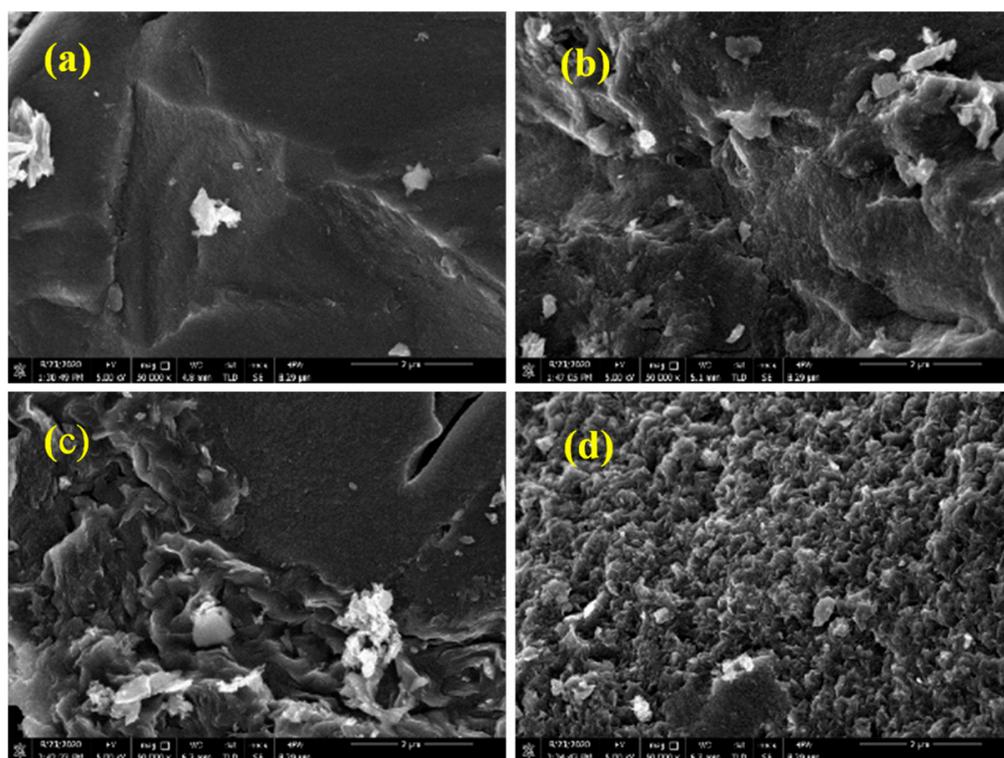


Figure 5. SEM micrographs of (a) raw SC; (b) SC after CO₂ gasification in conventional heating (CH); (c) SC after CO₂ gasification in a microwave (MW); (d) SC/BaCO₃ after CO₂ gasification in a MW. Reaction conditions: the SC particle size was 0.200–0.450 mm and the reaction temperature was 750 °C.

Table 1. The calculations of specific surface area (BET), and total pore volume.

Sample	Raw SC	CH-SC	MW-SC	MW-SC/BaCO ₃
S _{bet} (m ² /g)	2.2	3.6	18.2	14.3
V _{total} (cm ³ /g)	1.3 × 10 ⁻³	1.7 × 10 ⁻³	2.8 × 10 ⁻³	2.5 × 10 ⁻³

From the graph of $\ln(1 - x) - t$, the value of the first-order reaction rate constant k_{VAM} at each temperature could be obtained. The temperature dependence of k_{VAM} was expressed by the Arrhenius equation as follows:

$$k_{VRM} = A \exp\left(-\frac{E_a}{RT}\right). \quad (3)$$

$$\ln k_{VRM} = -\frac{E_a}{RT} + \ln A. \quad (4)$$

In the formula, the k_{VRM} is the rate constant, min⁻¹; the A is the pre-exponential factor, min⁻¹; the E_a is the reaction activation energy, kJ/mol; the R is the gas constant (8.314 J/mol/K) and the X is the SC conversion.

Figure 6a,b shows the relationship between the microwave and conventional reaction times and carbon conversions. The slope of the fitted straight line was the reaction rate constant at this temperature. It was suggested that the reaction rate constant increased with an increase in temperature in the two heating methods, which indicated that when the temperature increased, the reaction rate increased. Figure 6c shows the Arrhenius diagram

of microwave and conventional reactions. For microwave and conventional reaction experiments, higher regression coefficients were obtained. The activation energy and pre-exponential factor were obtained from the slope of the fitted straight line. Table 2 shows the activation energy and pre-exponential energy under microwave and conventional heating. The activation energies were $47.1 \text{ kJ}\cdot\text{mol}^{-1}$ and $148.9 \text{ kJ}\cdot\text{mol}^{-1}$, respectively. The activation energy was much smaller than that under conventional heating. The large difference between the microwave-induced reaction rate and the thermal reaction rate indicated that the rate constant must have had a fundamentally different dependence on temperature, which was demonstrated in the Arrhenius parameter. In addition, as shown in Table 2, the exponential factor of the microwave heating reaction was significantly smaller than that of the conventional thermal reaction by more than 1000 orders of magnitude. Hunt et al. [26] suggested that a lower reaction temperature in the microwave experiment caused a lower collision frequency of reactants to reduce the pre-exponential term. That is to say, microwave heating should lead to a more efficient collision frequency of reactants.

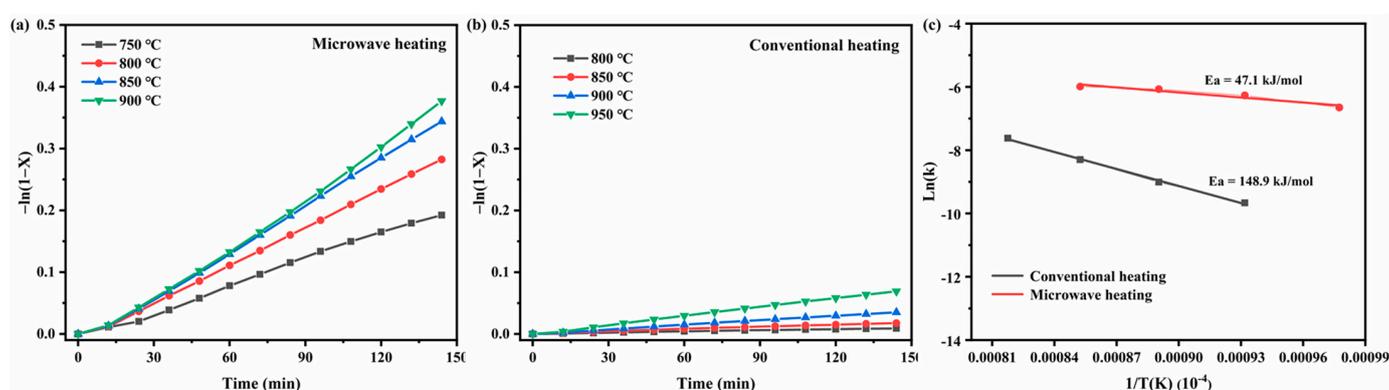


Figure 6. (a) Conversion versus time under MW; (b) Conversion versus time under CH; (c) Dynamic parameters obtained through the Arrhenius diagram.

Table 2. Kinetic parameters under microwave heating and conventional heating.

Parameters	Raw SC	CH-SC
$E_a/\text{kJ}\cdot\text{mol}^{-1}$	47.1	148.9
A/min^{-1}	0.3	1088.6

3. Materials and Methods

3.1. Materials

The semi-coke was provided by the Shanxi Lu'an Coal Industry (Changzhi, China). The ultimate analysis and proximate analysis are shown in Table 3. The semi-coke was dried, crushed and sieved into four particle sizes of $<0.200 \text{ mm}$, $0.200\text{--}0.450 \text{ mm}$, $0.450\text{--}0.850 \text{ mm}$ and $0.850\text{--}1.40 \text{ mm}$. Before the experiment, the semi-coke was continuously dried at $105 \text{ }^\circ\text{C}$ for 12 hrs and then stored in a well-sealed dryer for use in the experiment. This article named semi-coke as SC. Ar and CO_2 (purity of 99.9%), calcium oxide (CaO , 99% from Aldrich) and barium carbonate (BaCO_3 , 99% from Aldrich) were used in the experiment.

Table 3. The ultimate and proximate analysis of SC.

Ultimate Analysis (%)					Proximate Analysis (%)			
C	H	N	O	S	FC	M	V	Ash
82.3	0.7	1.15	14.8	0.9	81.7	1.5	2.9	14.8

FC: Fixed carbon; M: Moisture; V: Volatile.

3.2. Methods

The reactions heated by microwaves were carried out in a microwave fixed bed reactor (Synotherm Corporation, Changsha, China) and the experimental schematic diagram is shown in Figure S1. The microwave fixed bed reactor was heated by a monomodal cavity with a magnetron generator operating at 2.45 GHz (the maximum output power was 1500 W). The reactor was equipped with a temperature automatic control system and a quartz glass tube with an inner diameter of 38 mm and a length of 90 cm. For conventional heating, the reactions were carried out in a fixed bed reactor under the same conditions. In the experiment, approximately 40.0 ± 0.01 g of SC was first put into a quartz glass tube. Before the reaction, Ar was introduced into the reactor at a flow rate of 100 mL/min for 30 min. When the temperature reached the desired value, CO₂ gas was precisely introduced into the reactor and the reaction started. The composition of the gas products was analyzed online by a gas chromatograph (GC) (SHIMADZU, 2014C, Japan) equipped with a thermal conductivity detector (TCD) and a packed column (Porapak Q 80–100 mesh, 2 m × 4 mm) and the reacted SC was analyzed after the reaction. In our experiments, the heating rate in the conventional fixed bed reactor was 10 °C/min while in the microwave reactor the heating rate was 60 °C/min although the input power of the conventional fixed bed reactor and the microwave oven were 1200 kw and 800 kw, respectively.

3.3. Carbon Characterization and Data Analysis

The pore structures of SC were measured using a Micromeritics ASAP 2460 N₂ adsorption analyzer (ASAP 2460, Micromeritics, the United States). SC (0.1 g) was weighed and placed in a quartz tube for high-temperature vacuum degassing and then placed in a bottle containing liquid nitrogen at −196 °C for the N₂ adsorption/desorption experiments. The specific surface area was calculated using the BET equation and the average pore size data were calculated from the H-K equation (Horvath-Kawazoe equation). The surface structure of SC was observed by scanning electron microscopy (SEM) (FEI Nova Nono 450, Netherlands) with an accelerating voltage of 5.0 kV.

The real-time composition of the outlet gas was measured by a GC and the CO₂ conversion, CO output and SC conversion were calculated according to the changes before and after the CO₂ reaction as follows:

$$Con_{SC} = \frac{m - m_t}{m - m_{ash}} \quad (5)$$

where m , m_t and m_{ash} represented the initial mass of SC, the mass of SC after the reaction and the mass of ash in SC, respectively.

$$Con_{CO_2} = \frac{n_b - n_a}{n_b} \quad (6)$$

where n_b and n_a represented the moles of CO₂ before the reaction and the moles of CO₂ after the reaction, respectively.

4. Conclusions

The CO₂ gasification of semi-coke was studied through microwave radiation. We found that microwaves do have an excellent enhancement effect on the reaction. The experimental results showed that the maximum CO₂ conversion was 99.9% in the presence of barium carbonate. Based on the kinetic study, the activation energy for microwave heating was 47.1 kJ/mol while this value was 148.9 kJ/mol for conventional heating, indicating that microwaves could increase the Boudouard reaction and reduce the reaction activation energy. Thus, BaCO₃ for an enhanced microwave chemical Boudouard reaction makes the zero emission of CO₂ and the clean utilization of coal resources possible.

Supplementary Materials: The following are available online, Figure S1: Schematic diagram of the microwave experiment device; Table S1: Experiment data.

Author Contributions: Conceptualization, B.J. and H.Z.; research ideas: B.J., H.Z. and S.C.; investigation, H.D.; methodology, H.D. and S.C.; software, H.D.; validation, B.J., H.Z. and H.D.; formal analysis, H.D. and S.C.; data management: H.D.; writing—original draft preparation, H.D.; writing—review and editing, B.J. and H.Z.; supervision, B.J. and H.Z.; project administration, H.Z.; funding acquisition, B.J. All authors have read and agreed to the published version of the manuscript.

Funding: This work was supported by the Shanghai Science and Technology Committee(15DZ1206800).

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Conflicts of Interest: The authors declare no conflict of interest.

Sample Availability: Not available.

References

1. Song, C. Global challenges and strategies for control, conversion and utilization of CO₂ for sustainable development involving energy, catalysis, adsorption and chemical processing. *Catal. Today* **2006**, *115*, 2–32. [[CrossRef](#)]
2. Das Neves Gomes, C.; Blondiaux, E.; Thuery, P.; Cantat, T. Metal-free reduction of CO₂ with hydroboranes: Two efficient pathways at play for the reduction of CO₂ to methanol. *Chemistry* **2014**, *20*, 7098–7106. [[CrossRef](#)] [[PubMed](#)]
3. Lahijani, P.; Zainal, Z.A.; Mohammadi, M.; Mohamed, A.R. Conversion of the greenhouse gas CO₂ to the fuel gas CO via the Boudouard reaction: A review. *Renew. Sustain. Energy Rev.* **2015**, *41*, 615–632. [[CrossRef](#)]
4. Beller, M. Catalytic Carbonylation Reaction. *Organomet. Chem.* **2006**, *18*, 1–283.
5. Ratnasamy, C.; Wagner, J.P. Water Gas Shift Catalysis. *Catal. Rev.* **2009**, *51*, 325–440. [[CrossRef](#)]
6. Leadbeater, N.E. *Microwave Heating as a Tool for Sustainable Chemistry*; CRC Press: Boca Raton, FL, USA, 2017.
7. Bykov, Y.V.; Rybakov, K.I.; Semenov, V.E. High temperature microwave processing. *Appl. Phys.* **2001**, *34*, 55–75.
8. Gabriel, C.; Gabriel, S.; Grant, E.H.; Halstead, B.S.J.; Mingos, D.M.P. Dielectric parameters relevant to microwave dielectric heating. *Chem. Soc. Rev.* **1998**, *27*, 213–224. [[CrossRef](#)]
9. Jia, Z.; Lin, K.; Wu, G.; Xing, H.; Wu, H. Recent Progresses of High-Temperature Micro-wave-Absorbing Materials. *NANO* **2018**, *13*, 1830005. [[CrossRef](#)]
10. Bermúdez, J.M.; Ruisánchez, E.; Arenillas, A.; Moreno, A.H.; Menéndez, J.A. New concept for energy storage: Microwave-induced carbon gasification with CO₂. *Energy Convers. Manag.* **2014**, *78*, 559–564. [[CrossRef](#)]
11. Lahijani, P.; Mohammadi, M.; Zainal, Z.A.; Mohamed, A.R. Improvement of biomass char-CO₂ gasification reactivity using microwave irradiation and natural catalyst. *Thermochim. Acta* **2015**, *604*, 61–66. [[CrossRef](#)]
12. Lahijani, P.; Zainal, Z.A.; Mohamed, A.R.; Mohammadi, M. Microwave-enhanced CO₂ gasification of oil palm shell char. *Bioresour. Technol.* **2014**, *158*, 193–200. [[CrossRef](#)]
13. Chun, Y.N.; Song, H.G. Microwave-induced carbon-CO₂ gasification for energy conversion. *Energy* **2020**, *190*, 116386. [[CrossRef](#)]
14. Chun, Y.N.; Song, H.G. Microwave-enhanced gasification of sewage sludge waste. *Environ. Eng. Res.* **2018**, *24*, 591–599. [[CrossRef](#)]
15. Lartey-Young, G.; Ma, L. Remediation with Semicoke-Preparation, Characterization, and Adsorption Application. *Materials* **2020**, *13*, 4334. [[CrossRef](#)]
16. Ramirez, A.; Hueso, J.L.; Abian, M.; Alzueta, M.U.; Mallada, R.; Santamaria, J. Escaping undesired gas-phase chemistry: Microwave-driven selectivity enhancement in heterogeneous catalytic reactors. *Sci. Adv.* **2019**, *5*, eaau9000. [[CrossRef](#)]
17. Sugawara, H.; Kashimura, K.; Hayashi, M.; Ishihara, S.; Mitani, T.; Shinohara, N. Behavior of microwave-heated silicon carbide particles at frequencies of 2.0–13.5 GHz. *Appl. Phys. Lett.* **2014**, *105*, 034103. [[CrossRef](#)]
18. Thostenson, E.T.; Chou, T.W. Microwave processing fundamentals and applications. *Compos. Part A Appl. Sci.* **1999**, *30*, 1055–1071. [[CrossRef](#)]
19. Liu, Y.; Guan, Y.; Zhang, K. CO₂ gasification performance and alkali/alkaline earth metals catalytic mechanism of Zhundong coal char. *Korean J. Chem. Eng.* **2018**, *35*, 859–866. [[CrossRef](#)]
20. Uwaoma, R.C.; Strydom, C.A.; Bunt, J.R.; Okolo, G.N.; Matjie, R.H. The catalytic effect of Benfield waste salt on CO₂ gasification of a typical South African Highveld coal. *J. Therm. Anal. Calorim.* **2018**, *135*, 2723–2732. [[CrossRef](#)]
21. Lahijani, P.; Mohammadi, M.; Mohamed, A.R. Catalytic CO₂ gasification of rubber seed shell-derived hydrochar: Reactivity and kinetic studies. *Environ. Sci. Pollut. Res.* **2019**, *26*, 11767–11780. [[CrossRef](#)]
22. Irfan, M.F.; Usman, M.R.; Kusakabe, K. Coal gasification in CO₂ atmosphere and its kinetics since 1948: A brief review. *Energy* **2011**, *36*, 12–40. [[CrossRef](#)]
23. Wen, X.D.; Man, S.F.; Long, Y.J.; Xin, J.; Yan, Z.h.; Jian, G.Q.; Xin, L.J. Combustion characteristics of unburned pulverized coal and its reaction kinetics with CO₂. *Int. J. Miner. Metall. Mater.* **2019**, *26*, 811–821.
24. Zhang, Y.; Geng, P.; Zheng, Y. Exploration and practice to improve the kinetic analysis of char-CO₂ gasification via thermogravimetric analysis. *Chem. Eng. J.* **2019**, *359*, 298–304. [[CrossRef](#)]

-
25. Bhui, B.; Vairakannu, P. Experimental and kinetic studies on in-situ CO₂ gasification based chemical looping combustion of low ash coal using Fe₂O₃ as the oxygen carrier. *J. CO₂ Util.* **2019**, *29*, 103–116. [[CrossRef](#)]
 26. Hunt, J.; Ferrari, A.; Lita, A.; Crosswhite, M.; Ashley, B.; Stiegman, A.E. Microwave-Specific Enhancement of the Carbon–Carbon Dioxide (Boudouard) Reaction. *J. Phys. Chem. C* **2013**, *117*, 26871–26880. [[CrossRef](#)]