

Article

Multiple Twisted Chiral Nematic Structures in Cylindrical Confinement

Milan Ambrožič^{1,2}, Apparao Gudimalla^{3,4} , Charles Rosenblatt⁵  and Samo Kralj^{1,4,*} 

¹ Department of Physics, Faculty of Natural Sciences and Mathematics, University of Maribor, Koroška 160, 2000 Maribor, Slovenia; milan.ambrozic.prenosnik@gmail.com

² Faculty of Industrial Engineering, Šegova 112, 8000 Novo Mesto, Slovenia

³ Jožef Stefan International Postgraduate School, Jamova 39, 1000 Ljubljana, Slovenia; appigspl@gmail.com

⁴ Condensed Matter Physics, Jožef Stefan Institute, Jamova 39, 1000 Ljubljana, Slovenia

⁵ Department of Physics, Case Western Reserve University, Cleveland, OH 44106, USA; rosenblatt@case.edu

* Correspondence: samo.kralj@um.si

Received: 3 June 2020; Accepted: 3 July 2020; Published: 4 July 2020



Abstract: In this article, we theoretically and numerically study the chirality and saddle-splay elastic constant (K_{24})-enabled stability of multiple twist-like nematic liquid crystal (LC) structures in cylindrical confinement. We focus on the so-called radially z-twisted (RZT) and radially twisted (RT) configurations, which simultaneously exhibit twists in different spatial directions. We express the free energies of the structures in terms of dimensionless wave vectors, which characterise the structures and play the roles of order parameters. The impact of different confinement anchoring conditions is explored. A simple Landau-type analysis provides an insight into how different model parameters influence the stability of structures. We determine conditions for which the structures are stable in chiral and also nonchiral LCs. In particular, we find that the RZT structure could exhibit macroscopic chirality inversion upon varying the relevant parameters. This phenomenon could be exploited for the measurement of K_{24} .

Keywords: liquid crystals; chirality; saddle-splay elasticity; double twist deformations

1. Introduction

Chirality is pervasive in nature and refers to cases where an object and its mirror image are different [1–3]. It signals the absence of inversion symmetry, giving rise to a right-handed and left-handed appearance and behaviour. Chirality is present throughout physics and often impacts or even dominates numerous important natural phenomena. For example, chiral symmetry plays an important role in the Standard Model of physics [4]. The functionalities of several essential components of biological cells rely heavily on chirality [3]. Furthermore, it could be exploited in various technological and medical applications [5–7]. By exploiting chirality, one could engineer new materials with extraordinary properties (e.g., metamaterials exhibiting negative refractive index [8]). Therefore, a deep understanding of chirality and its related emergent behaviours is of interest throughout the physical and biological sciences.

However, several issues related to chirality remain unresolved, even at a fundamental level. For instance, the molecular origins of chirality and the relative role of chiral symmetry-breaking remain an open problem [9]. In particular, the mechanisms involved in the transfer of chirality from microscopic to macroscopic level [10] are not sufficiently understood. Convenient systems with which to gain a deeper understanding of the latter features are chiral uniaxial nematic liquid crystals (NLCs; a list of abbreviations appears at the end), one of the simplest representatives of anisotropic soft materials [11,12]. These systems are relatively easily accessible experimentally, structural changes can

be triggered by relatively weak external stimuli, and a macroscopic chiral response can be achieved using different pathways.

Uniaxial NLCs consist of approximately rod-shaped objects that, in bulk equilibrium, exhibit long-range orientational order and the absence of translational order [11]. The local orientational order is commonly described by the mesoscopic nematic director field $\vec{n}$, exhibiting head-to-tail invariance—the states $\pm\vec{n}$ are physically equivalent. In the classical Oseen–Frank approach [11], the elastic free energy is expressed as the sum of the so-called splay, twist, bend, and saddle-splay contributions, weighted by Frank splay (K_{11}), twist (K_{22}), bend (K_{33}), and saddle-splay (K_{24}) elastic constants. These contributions penalise different elastic distortions and determine equilibrium nematic director field patterns.

In the bulk achiral nematic phase, $\vec{n}$ is spatially homogeneously aligned along a single symmetry-breaking direction. In a simple chiral nematic (also referred to as the cholesteric) phase, in the bulk equilibrium structure, $\vec{n}$ twists in space, describing a helix where $\vec{n}$ is always perpendicular to the helix axis. This structure exhibits only a single twist (i.e., it twists only along one spatial direction) deformation.

Even more complex structures could be formed in chiral materials exhibiting a propensity for saddle-splay deformations [13,14], which in liquid crystals (LCs) is controlled by the saddle-splay elastic constant K_{24} . The energy elastic term weighted by K_{24} equals the Gaussian curvature of a hypothetical local surface [11], whose surface normal is determined by $\vec{n}$. This term is different from zero for the nematic structures displaying, e.g., double twist-like deformations, in which $\vec{n}$ varies in two orthogonal directions. Consequently, such structures could decrease the overall free energy for a large enough value of K_{24} . Note that the saddle-splay elastic term can be expressed as pure divergence, and can be mathematically integrated out to the surface confining the LC. Therefore, it affects LC order through boundary conditions. In most cases, the saddle-splay-enforced boundary tendency is masked by stronger surface anchoring conditions. For this reason, the K_{24} contribution is often ignored in theoretical modelling [11,14]. Its magnitude range is determined by Ericksen's inequality [15] $0 < K_{24} < K_{1,2}^{(min)}$, where $K_{1,2}^{(min)}$ corresponds to the lower elastic modulus of the twist (K_{22}) and splay (K_{11}) elastic deformations. Furthermore, due to the anchoring strength–“masking” effect it is relatively difficult to measure the magnitude of K_{24} . In other words, for strong enough anchoring [11] (i.e., $RW/K \gg 1$, where R is the characteristic confinement length, K stands for the average Frank elastic constant, and W is the surface anchoring strength coefficient), the surface anchoring contribution overrides the competing K_{24} contribution in the relevant surface Euler-Lagrange equilibrium equations. Consequently, only a few experimental measurements of K_{24} have been reported [16–18]. Several of these measurements report values of K_{24} that are close to $K_{1,2}^{(min)}$.

We note that a natural decomposition of representative nematic elastic distortions was recently proposed by Selinger [19]. Four bulk elastic normal modes were introduced, representing distinct irreducible representations of the rotational symmetry group characterising NLC symmetry. These are referred to as the double splay, double twist, bend, and biaxial splay mode, which could be separately and independently excited. On the contrary, the classical (single) splay, (single) twist, bend, and saddle-splay distortions [11,19] are, in general, coupled. For instance, the saddle-splay term can be expressed as a sum of double splay, double twist, and biaxial splay mode.

Nematic structures exhibiting nonplanar 3D nematic distortions (e.g., double twist deformations) impose elastic frustrations, which can be resolved in bulk by introducing assemblies of topological defects [20,21], as manifested in Blue Phases (BPs) [22–24]. In NLCs, a description of defects would require a more complex structural description in terms of the tensor nematic order parameter [11], which allows for the local melting of the LC order and the presence of biaxial states [25]. On the other hand, such deformations could be realised without defects in appropriate confinement geometries, where cylindrical confinements [26–31] are most often used. Note that stable 3D realisations of topological defects are of interest for science in general. For instance, if physical fields represent

fundamental entities of nature [32], then topological defects might represent [33] fundamental particles in the conventional “particle”-based natural description.

In this contribution, we consider nematic structures within chiral LCs in cylindrical confinement. We focus on the (meta) stability of multiple twist-type structures, which exhibit variations in the nematic molecular field simultaneously in at least two orthogonal spatial directions. We show that several structural properties can arise in the context of a simple Landau-type model. A more general analysis is carried out numerically. We determine regimes where one could observe a change in the handedness of structures by varying relevant material parameters. Furthermore, we determine regimes in which the saddle-splay elasticity sensitively controls the stability of competing structures.

2. Results

Of interest are defect-free spontaneously twisted NLC structures within an infinitely long cylinder of radius R . For this reason, we use cylindrical coordinates $\{r, \varphi, z\}$, defined by the unit vector triad $\{\vec{e}_r, \vec{e}_\varphi, \vec{e}_z\}$. We consider two different ansatzes, which give a good approximation of two qualitatively different families of solutions that are expected to be stable for the geometries and boundary conditions of interest well [26,27].

The first class is represented by [26,27]

$$\vec{n}^{(i)} = \cos\psi \sin\Omega \vec{e}_r + \sin\psi \sin\Omega \vec{e}_\varphi + \cos\Omega \vec{e}_z, \quad (1)$$

where $\psi = q_1 z - \varphi$, $\Omega = \frac{\pi}{2} - q_2 r \sin\psi$, the wave vectors q_1 and q_2 are variational parameters. A typical representative structure is shown in Figure 1a and in the Supplementary Materials.

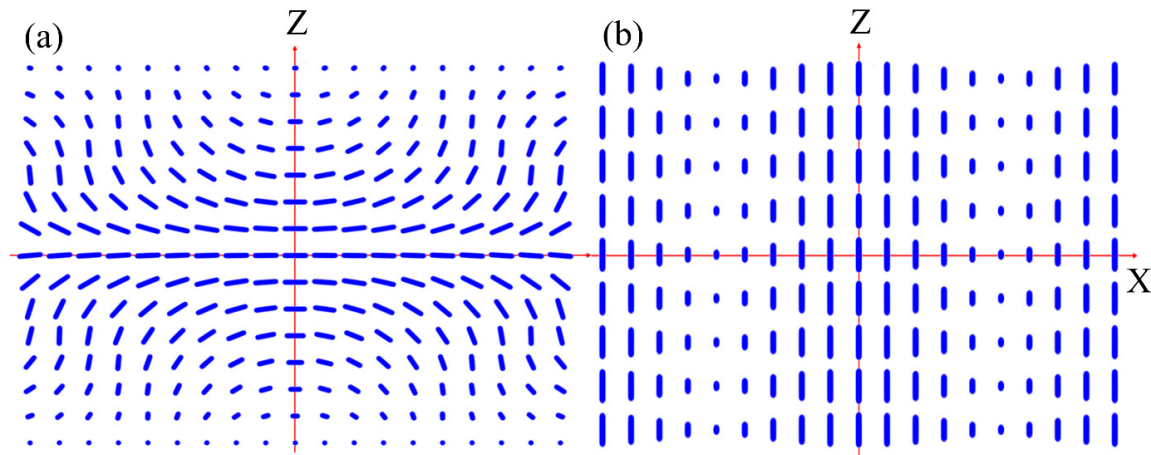


Figure 1. Twisted nematic structures. (a) The radially z-twist deformation. $Q_1 = 1.0$, $Q_2 = 1.0$. The twist is realised both along the $\vec{e}_\varphi$ and $\vec{e}_z$ directions. (b) The radially twisted structure. Here, the twist is realised along $\vec{e}_r$. $Q_{RT} = 1.1$.

In the Cartesian coordinates $\{x, y, z\}$ the ansatz reads $\vec{n}^{(i)} = \cos(q_1 z) \sin\Omega \vec{e}_x + \sin(q_1 z) \sin\Omega \vec{e}_y + \cos\Omega \vec{e}_z$. Cases $q_1 \neq 0$ and $q_2 \neq 0$ determine multiple twisted solutions. In these patterns, which we refer to as radially z-twisted (RZT) structures, twist deformation is realised both along the $\vec{e}_r$ and $\vec{e}_z$ directions [26]. This ansatz also encompasses single twisted structures. For example, for $q_2 = 0$ a structure twisting around the z axis is expressed as

$$\vec{n}^{(i)} = \cos(q_1 z - \varphi) \vec{e}_r + \sin(q_1 z - \varphi) \vec{e}_\varphi, \quad (2)$$

which corresponds to a classical cholesteric solution with wave vector q_1 .

The second family of solution corresponds to the radially twisted (RT) structures [26,27], where the twist is realised along $\vec{e}_r$, see Figure 1b. For this purpose, we use the ansatz

$$\vec{n}^{(ii)} = \sin\alpha \vec{e}_\varphi + \cos\alpha \vec{e}_z. \quad (3a)$$

Here, $\alpha = \alpha(r)$ and to avoid a singularity at the cylinder axis we impose the condition $\alpha(0) = 0$. Previous numerical studies [26,31] have revealed that the dependence of $\alpha(r)$ is roughly linear in r , even for large twists of $\vec{n}$. Consequently, we use the approximation:

$$\alpha = q_{RT}r. \quad (3b)$$

These structures were numerically studied in Refs. [26,27,31], where their stability was analysed. Our proposed ansatzes mimic the numerically obtained structures for the anchoring conditions of interest well for relatively small wave vectors and in the approximation of equal Frank elastic constants $K_{11} = K_{22} = K_{33}$. In the cases examined, the free energies of structures obtained (i) numerically by solving the relevant Euler–Lagrange equations or (ii) using our ansatzes differ by less than 10%. By using the analytical ansatzes, we were able to carry out a Landau-type approach, which enabled a more detailed insight into the stability of structures of interest for various different material-dependent parameters.

In the following, we use the approximation of equal elastic constants $K \equiv K_{11} = K_{22} = K_{33}$, but allow $K_{24} \neq K$. At the cylinder's lateral wall, $r = R$, we impose, for the positive anchoring strength, $W > 0$ (see Equation (19) in Methods) either (a) homeotropic anchoring ($\vec{e} = \vec{e}_r$), (b) tangential anchoring along $\vec{e}_z$ (i.e., $\vec{e} = \vec{e}_z$), or (c) tangential anchoring along $\vec{e}_\varphi$ ($\vec{e} = \vec{e}_\varphi$). We henceforth refer to these cases as (a) homeotropic, (b) zenithal tangential, and (c) azimuthal tangential anchoring, respectively. For $W < 0$, these cases correspond to isotropic tangential anchoring in a plane with a normal surface in the direction $\vec{e}$. Note that, in our study, the latter case is sensible only for condition (a).

For convenience, we introduce the following dimensionless quantities: $Q = qR$, $Q_1 = q_1R$, $Q_2 = q_2R$, $Q_{RT} = q_{RT}R$, $k_{24} = K_{24}/K$, $w = RW/K$, and the dimensionless free energy is scaled in units of $F_0 = \pi KH$. Therefore $F \rightarrow F/F_0$, where H is the height of the cylinder. For numerical convenience, we suppose that H is either large in comparison with the period $p = 2\pi/q_1$, or an integer number of p .

2.1. Free Energies of Structures

Using the ansatzes Equations (1) and (3) and the scaling described above, we calculate the free energies F of the structures (see Equation (1)). For later convenience, the energies are decomposed as $F^{(i)} = F_e^{(i)} + F_s^{(i)}$ and $F^{(ii)} = F_e^{(ii)} + F_s^{(ii)}$ for the first (RZT) and second class (RT) of solutions, respectively.

We consider first the family of solutions labelled by $\vec{n}^{(i)}$ (Equation (1)). The elastic contribution is

$$F_e^{(i)} = \frac{(Q - Q_2)^2}{2} + \frac{Q_1^2 Q_2^2}{8} + \frac{Q_1}{2} \left(\frac{Q_1}{2} + (1 - k_{24})Q_2 - Q \right) \left(1 + \frac{J_1(2Q_2)}{Q_2} \right) \quad (4)$$

Now let $F_s^{(i)}$ stand for the interface contribution, which is different for (a) homeotropic ($F_s^{(i)} = F_{s,h}^{(i)}$), (b) zenithal ($F_s^{(i)} = F_{s,z}^{(i)}$), and (c) azimuthal ($F_s^{(i)} = F_{s,\varphi}^{(i)}$) anchoring:

$$F_{s,h}^{(i)} = \frac{3w}{4} - \frac{w}{4} \frac{J_1(2Q_2)}{Q_2} \quad (5a)$$

$$F_{s,z}^{(i)} = \frac{w}{2} - \frac{w}{2} J_0(2Q_2), \quad (5b)$$

$$F_{s,\varphi}^{(i)} = \frac{3w}{4} + w \left(\frac{J_1(2Q_2)}{4Q_2} - \frac{J_0(2Q_2)}{2} \right). \quad (5c)$$

where J_0 and J_1 stand for the Bessel functions in the order of zero and one, respectively.

The second class of solutions is determined by the elastic term:

$$F_e^{(ii)} = \frac{1}{2}(Q + Q_{RT})^2 + \left(1 - k_{24} + \frac{Q}{Q_{RT}}\right) \sin^2 Q_{RT} + \int_0^1 \frac{\sin^2(Q_{RT}x)}{x} dx, \quad (6)$$

and surface contributions:

$$F_{s,h}^{(ii)} = w, \quad (7a)$$

$$F_{s,z}^{(ii)} = w \sin^2 Q_{RT}, \quad (7b)$$

$$F_{s,\varphi}^{(ii)} = w \cos^2 Q_{RT} \quad (7c)$$

We obtain solutions by varying the variational parameters Q_1 , Q_2 and Q_{RT} for the given material properties (determined by Q , k_{24} , w) and boundary conditions.

Of interest is the determination of regimes where radially z -twisted (RZT) or radially twisted (RT) structures are stable. We first perform an analytic analysis of these structures, where we expand the free energies in the limit of relatively small dimensionless wave numbers Q_1 , Q_2 and Q_{RT} . Then, we perform a more detailed stability analysis numerically.

2.2. Landau-Type Analysis

We first consider RZT (class 1) structures using the ansatz of Equation (4). By minimising the total free energy $F^{(i)}$ with respect to Q_1 , it follows that:

$$Q_1 = \frac{Q + (k_{24} - 1)Q_2}{1 + \frac{Q_2^2}{2(1 + \frac{J_1(2Q_2)}{Q_2})}} \quad (8)$$

In the following, we examine only the regimes of relatively low wave vectors Q_2 (i.e., $Q_2 \ll 1$), for which Equation (8) yields:

$$Q_1 \sim Q + (k_{24} - 1)Q_2 - \frac{Q_2^2 Q}{4}. \quad (9)$$

Taking this into account, we expand $F^{(i)}$ up to the fourth power in Q_2 . It follows that:

$$F_h^{(i)} = \frac{w}{2} + \frac{(Q - Q_2)^2}{2} - k_{24}QQ_2 + \frac{8k_{24} - 4k_{24}^2 + 2Q^2 + w}{8}Q_2^2 + \frac{Q(k_{24} - 1)}{2}Q_2^3 + \frac{24 - 48k_{24} + 24k_{24}^2 - 5Q^2 - 2w}{96}Q_2^4, \quad (10a)$$

$$F_z^{(i)} = \frac{(Q - Q_2)^2}{2} - k_{24}QQ_2 + \frac{4k_{24} - 2k_{24}^2 + Q^2 + 2w}{4}Q_2^2 + \frac{Q(k_{24} - 1)}{2}Q_2^3 + \frac{24 - 48k_{24} + 24k_{24}^2 - 5Q^2 - 12w}{96}Q_2^4, \quad (10b)$$

$$F_\varphi^{(i)} = \frac{w}{2} + \frac{(Q - Q_2)^2}{2} - k_{24}QQ_2 + \frac{8k_{24} - 4k_{24}^2 + 3w}{8}Q_2^2 + \frac{Q(k_{24} - 1)}{2}Q_2^3 + \frac{24 - 48k_{24} + 24k_{24}^2 - 10w}{96}Q_2^4. \quad (10c)$$

where $F_h^{(i)}$, $F_z^{(i)}$, and $F_\varphi^{(i)}$ denote $F^{(i)}$ for homeotropic, zenithal, and azimuthal anchoring, respectively. We thus obtain a Landau-type expansion of the form $F^{(i)} = F_0^{(i)} + \alpha_1 Q_2 + \alpha_2 Q_2^2 + \alpha_3 Q_2^3 + \alpha_4 Q_2^4$, where Q_2 and $\{\alpha_1, \alpha_2, \alpha_3, \alpha_4\}$ play the role of order parameter and Landau expansion coefficients, respectively.

For achiral LCs ($Q = 0$), one obtains:

$$F_h^{(i)} = \frac{w}{2} + \frac{8k_{24} - 4k_{24}^2 + w + 4}{8}Q_2^2 + \frac{24 - 48k_{24} + 24k_{24}^2 - 2w}{96}Q_2^4, \quad (11a)$$

$$F_z^{(i)} = \frac{4k_{24} - 2k_{24}^2 + 2w + 4}{4}Q_2^2 + \frac{24 - 48k_{24} + 24k_{24}^2 - 12w}{96}Q_2^4, \quad (11b)$$

$$F_\varphi^{(i)} = \frac{w}{2} + \frac{8k_{24} - 4k_{24}^2 + 3w + 4}{8}Q_2^2 + \frac{24 - 48k_{24} + 24k_{24}^2 - 10w}{96}Q_2^4. \quad (11c)$$

The spatially homogeneous order becomes unstable with respect to the RZT class of solutions where the coefficients α_2 that weight the Q_2^2 contribution in Equation (11) change signs. From the condition $\alpha_2 = 0$, one could deduce a critical value, k_{24} , above which the RZT structures become stable:

$$k_{24}^{(h)} = 1 + \sqrt{1 + \frac{w}{4}} \quad (12a)$$

$$k_{24}^{(z)} = 1 + \sqrt{1 + w} \quad (12b)$$

$$k_{24}^{(\varphi)} = 1 + \sqrt{1 + \frac{3w}{4}} \quad (12c)$$

where $k_{24}^{(h)}$, $k_{24}^{(z)}$, and $k_{24}^{(\varphi)}$ determine the critical values of k_{24} for homeotropic, zenithal, and azimuthal anchoring, respectively. Note that, in the approximation of equal elastic constants, the Ericksen critical value of K_{24} is given by $k_{24}^{(e)} = 2$. Therefore, in the absence of chirality, K_{24} could trigger twisted structures only for $w < 0$, which, in our modelling, is physically meaningful for the case given by Equation (12a).

Next, we focus on the RT structures using the ansatz of Equation (3). When $Q_{RT} \ll 1$, it follows that:

$$F_c^{(ii)} \sim \frac{Q^2}{2} + 2QQ_{RT} + (2 - k_{24})Q_{RT}^2 - \frac{QQ_{RT}^3}{3} + \frac{(k_{24} - \frac{5}{4})}{3}Q_{RT}^4. \quad (13)$$

It is easy to estimate the equilibrium value of the chirality wave number Q_{RT} of the RT structure if both Q and Q_{RT} are small. We use Equations (13) and (7) and free energy minimisation yields:

$$Q_{RT} = -Q/(2 + \Delta - k_{24}), \quad (14)$$

with $\Delta = 0$ for homeotropic anchoring, and $\Delta = \pm w$ for tangential anchorings (positive sign for zenithal anchoring and negative sign for azimuthal anchoring). Note that Equation (14) is valid only in the limit when $|Q_{RT}| < 1$.

For achiral LCs it follows that:

$$F_h^{(ii)} \sim w + (2 - k_{24})Q_{RT}^2 + \frac{(k_{24} - \frac{5}{4})}{3}Q_{RT}^4. \quad (15a)$$

$$F_z^{(ii)} \sim (2 - k_{24} + w)Q_{RT}^2 + \frac{(k_{24} - \frac{5}{4} - w)}{3}Q_{RT}^4. \quad (15b)$$

$$F_\varphi^{(ii)} \sim w + (2 - k_{24} - w)Q_{RT}^2 + \frac{(k_{24} - \frac{5}{4} + w)}{3}Q_{RT}^4. \quad (15c)$$

The critical conditions read:

$$k_{24}^{(h)} = 2, \quad (16a)$$

$$k_{24}^{(z)} = 2 + w, \quad (16b)$$

$$k_{24}^{(\varphi)} = 2 - w. \quad (16c)$$

Therefore, in achiral LCs, the saddle-splay elasticity may trigger an RT structure below $k_{24}^{(e)} = 2$ only in the case of azimuthal anchoring.

2.3. Numerical Analysis

We next explore the (meta) stability of double-twist structures in chiral LCs. Of particular interest is the determination of regimes in which the reversal of macroscopic chirality could be realised by varying a relevant parameter. Note that our estimates work well for dimensionless wave vectors less than one. Most of the “interesting” phenomena are realised in this regime. Therefore, results obtained for wave vectors larger than one are only indicative.

2.3.1. RZT Structure: Homeotropic Anchoring

We focus first on RZT (class 1) structures and homeotropic anchoring. Of interest is the exploration of the impact of the saddle-splay constant k_{24} and intrinsic chirality Q for relatively weak anchoring, which we set to $w = 1$. In Figure 2, we plot Q_1 and Q_2 equilibrium values (i.e., they determine local minima in F) varying Q between zero and one. For the case $Q = 0$ (achiral nematic) the RZT structures could be triggered only in the regime $k_{24} > k_{24}^{(e)} \equiv 2$. However, for chiral LCs, k_{24} efficiently promotes the stability of RZT structures well below $k_{24}^{(e)}$. Furthermore, for $k_{24} = 0$, it holds that $Q_2 = 0$ and $Q_1 = Q$. This solution corresponds to the classic cholesteric structure; see Equation (2). Graphs in Figure 2 also reveal that the value of k_{24} can be extracted experimentally.

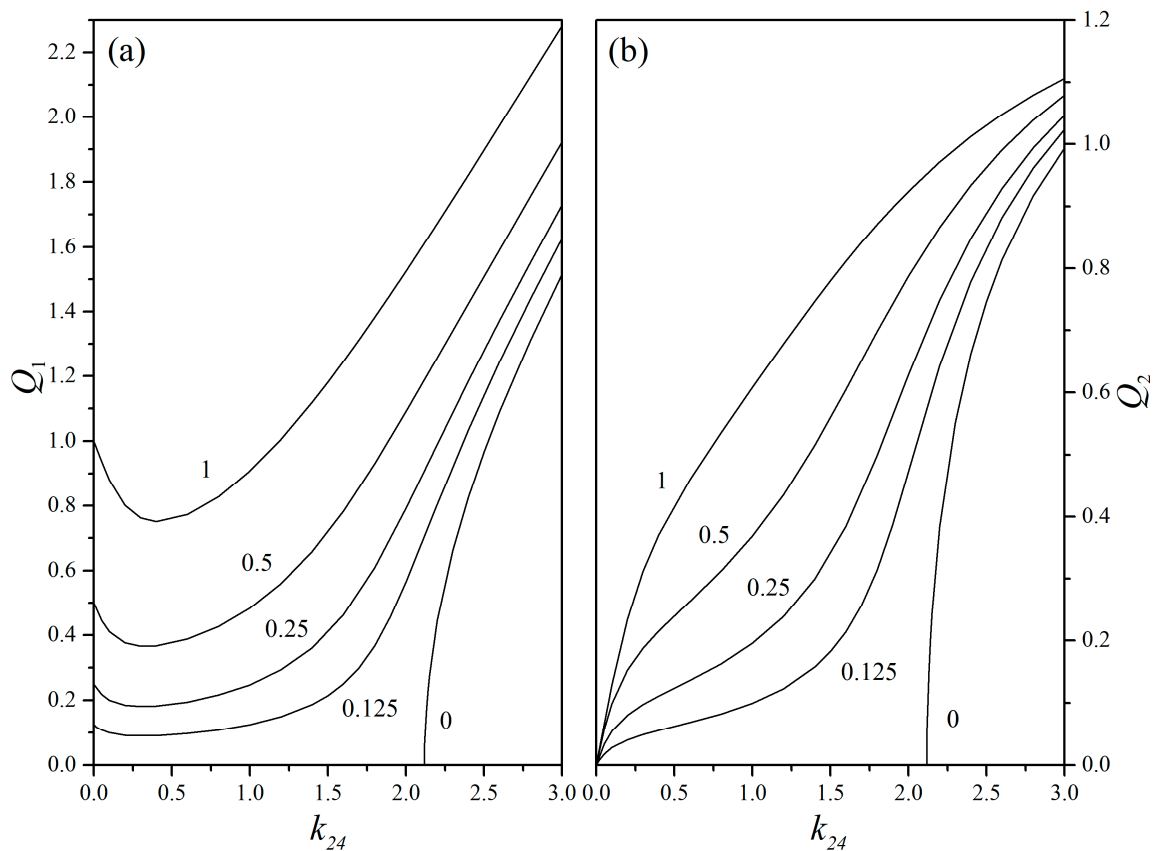


Figure 2. Dependence of equilibrium values of Q_1 (a) and Q_2 (b) on k_{24} for five different values of the intrinsic chirality Q (denoted by numbers in graphs). Homeotropic anchoring, $w = 1$.

2.3.2. RZT Structure: Tangential Anchoring

For tangential anchorings, the configurational variability of RZT structures is much more complex. This is illustrated in Figure 3, where we plot the dependencies of $Q_1(k_{24})$ and $Q_2(k_{24})$ on all studied anchoring conditions for two significantly different values of Q , viz., $Q = 0.125$ and $Q = 1$. The behaviour is roughly similar for homeotropic and azimuthal anchoring, whereas, for zenithal anchoring, qualitatively different features emerge. In particular, Q_1 could even change signs at a critical value of k_{24} , which we denote by $k_{24}^{(c)}$. Similarly, for a given value of k_{24} , this crossover could be achieved by varying Q , and we label the corresponding critical value as Q_c .

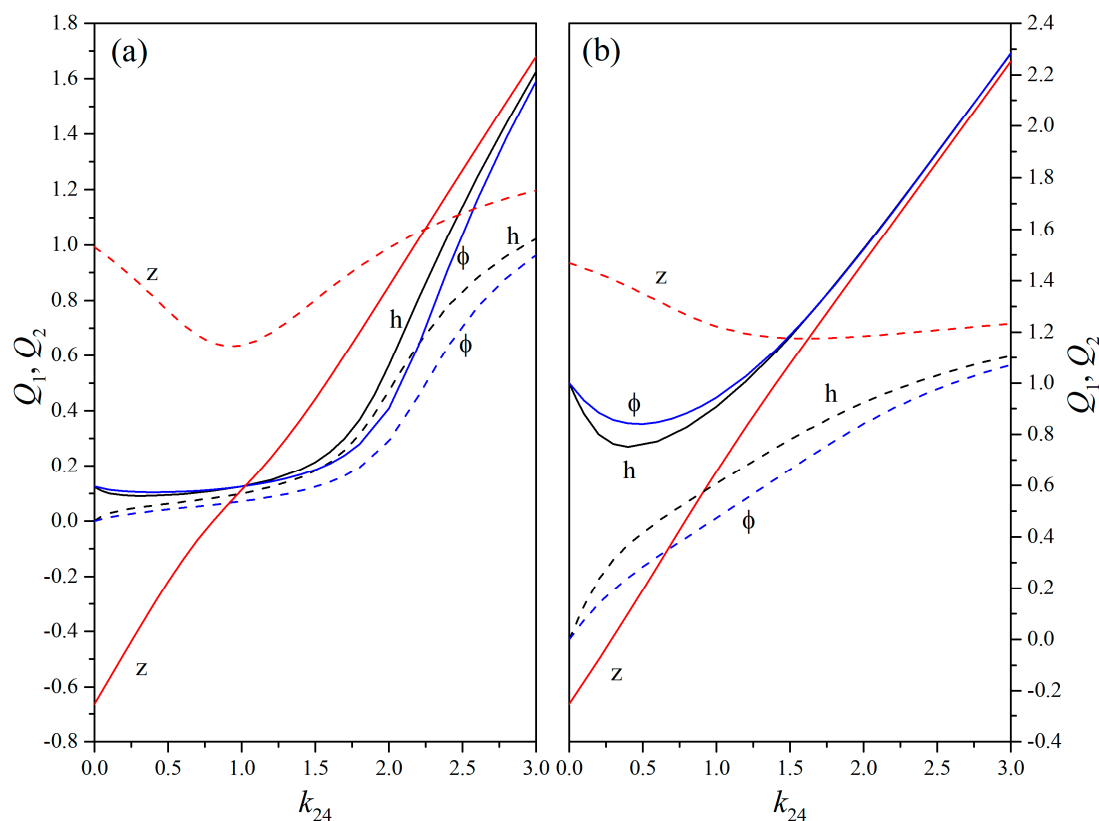


Figure 3. Dependence of Q_1 (solid lines) and Q_2 (dashed lines) on k_{24} for $Q = 0.125$ (a) and $Q = 1$ (b) and different types of anchoring, labelled by homeotropic (“h”), azimuthal (“ ϕ ”) and zenithal (“z”). $w = 1$.

Note that the value of $k_{24}^{(c)}$ depends relatively strongly on Q . Because the uniaxial twist with $Q_1 = 0$ can be observed easily by polarised optical microscopy, this phenomenon may be exploited to measure the splay–bend elastic constant. This is illustrated in Figure 4, where we plot the $Q_c(k_{24})$ dependence for different anchoring strengths. Experimentally, one could vary Q by adding a chiral dopant to LC. The reversal of the sign of Q_1 exists in the interval $0 < k_{24} < 1$, well below $k_{24}^{(e)}$. In the strong anchoring limit $W \rightarrow \infty$, the graph $Q_c(k_{24})$ approaches a straight line.

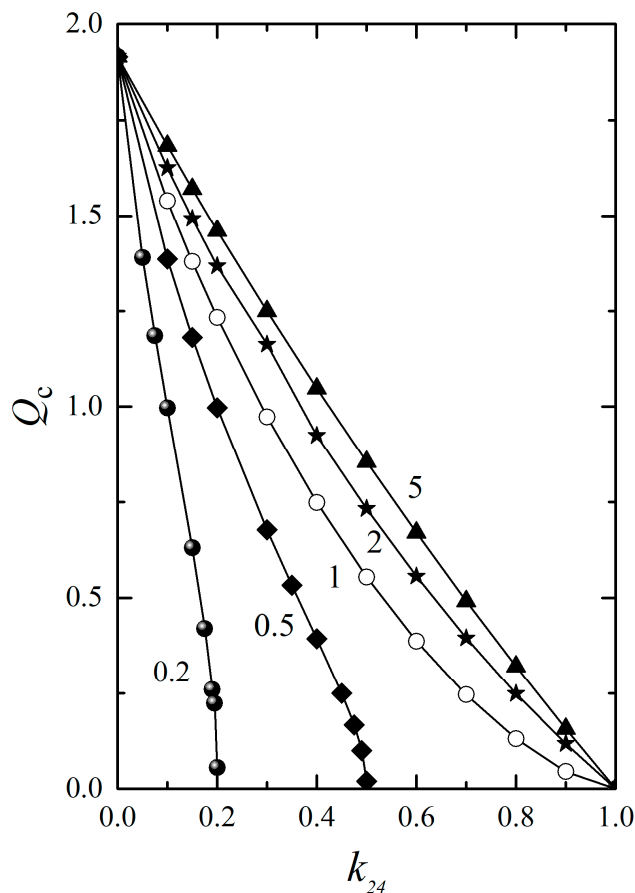


Figure 4. The dependence of the critical intrinsic chirality Q_c (where $Q_1 = 0$) on k_{24} in the case of zenithal anchoring for different values of anchoring strength. The results were calculated in points labelled with symbols and lines to serve as guides for the eye. From left to right: $w = 0.2$ (circles), 0.5 (diamonds), 1 (open circles), 2 (stars) and 5 (triangles).

2.3.3. Relative Stability of RZT and RT Structures

The minimum energies (corresponding to local minima in varying variational parameters) of both types of structures (RZT and RT) were compared for different sets of parameters. In general, homeotropic anchoring favours RZT configurations. This is obvious since the nematic director of the RT structure is always parallel to the boundary plane at the cylinder boundary. On the other hand, for both types of tangential anchoring, the stability regimes of different structures depend on a specific set of parameters, k_{24} , Q and w . Due to a broad parameter space, we limit our analysis to a few cases relevant to our study. For example, Figure 4 reveals the parameters for which $Q_1 = 0$ (chirality reversal) is realised for the RZT configuration for zenithal anchoring. It is essential to compare its free energy with the competitive RT structure. Some representative examples are depicted in Figures 5 and 6. In Figure 5, we plot the minimum energies of the competing structures on varying Q for $k_{24} = 0.5$ and weak ($w = 1$) zenithal anchoring for the case exhibiting chirality reversal. In this case, the RZT structure with $Q_1 < 0$ is metastable with respect to RT. However, Figure 5 illustrates the existence of a regime for which the configuration with $Q_1 < 0$ is stable for $k_{24} = 0.25$. Thus, chirality reversal may be found experimentally in this case. The arrows in Figure 5 approximately indicate the energy of the RZT structure at the reversal of the sign of Q_1 , together with the calculated chirality parameters. For lower values of Q , it holds that $Q_1 < 0$, and vice versa. Although the energies for $k_{24} = 0.25$ and 0.5 are not very different, the critical value of Q ($Q_c = Q$, where Q_1 changes signs) differs significantly: $Q_c = 0.554$ for $k_{24} = 0.5$, whereas $Q_c = 1.097$ for $k_{24} = 0.25$.

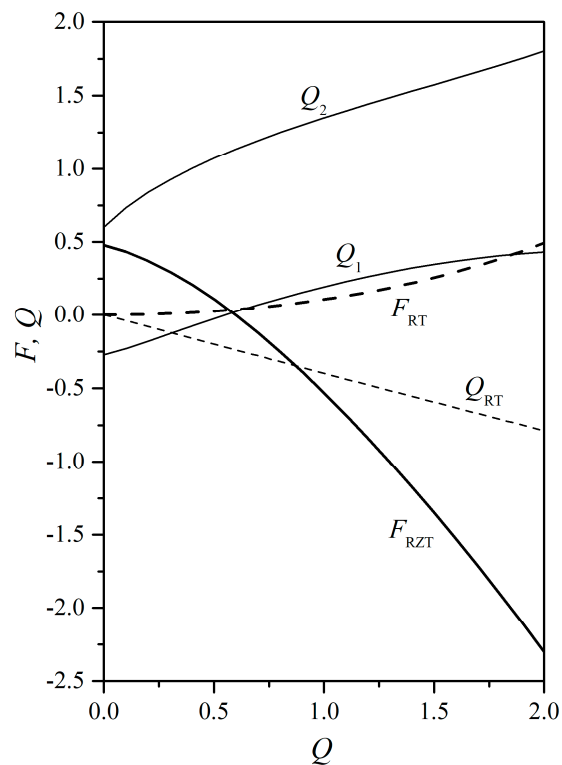


Figure 5. Dependence of the minimum energies (thick lines) and chirality parameters (thin lines) of the radially z-twisted (RZT) structure (solid lines) and radially twisted (RT) structure (dashed lines) on the intrinsic chirality Q . $k_{24} = 0.5$, zenithal anchoring with $w = 1$.

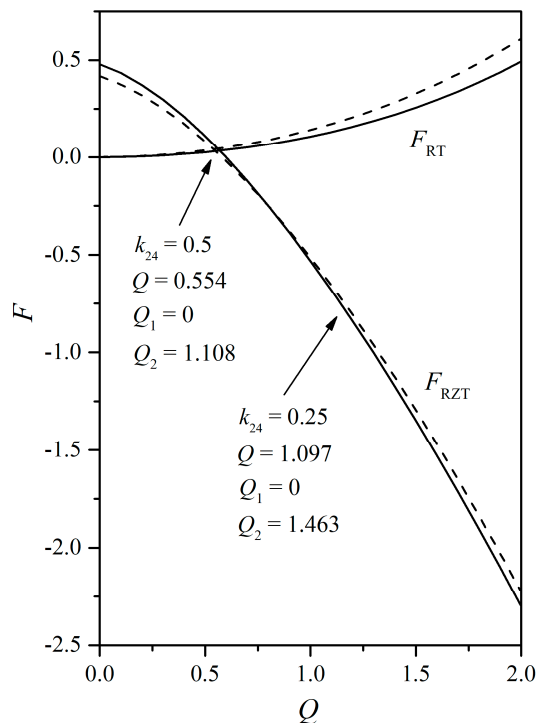


Figure 6. Dependence of the minimum energies of the RZT and RT structures on the intrinsic chirality Q . Solid lines: $k_{24} = 0.5$. Dashed lines: $k_{24} = 0.25$. Zenithal anchoring with $w = 1$. Arrows indicate the sign reversal of Q_1 for both values of k_{24} . For $k_{24} = 0.25$, the chirality Q_1 reverses its sign in the regime where $F_{RZT} < F_{RT}$.

Note that we have tested the stability of RZT and RT structures with respect to the nonchiral escaped radial structure [18], in which the director profile exhibits cylindrical symmetry. It tends to be radially oriented at the cylinder wall and gradually reorients along the z axis on approaching the cylinder axis. For homeotropic anchoring, it exists for $w = RW/K > 1$, and its free energy is given by [18]:

$$\frac{F}{\pi KH} = 3 - k_{24} - \frac{1}{\sigma} \quad (17)$$

where $\sigma = w + k_{24} - 1$. In the region of interest, this structure is energetically costlier with respect to the competing RZT or RT structure.

Finally, in Figures 7 and 8, we show calculated optical polarising microscopy patterns for the competing RZT and RT structures for two different polarisation directions of the polariser and analyser, where we set $Q_1 = Q_2 = Q_{RT} = 1$. Simulation details are described in [29]. The polarisations of the polariser and analyser are mutually perpendicular. The angle between the polariser and x -axis (horizontal axis) is 0° or 45° . One sees that the textures are significantly different and that one could easily distinguish these structures by using polarising optical microscopy.

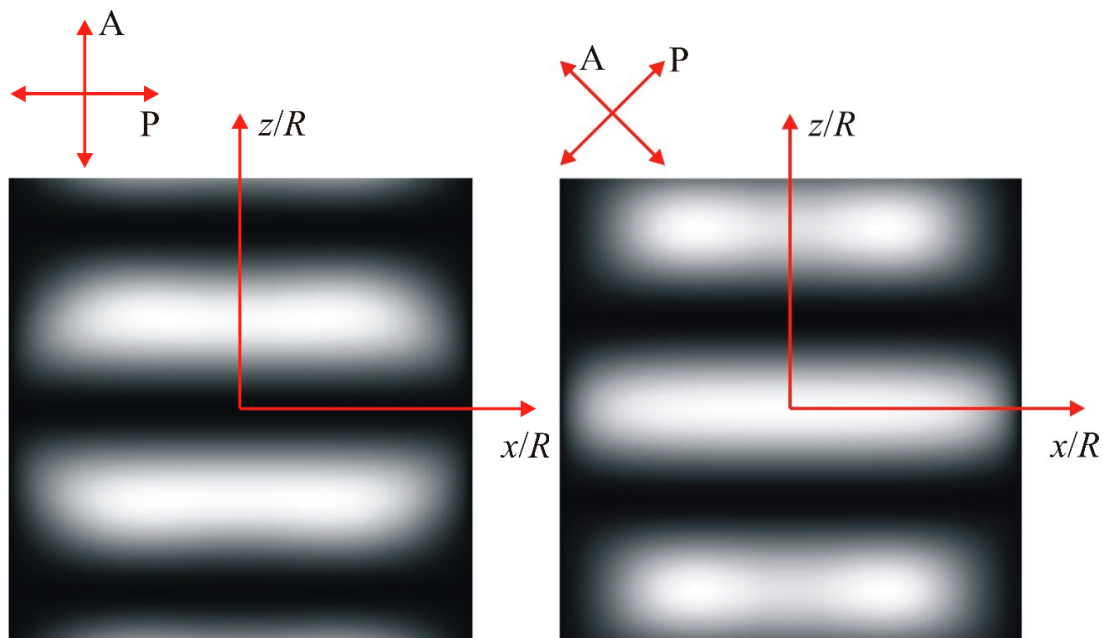


Figure 7. Calculated optical patterns for the RZT structure with $Q_1 = Q_2 = 1$. The transmitted polarisation of the polariser is in the x direction (left figure) and at an angle of 45° with respect to the x direction (right figure). Optical data: $R = 1 \mu\text{m}$, laser light wavelength $\lambda = 445 \text{ nm}$, refraction indices: $n_o = 1.544$, $n_e = 1.821$, corresponding to nematic liquid crystal (NLC) E7.

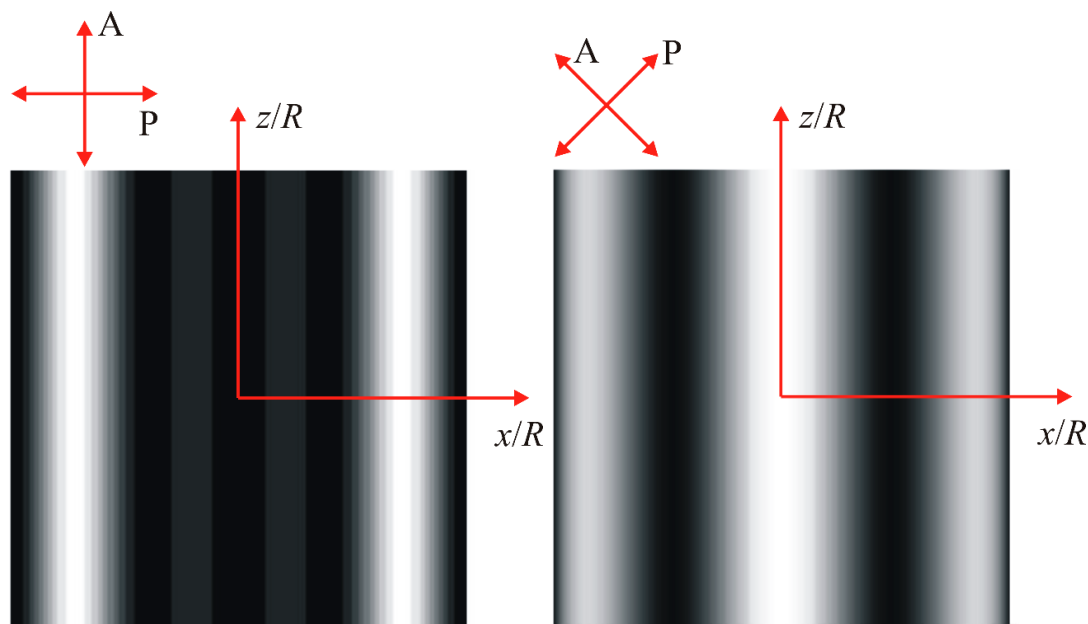


Figure 8. The same as for Figure 7, but for RT structure with $Q_{RT} = 1$.

3. Conclusions

We studied the impact of chirality, the saddle-splay elastic constant and anchoring conditions on the (meta) stability of radially z-twisted (RZT), and radially twisted (RT) configurations realised in a cylindrical confinement of the radius, R . We used the Oseen–Frank uniaxial description in terms of the nematic director field. Such a description is sensible because we do not consider configurations exhibiting topological defects, which would require the local melting of the nematic order or the presence of biaxiality. Furthermore, we used the approximation of equal Frank elastic constants $K_{11} = K_{22} = K_{33} \equiv K$. We expressed the free energy of structures in terms of dimensionless wavenumbers Q_1, Q_2, Q_{RT} , which represent order parameters in our Landau-type analysis. The parameter space controlling the relative stability of the structures consists of the dimensionless chirality $Q = Rq$, dimensionless saddle-splay constant $k_{24} = K_{24}/K$, and dimensionless anchoring strength $w = \frac{RW}{K}$.

We found that, in the absence of chirality, the RZT structure could be (meta) stable (fulfilling the Ericksen inequality $k_{24} < k_e \equiv 2$) only for isotropic tangential anchoring, provided that $k_{24} > 1 + \sqrt{1 - |w|/4}$. On the other hand, the RT structure could be (meta) stable for the azimuthal anchoring condition and $k_{24} > 2 - |w|$. However, chirality enables the stability of RZT structures for k_{24} values in the interval $k_{24} \in [0, 2]$. Furthermore, for $Q_{RT} < 1$, we found that the RT structures exhibit the wave vector $Q_{RT} \sim -Q/(2 + \Delta - k_{24})$, where (i) $\Delta = 0$, (ii) $\Delta = |w|$, (iii) $\Delta = -|w|$ for (i) homeotropic, (ii) zenithal, and (iii) azimuthal anchoring, respectively. In addition, we observed that the RZT configuration could exhibit a sign reversal of the wave vector for zenithal anchoring upon varying a relevant control parameter. This approach could be exploited for the experimental determination of K_{24} values, which still require considerably more exploration.

Note that multiple twisted structures could be exploited in several applications because their wave vectors can be adjusted to the optically visible regime. Such 3D structures could stabilise the lattices of disclinations, as manifested in the Blue Phases and related Skyrmion-like structures. The study of the latter structures could also provide an understanding of the fundamental workings of their nature, which is still lacking.

4. Methods

We used the Oseen–Frank continuum approach [11], where nematic structures are expressed in terms of the nematic director field $\vec{n}$. The free energy of confined NLCs is expressed as:

$$F = \iiint f_e d^3\vec{r} + \iint f_s d^2\vec{r}. \quad (18)$$

The first and second integrals are carried over the LC volume and over a NLC-confining surface. The quantities f_e and f_s determine the elastic and NLC-confining surface free energy density contributions.

The elastic term reads:

$$f_e = \frac{K_{11}}{2}(\nabla \cdot \vec{n})^2 + \frac{K_{22}}{2}(\vec{n} \cdot \nabla \times \vec{n} + q)^2 + \frac{K_{33}}{2}|\vec{n} \times \nabla \times \vec{n}|^2 - \frac{K_{24}}{2}\nabla \cdot (\vec{n} \nabla \cdot \vec{n} + \vec{n} \times \nabla \times \vec{n}). \quad (19)$$

The elastic response is determined by the splay (K_{11}), twist (K_{22}), bend (K_{33}) and saddle-splay (K_{24}) elastic constant, respectively. The wave vector q reflects the inherent LC chirality.

We modeled the surface interaction term using a simple Rapini–Papoular [11] description:

$$f_s = \frac{W}{2} \left(1 - (\vec{n} \cdot \vec{e})^2 \right). \quad (20)$$

Here, the unit vector $\vec{e}$ is commonly referred to as the easy axis. For instance, for $W > 0$, the corresponding free energy is locally minimised if $\vec{n}$ is aligned along $\vec{e}$. Furthermore, for $W < 0$, the term is minimised for $\vec{n} \perp \vec{e}$.

Supplementary Materials: The following are available online at <http://www.mdpi.com/2073-4352/10/7/576/s1>, Video S1: RZT structure, the Q1Q2 movie shows the radially z-twisted deformation and, here, the twist is realised both along the $\vec{e}_\varphi$ and $\vec{e}_z$ directions. The values used in the movie were from Q1 = 0.0 to 3.0, and Q2 = 0.0 to 3.0. Video S2: RT structure, the Qrt movie shows the radially twisted structure, and here the twist is realised along $\vec{e}_r$. The values used in the movie were from QRT = 0.0 to 3.0.

Author Contributions: M.A., S.K. and C.R. proposed and guided the research. M.A. did the numerical simulations, A.G. did the analytical analysis. M.A. and A.G. prepared the figures. All authors were involved in writing the paper. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Acknowledgments: A.G. acknowledges the support of AD FUTURA, the Public Scholarship, Development, Disability, and Maintenance Fund of the Republic of Slovenia. S.K. acknowledges the support of a Slovenian Research Agency grant P1-0099. C.R. was supported by the National Science Foundation Condensed Matter Physics program under grant DMR-1901797.

Conflicts of Interest: The authors declare no conflict of interest.

Abbreviations

The following abbreviations are used in this manuscript:

LC:	liquid crystal
BP:	blue phase
RZT:	radially z-twisted
RT:	radially twisted
NLC:	nematic liquid crystal

References

1. Pasteur, L. Memoires sur la relation qui peut exister entre la forme cristalline et al composition chimique, et sur la cause de la polarization rotatoire. *Compt. Rend.* **1848**, *26*, 535–538.

2. Harris, A.B.; Kamien, R.D.; Lubensky, T.C. Molecular chirality and chiral parameters. *Rev. Mod. Phys.* **1999**, *71*, 1745–1757. [[CrossRef](#)]
3. Green, M.M.; Jain, V. Homochirality in Life: Two Equal Runners, One Tripped. *Orig. Life Evol. Biosph.* **2010**, *40*, 111–118. [[CrossRef](#)] [[PubMed](#)]
4. Li, H.; Xu, S.; Rao, Z.-C.; Zhou, L.-Q.; Wang, Z.-J.; Zhou, S.-M.; Tian, S.-J.; Gao, S.-Y.; Li, J.-J.; Huang, Y.-B. Chiral fermion reversal in chiral crystals. *Nat. Commun.* **2019**, *10*, 5505. [[CrossRef](#)] [[PubMed](#)]
5. Green, M.M.; Peterson, N.C.; Sato, T.; Teramoto, A.; Cook, R.; Lifson, S. A Helical Polymer with a Cooperative Response to Chiral Information. *Science* **1995**, *268*, 1860–1866. [[CrossRef](#)]
6. Hendry, E.; Carpy, T.; Johnston, J.; Popland, M.; Mikhaylovskiy, R.V.; Lapthorn, A.J.; Kelly, S.M.; Barron, L.D.; Gadegaard, N.; Kadodwala, M. Ultrasensitive detection and characterization of biomolecules using superchiral fields. *Nat. Nanotechnol.* **2010**, *5*, 783–787. [[CrossRef](#)]
7. Soukoulis, C.M.; Wegener, M. Past achievements and future challenges in the development of three-dimensional photonic metamaterials. *Nat. Photonics* **2011**, *5*, 523–530. [[CrossRef](#)]
8. Zhang, S.; Park, Y.-S.; Li, J.; Lu, X.; Zhang, W.; Zhang, X. Negative Refractive Index in Chiral Metamaterials. *Phys. Rev. Lett.* **2009**, *102*, 023901. [[CrossRef](#)]
9. Wu, L.; Sun, H. Manipulation of cholesteric liquid crystal phase behavior and molecular assembly by molecular chirality. *Phys. Rev. E* **2019**, *100*, 022703. [[CrossRef](#)]
10. Kim, Y.; Yeom, B.; Arteaga, O.; Jo Yoo, S.; Lee, S.-G.; Kim, J.-G.; Kotov, N.A. Reconfigurable chiroptical nanocomposites with chirality transfer from the macro- to the nanoscale. *Nat. Mater.* **2016**, *15*, 461–468. [[CrossRef](#)]
11. Kleman, M.; Lavrentovich, O.D. *Soft Matter Physics: An Introduction*; Springer Science & Business Media: New York, NY, USA, 2007; ISBN 0387952675.
12. Palffy-Muhoray, P. The diverse world of liquid crystals. *Phys. Today* **2007**, *60*, 54–60. [[CrossRef](#)]
13. Sparavigna, A.; Lavrentovich, O.D.; Strigazzi, A. Periodic stripe domains and hybrid-alignment regime in nematic liquid crystals: Threshold analysis. *Phys. Rev. E* **1994**, *49*, 1344–1352. [[CrossRef](#)] [[PubMed](#)]
14. Lavrentovich, O.D.; Pergamenschchik, V.M. Patterns in thin liquid crystals films and the divergence (“surfcelike”) elasticity. *Int. J. Mod. Phys. B* **1995**, *9*, 2389–2437. [[CrossRef](#)]
15. Ericksen, J.L. Inequalities in Liquid Crystal Theory. *Phys. Fluids* **1966**, *9*, 1205–1207. [[CrossRef](#)]
16. Polak, R.D.; Crawford, G.P.; Kostival, B.C.; Doane, J.W.; Žumer, S. Optical determination of the saddle-splay elastic constant K_{24} in nematic liquid crystals. *Phys. Rev. E* **1994**, *49*, R978–R981. [[CrossRef](#)]
17. Allender, D.W.; Crawford, G.P.; Doane, J.W. Determination of the liquid-crystal surface elastic constant K_{24} . *Phys. Rev. Lett.* **1991**, *67*, 1442–1445. [[CrossRef](#)]
18. Crawford, G.P.; Allender, D.W.; Doane, J.W. Surface elastic and molecular-anchoring properties of nematic liquid crystals confined to cylindrical cavities. *Phys. Rev. A* **1992**, *45*, 8693–8708. [[CrossRef](#)]
19. Selinger, J.V. Interpretation of saddle-splay and the Oseen-Frank free energy in liquid crystals. *Liq. Cryst. Rev.* **2018**, *6*, 129–142. [[CrossRef](#)]
20. Mermin, N.D. The topological theory of defects in ordered media. *Rev. Mod. Phys.* **1979**, *51*, 591–648. [[CrossRef](#)]
21. Kurik, M.V.; Lavrentovich, O.D. Defects in liquid crystals: Homotopy theory and experimental studies. *Sov. Phys. Uspekhi* **1988**, *31*, 196–224. [[CrossRef](#)]
22. Meiboom, S.; Sammon, M. Structure of the Blue Phase of a Cholesteric Liquid Crystal. *Phys. Rev. Lett.* **1980**, *44*, 882–885. [[CrossRef](#)]
23. Ravník, M.; Alexander, G.P.; Yeomans, J.M.; Zumer, S. Three-dimensional colloidal crystals in liquid crystalline blue phases. *Proc. Natl. Acad. Sci. USA* **2011**, *108*, 5188–5192. [[CrossRef](#)] [[PubMed](#)]
24. Jo, S.-Y.; Jeon, S.-W.; Kim, B.-C.; Bae, J.-H.; Araoka, F.; Choi, S.-W. Polymer Stabilization of Liquid-Crystal Blue Phase II toward Photonic Crystals. *ACS Appl. Mater. Interfaces* **2017**, *9*, 8941–8947. [[CrossRef](#)]
25. Schopohl, N.; Sluckin, T.J. Defect Core Structure in Nematic Liquid Crystals. *Phys. Rev. Lett.* **1987**, *59*, 2582–2584. [[CrossRef](#)]
26. Ambrožič, M.; Žumer, S. Chiral nematic liquid crystals in cylindrical cavities. *Phys. Rev. E* **1996**, *54*, 5187–5197. [[CrossRef](#)]
27. Ambrožič, M.; Žumer, S. Axially twisted chiral nematic structures in cylindrical cavities. *Phys. Rev. E* **1999**, *59*, 4153–4160. [[CrossRef](#)]

28. Jeong, J.; Kang, L.; Davidson, Z.S.; Collings, P.J.; Lubensky, T.C.; Yodh, A.G. Chiral structures from achiral liquid crystals in cylindrical capillaries. *Proc. Natl. Acad. Sci. USA* **2015**, *112*, E1837–E1844. [[CrossRef](#)]
29. Crawford, G.P.; Mitcheltree, J.A.; Boyko, E.P.; Fritz, W.; Žumer, S.; Doane, J.W. K33/K11 determination in nematic liquid crystals: An optical birefringence technique. *Appl. Phys. Lett.* **1992**, *60*, 3226–3228. [[CrossRef](#)]
30. Kralj, S.; Žumer, S. The stability diagram of a nematic liquid crystal confined to a cylindrical cavity. *Liq. Cryst.* **1993**, *15*, 521–527. [[CrossRef](#)]
31. Ondris-Crawford, R.J.; Ambrožič, M.; Doane, J.W.; Žumer, S. Pitch-induced transition of chiral nematic liquid crystals in submicrometer cylindrical cavities. *Phys. Rev. E* **1994**, *50*, 4773–4779. [[CrossRef](#)]
32. Hobson, A. There are no particles, there are only fields. *Am. J. Phys.* **2013**, *81*, 211–223. [[CrossRef](#)]
33. Skyrme, T.H.R. A unified field theory of mesons and baryons. *Nucl. Phys.* **1962**, *31*, 556–569. [[CrossRef](#)]



© 2020 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).