




Article

Synthesis, Properties, and Biodegradability of Novel Sequence-Controlled Copolyesters Composed of Glycolic Acid, Dicarboxylic Acids, and C₃ or C₄ Diols

Yuushou Nakayama ^{1,*} , Keitaro Fukumoto ¹, Yuji Kusu ¹, Ryo Tanaka ¹ , Takeshi Shiono ¹ ,
Norioki Kawasaki ², Naoko Yamano ² and Atsuyoshi Nakayama ²

¹ Department of Applied Chemistry, Graduate School of Advanced Science and Engineering, Hiroshima University, 1-4-1 Kagamiyama, Higashi-Hiroshima 739-8527, Hiroshima, Japan

² Biomedical Research Institute, National Institute of Advanced Industrial Science and Technology (AIST), 1-8-31 Midorigaoka, Ikeda 563-8577, Osaka, Japan

* Correspondence: yuushou@hiroshima-u.ac.jp

Abstract: We have previously reported that sequence-controlled copolyesters such as poly((ethylene diglycolate) terephthalate) (poly(GEGT)) showed higher melting temperatures than those of the corresponding random copolymers and high biodegradability in seawater. In this study, to elucidate the effect of the diol component on their properties, a series of new sequence-controlled copolyesters composed of glycolic acid, 1,4-butanediol or 1,3-propanediol, and dicarboxylic acid units was studied. 1,4-Butylene diglycolate (GBG) and 1,3-trimethylene diglycolate (GPG) were prepared by the reactions of 1,4-dibromobutane or 1,3-dibromopropane with potassium glycolate, respectively. Polycondensation of GBG or GPG with various dicarboxylic acid chlorides produced a series of copolyesters. Terephthalic acid, 2,5-furandicarboxylic acid, and adipic acid were used as the dicarboxylic acid units. Among the copolyesters bearing terephthalate or 2,5-furandicarboxylate units, the melting temperatures (T_m) of the copolyesters containing 1,4-butanediol or 1,2-ethanediol units were substantially higher than those of the copolyester containing the 1,3-propanediol unit. Poly((1,4-butylenediglycolate) 2,5-furandicarboxylate) (poly(GBGF)) showed a T_m at 90 °C, while the corresponding random copolymer was reported to be amorphous. The glass-transition temperatures of the copolyesters decreased as the carbon number of the diol component increased. Poly(GBGF) was found to show higher biodegradability in seawater than that of poly(butylene 2,5-furandicarboxylate) (PBF). On the other hand, the hydrolysis of poly(GBGF) was suppressed in comparison with that of poly(glycolic acid). Thus, these sequence-controlled copolyesters have both improved biodegradability compared to PBF and lower hydrolyzability than PGA.

Keywords: sequence-controlled copolyesters; alkanediols; glycolic acid; dicarboxylic acid; biodegradation in seawater; hydrolysis



Citation: Nakayama, Y.; Fukumoto, K.; Kusu, Y.; Tanaka, R.; Shiono, T.; Kawasaki, N.; Yamano, N.; Nakayama, A. Synthesis, Properties, and Biodegradability of Novel Sequence-Controlled Copolyesters Composed of Glycolic Acid, Dicarboxylic Acids, and C₃ or C₄ Diols. *Polymers* **2023**, *15*, 1155. <https://doi.org/10.3390/polym15051155>

Academic Editors: Manuela Zubitur, Ricardo I. Castro Cepeda and Cristian Rodrigo Valdes Vergara

Received: 28 January 2023

Revised: 16 February 2023

Accepted: 20 February 2023

Published: 24 February 2023



Copyright: © 2023 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Because of the problems of global warming and plastic pollution, bioplastics including bio-based polymers and/or biodegradable polymers are attracting current attention. Aliphatic polyesters such as poly(L-lactic acid) [1–3] and poly(glycolic acid) (PGA) [3,4] are known as representative biodegradable polymers. On the other hand, aromatic polyesters such as poly(ethylene terephthalate) (PET), poly(trimethylene terephthalate) (PTT), and poly(butylene terephthalate) (PBT) have excellent thermal and mechanical properties and are widely used as commodity plastics as well as fibers. However, aromatic polyesters generally have poor biodegradability, which leads to the accumulation of waste plastics in the environment. From these backgrounds, aliphatic–aromatic copolyesters have been studied to develop polymers with both good physical properties and biodegradability.

ity [5,6]. The production of some aliphatic–aromatic copolyesters such as poly(butylene terephthalate-*co*-adipate) (PBAT) [7] has been commercialized.

Some copolyesters containing lactic acid have been reported. Olewnik [8] and Gara [9] synthesized poly(ethylene terephthalate-*co*-lactic acid) from the reaction of bis(2-hydroxyethyl terephthalate) (BHET) with L-lactic acid oligomers and that of BHET with lactide, respectively. The content of aromatic ester units in the copolymers affected the melting temperature (T_m) of the copolymer, and the copolymer with about 80% aromatic ester units showed a T_m of 215 °C, while the copolymer with 60% aromatic ester units showed no T_m . PGA is a highly biodegradable and hydrolyzable polymer [3,4], and the incorporation of glycolic acid components into other polymers has also been studied. Olewnik et al. reported the synthesis of poly(ethylene terephthalate-*co*-glycolic acid) from the reaction of BHET with glycolic acid oligomers [10]. The T_m of the copolyester with 36 mol% of glycolic acid was detected at 166 °C. Ding et al. and Tial et al. recently independently reported poly(butylene succinate-*co*-glycolic acid) (PBSGA), which showed higher enzymatic hydrolyzability than poly(butylene succinate) [11,12]. The structures of these copolymers are random or block-like.

We recently synthesized ABAC-type sequence-regulated aliphatic–aromatic copolyesters composed of glycolic acid, ethylene glycol, and terephthalic acid units [13]. In this study, poly((ethylene diglycolate) terephthalate) (poly(GEGT)) was found to show relatively high T_m in comparison with the corresponding random copolymer. Poly(GEGT) also exhibited high biodegradability in seawater.

It is known that the properties of polyesters significantly depend on whether the carbon numbers of the components are odd or even, where the polyesters composed of diols with even carbon numbers tend to exhibit higher T_m than those with odd carbon numbers [14–16].

To elucidate the effect of the diol structure on the properties of the ABAC-type sequence-controlled aliphatic–aromatic copolyesters, in this study, a series of the sequence-controlled copolyesters composed of glycolic acid, dicarboxylic acids, and 1,4-butanediol or 1,3-propanediol was synthesized. Their thermal properties, biodegradability in seawater, and hydrolyzability were investigated.

2. Materials and Methods

2.1. General

All polymerization reactions were conducted under a nitrogen (N_2) atmosphere using Schlenk techniques. 1H and ^{13}C NMR spectra were recorded on Varian system 500 (Santa Clara, CA, USA) or JEOL Lambda 500 spectrometers (Tokyo, Japan) (500 MHz for 1H nucleus or 125 MHz for ^{13}C nucleus, respectively). Chemical shifts of 1H NMR spectra were calibrated by using the signal for the residual protons in chloroform-*d* ($\delta = 7.26$ ppm) or in 1,1,2,2-tetrachloroethane ($\delta = 6.00$ ppm). Chemical shifts of ^{13}C NMR spectra were calibrated by using the signal for the carbons in chloroform-*d* ($\delta = 77.16$ ppm) or in 1,1,2,2-tetrachloroethane ($\delta = 74.0$ ppm). Electrospray ionization mass spectrometry (ESI-MS) experiments were carried out on a Thermo Fisher Scientific LTQ Orbitrap XL (Waltham, MA, USA) at the Natural Science Center for Basic Research and Development (N-BARD), Hiroshima University. Spectra were recorded in a positive ion mode using a spray voltage of 5.0 kV and mass range of m/z 100–2000. Samples were dissolved in methanol as a matrix solution. Elemental analysis was performed on a Perkin Elmer 2400 series II CHN/O analyzer (Waltham, MA, USA). Molecular weights and polydispersities of the polymers soluble in tetrahydrofuran (THF) were determined by gel permeation chromatography (GPC) measurements on a Tosoh GPC system (HLC-8320, Tokyo, Japan) equipped with an RI detector connected to a series of TSK gel columns G2000, G3000, G4000, and G5000. THF was used as an eluent at a flow rate of 1.0 mL/min at 40 °C. Molecular weights and polydispersities of the polymers soluble in $CHCl_3$ but insoluble in THF were determined by GPC measurements on a JASCO GPC system (PU-2080, Tokyo, Japan) equipped with an RI detector. $CHCl_3$ was used as an eluent at a flow rate of 1.0 mL/min at 40 °C. The GPC curves were calibrated using standard polystyrenes. Molecular weights and polydispersities

of the polymers insoluble in both THF and chloroform were determined using a GPC system (HLC-8220, TOSOH Co., Tokyo, Japan). Poly(methyl methacrylate) was used as a standard substance. A column (TSK gel Super HM-N, TOSOH Co., Tokyo, Japan) was used with 1,1,1,3,3,3-hexafluoro-2-propanol (HFIP) (Central Glass Co. Ltd., Tokyo, Japan) as an eluent (0.2 mL/min, 40 °C). The melting temperature (T_m), melting enthalpy (ΔH_m), and glass transition temperature (T_g) of the polymers were measured by differential scanning calorimetry (DSC) using a Seiko DSC 6220 apparatus (Chiba, Japan). The heating rate was 10 °C/min in a nitrogen stream. The T_m and ΔH_m were read from the first heating scan. The T_g values of the polymers were defined as the midpoint temperature of a heat capacity change in the second heating scan.

2.2. Materials

Glycolic acid (GA), thionyl chloride (SOCl_2), 1,4-butanediol (BD), adipic acid (AA), 2,5-furandicarboxylic acid (FDCA), and *N,N*-dimethylacetamide (DMAc) were purchased from Tokyo Chemical Industry Co. Potassium hydrogen carbonate and *o*-dichlorobenzene (ODCB) were purchased from Wako Pure Chemical Industries, Ltd. *N,N*-Dimethylformamide (DMF), 1,1,2,2-tetrachloroethane (TCE), pyridine, acetone, chloroform, methanol, THF, dimethyl sulfoxide (DMSO), and sulfuric acid (H_2SO_4) were purchased from Kanto Chemical Co., Inc (Tokyo Japan). 1,3-Dibromopropane (DBP), terephthaloyl dichloride (TC), and adipoyl dichloride (AC) were purchased from Tokyo Chemical Industry Co. (Tokyo Japan). 1,4-Dibromobutane, and poly(glycolic acid) (PGA) were purchased from Sigma-Aldrich, Inc. (St. Louis, MO, USA) Poly(butylene furanoate) (PBF) [17] and poly(butylene adipate) (PBA) [18] were prepared according to the literatures. 2,5-Furandicarbonyl dichloride (FC) was prepared from the reaction of FDCA with SOCl_2 according to the literature [19].

2.3. Synthesis of 1,4-Butylene Diglycolate (GBG)

First, potassium glycolate was prepared by the reaction of glycolic acid (0.134 mol) and potassium hydrogen carbonate (0.160 mol) in water (40 mL) at r.t. for 1 h, followed by evaporation to dryness. 1,4-Dibromobutane (0.016 mol) was added to a solution of potassium glycolate (0.035 mol) in DMF (30 mL) and the mixture was stirred at 80 °C for 2 h. Then, DMF was removed from the resulting mixture under reduced pressure to yield a solid. Acetone was added to the solid and the mixture was filtrated through silica gel. The filtrate was dried in air to give GBG as a white solid in 67% yield. ^1H NMR (500 MHz, CDCl_3 , r.t.): δ 4.23 (t, 4H, J = 6.0 Hz, $\text{OCH}_2\text{CH}_2\text{CH}_2\text{CH}_2\text{O}$), 4.17 (s, 4H, COCH_2OH), 2.53 (br, 2H, COCH_2OH), 1.75 (m, 4H, $\text{OCH}_2\text{CH}_2\text{CH}_2\text{CH}_2\text{O}$). ^{13}C NMR (125 MHz, CDCl_3 , r.t.): δ 173.50 (COCH_2OH), 64.90 (COCH_2OH), 60.65 ($\text{OCH}_2\text{CH}_2\text{CH}_2\text{CH}_2\text{O}$), 25.18 ($\text{OCH}_2\text{CH}_2\text{CH}_2\text{CH}_2\text{O}$). ESI-MS calculated for $\text{C}_8\text{H}_{14}\text{O}_6\text{Na}^+$: 229.06881, observed: 229.0684.

2.4. Synthesis of 1,3-Propylene Diglycolate (GPG)

First, potassium glycolate was prepared by the reaction of glycolic acid (0.134 mol) and potassium hydrogen carbonate (0.160 mol) in water (40 mL) at r.t. for 1 h, followed by evaporation to dryness. 1,3-Dibromopropane (0.008 mol) was added to a solution of potassium glycolate (0.018 mol) in DMF (25 mL) and the mixture was stirred at 80 °C for 2 h. Then, DMF was removed from the resulting mixture under reduced pressure to yield a solid. The solid was purified by column chromatography (silica gel) using acetone as an eluent and recrystallized from acetone to give GPG as a white solid in 40% yield. ^1H NMR (500 MHz, CDCl_3 , r.t.) δ 4.26 (t, 4H, J = 6.3 Hz, $\text{OCH}_2\text{CH}_2\text{CH}_2\text{O}$), 4.17 (s, 4H, COCH_2OH), 2.32 (br, 2H, OH), 2.03 (quin, 2H, J = 6.3 Hz, $\text{CH}_2\text{CH}_2\text{CH}_2$). ^{13}C NMR (125 MHz, CDCl_3) δ 173.4 (COCH_2OH), 61.9 ($\text{OCH}_2\text{CH}_2\text{CH}_2\text{O}$), 60.7 (COCH_2OH), 27.9 ($\text{OCH}_2\text{CH}_2\text{CH}_2\text{O}$). ESI-MS calculated for $\text{C}_7\text{H}_{12}\text{O}_6\text{Na}$: 215.05261, observed: 215.05231. Anal. Calcd for $\text{C}_7\text{H}_{12}\text{O}_6$: C, 43.75; H, 6.29. Found: C, 43.88, H, 6.29.

2.5. Polycondensation of GBG and TC

A typical procedure: A Schlenk tube was charged with GBG (2.13 mmol), TC (2.13 mmol), and 1,1,2,2-tetrachloroethane (2.0 mL). Then, pyridine (2.0 mL) was added to the Schlenk tube at 0 °C and the mixture was stirred for 10 min, followed by further stirring at room temperature for 2 h to promote the polycondensation. The resulting mixture was poured into excess methanol. The precipitated polymer was collected by centrifugation and dried in vacuo to give poly(GBGT) as a white solid in 86% yield. ¹H NMR (500 MHz, CD₂Cl₄, 130 °C): δ 8.19 (s, 4H, COC₆H₄CO), 4.89 (s, 4H, COCH₂O), 4.23 (brs, 4H, OCH₂CH₂CH₂CH₂O), 1.75 (brs, 4H, OCH₂CH₂CH₂CH₂O). ¹³C NMR (125 MHz, CD₂Cl₄, 130 °C): δ 167.2 (COCH₂O), 165.0 (COC₆H₄CO), 133.8 (*ipso*-C₆H₄), 129.8 (other C₆H₄), 64.8 (COCH₂O), 61.6 (OCH₂CH₂CH₂CH₂O), 25.3 (OCH₂CH₂CH₂CH₂O).

2.6. Polycondensation of GPG and TC

A Schlenk tube was charged with GPG (2.13 mmol), TC (2.13 mmol), and 1,1,2,2-tetrachloroethane (2.0 mL). Then, pyridine (2.0 mL) was added to the Schlenk tube at 0 °C and the mixture was stirred for 10 min, followed by further stirring at room temperature for 2 h to promote the polycondensation. The resulting mixture was poured into excess methanol. The precipitated polymer was collected by centrifugation and dried in vacuo to give poly(GPGT) as a white solid in 64% yield. ¹H NMR (500 MHz, CD₂Cl₄, 130 °C): δ 8.17 (s, 4H, COC₆H₄CO), 4.89 (s, 4H, COCH₂O), 4.28 (t, 4H, OCH₂CH₂CH₂O), 2.04 (quin, 2H, OCH₂CH₂CH₂O).

2.7. Polycondensation of GBG and FC

A typical procedure: A Schlenk tube was charged with GBG (1.05 mmol) and FC (1.16 mmol). Then, pyridine (1.5 mL) was added to the Schlenk tube at 0 °C and the mixture was stirred for 10 min, followed by further stirring at 70 °C for 2 h to promote the polycondensation. The resulting mixture was poured into excess methanol. The precipitated polymer was collected by centrifugation and dried in vacuo to give poly(GBGF) as a white solid in 92% yield. ¹H NMR (500 MHz, CD₂Cl₄, 130 °C): δ 7.34 (s, 4H, COC₄H₄OCO), 4.85 (s, 4H, COCH₂O), 4.20 (brs, 4H, OCH₂CH₂CH₂CH₂O), 1.73 (brs, 4H, OCH₂CH₂CH₂CH₂O).

2.8. Polycondensation of GPG and FC

A typical procedure: A Schlenk tube was charged with GPG (0.35 mmol) and FC (0.39 mmol). Then, pyridine (0.5 mL) was added to the Schlenk tube at 0 °C for 10 min, followed by further stirring at r.t. for 2 h to promote the polycondensation. The resulting mixture was poured into excess methanol. The precipitated polymer was collected by centrifugation and dried in vacuo to give poly(GPGF) as a light brown solid in 94% yield. ¹H NMR (500 MHz, CD₂Cl₄, 130 °C): δ 7.34 (s, 4H, COC₄H₄OCO), 4.86 (s, 4H, COCH₂O), 4.26 (t, 4H, OCH₂CH₂CH₂O), 2.04 (quin, 2H, OCH₂CH₂CH₂O).

2.9. Polycondensation of GBG and AC

A typical procedure: A Schlenk tube was charged with GBG (1.71 mmol), AC (1.71 mmol), and 1,1,2,2-tetrachloroethane (1.5 mL). Then, pyridine (1.0 mL) was added to the Schlenk tube at 0 °C and the mixture was stirred for 10 min, followed by further stirring at 50 °C for 3.5 h to promote the polycondensation. The resulting mixture was poured into excess methanol. The precipitated polymer was collected by centrifugation and dried in vacuo to give poly(GBGA) as a white solid in 92% yield. ¹H NMR (500 MHz, CD₂Cl₄, 130 °C): δ 4.60 (s, 4H, COCH₂O), 4.19 (t, 4H, OCH₂CH₂CH₂CH₂O), 2.47 (t, 4H, COCH₂CH₂CH₂CH₂CO), 1.73 (m, 8H, OCH₂CH₂CH₂CH₂O and COCH₂CH₂CH₂CH₂CO).

2.10. Biodegradation of the Polymers with Seawater Monitored by Biochemical Oxygen Demand (BOD) Method

Biodegradation lab tests of the polymers in seawater were evaluated from the determination of oxygen consumption using a BOD tester (TAITEC, BOD200F, Saitama, Japan). Seawater was taken at the shoreline from the sea surface of Osaka South Port area with

a bucket. The seawater was used within one or two days. Typically, 30 mg of polymer specimen was added into each 250 mL BOD testing bottle and then 200 mL supernatant of seawater was added. Evolved carbon dioxide (CO₂) was removed using calcium hydroxide from the BOD closed system. The biodegradation tests were carried out at 27 °C with stirring for 28 days. The observed O₂ consumption volume was corrected by subtraction of the O₂ consumption volume of the control. The theoretical O₂ consumption volume was calculated according to the structural formula of each polymer assuming that degraded products are completely mineralized to CO₂. Biodegradation (%) of each polymer was calculated according to the following equation:

$$\% \text{ Biodegradation} = (\text{Observed O}_2 \text{ consumption volume} / \text{theoretical O}_2 \text{ consumption volume}) \times 100$$

Each degradation test was repeated twice and averaged.

2.11. Hydrolysis of the Polymers Monitored by TOC Method


A polymer sample (10 mg) was added to a vial filled with 2.5 mL H₂O. The reactions were carried out by shaking the vial at 45 °C for 1, 3, and 7 days separately. Finally, the solution was filtered and stored in the refrigerator (−30 °C) until the total organic carbon concentration (TOC) measurement. The weight loss was evaluated by using a TOC analyzer (Shimadzu TOC-VCSH, Kyoto, Japan).

3. Results and Discussion

3.1. Synthesis of the Polymers

3.1.1. Preparation of GBG and GPG

1,4-Butylene diglycolate (GBG) and 1,3-propylene diglycolate (GPG) were synthesized by the reaction of 1,4-dibromobutane or 1,3-dibromopentane with potassium glycolate in *N,N*-dimethylformamide (DMF), similarly to GEG (Scheme 1) [13]. After the reaction of 1,4-dibromobutane or 1,3-dibromopentane with potassium glycolate, the acetone solution of the crude product was filtrated through silica gel followed by evaporation to give GBG in 67% yield. The ¹H NMR spectrum of GBG is shown in Figure 1. GPG was purified by silica gel column chromatography and recrystallization and obtained in 40% yield (Figure S1).

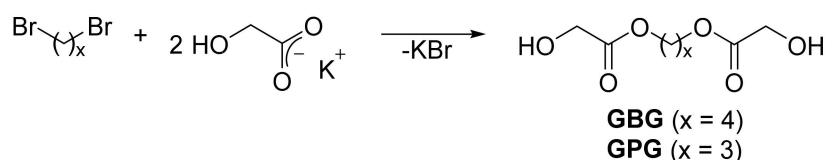


Scheme 1. Synthesis of GBG and GPG.

3.1.2. Synthesis of Poly(GBGT) and Poly(GPGT)

Similarly to the synthesis of poly(GEGT) [13], the polycondensation of GBG or GPG with terephthaloyl dichloride (TC) gave the corresponding sequence-controlled copolyesters, poly(GBGT) and poly(GPGT), respectively (Scheme 2, Table 1). The obtained poly(GBGT)s were hardly soluble in common organic solvents such as tetrahydrofuran (THF) and chloroform, so their GPC analysis was performed using 1,1,1,3,3,3-hexafluoro-2-propanol as an eluent to indicate their rather low molecular weight ($M_n \leq 2,400$). The attempted polycondensations of GBG with TC under various conditions such as different feed ratios of GBG or GPG against TC, different solvents (1,1,2,2-tetrachloroethane (TCE, DMF, dimethyl acetamide (DMAc), and dimethyl sulfoxide (DMSO)) and different temperatures did not enhance the molecular weight of the resulting poly(GBGT). The obtained poly(GPGT) (Figure S2) had a slightly higher molecular weight than that of poly(GBGT) and was also insoluble in THF but soluble in CHCl₃. The lower polymer yield of poly(GPGT) than that of poly(GBGT) should come from the higher solubility of poly(GPGT) in the precipitation solvent, MeOH. This could be attributed to the lower crystallinity of poly(GPGT)

than that of poly(GBGT) (vide infra). The ^1H and ^{13}C NMR spectra of poly(GBGT) were recorded in TCE-d_2 at 130°C as shown in Figures 2 and 3, respectively. The spectra showed four (^1H NMR) and seven (^{13}C NMR) sharp signals, respectively, indicating the regular comonomer sequence of the copolymer as expected.

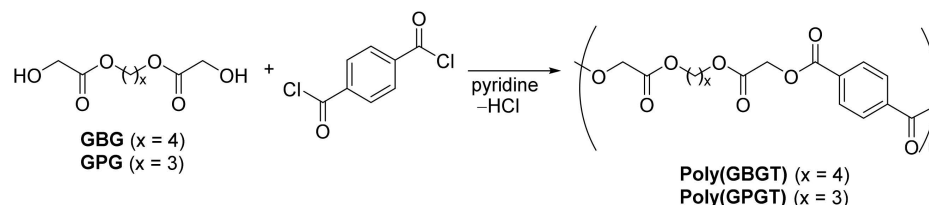

Scheme 2. Synthesis of poly(GBGT) and poly(GPGT).

Table 1. Synthesis of Poly(GBGT) and Poly(GPGT) ¹.

Run	Sample	Temp. (°C)	Yield (%)	M_n (kg mol ^{−1})	M_w/M_n
1	Poly(GBGT)	r.t.	86	2.4 ²	1.5 ²
2	Poly(GBGT)	70	89	1.5 ²	2.8 ²
3	Poly(GBGT)	100	95	1.0 ²	2.9 ²
4	Poly(GPGT)	r.t.	64	3.2 ³	3.6 ³

¹ Polymerization conditions: time = 2 h, solvent = $\text{C}_2\text{H}_2\text{Cl}_4$ (TCE), $[\text{TC}]_0 = 0.1$ M, pyridine (2 mL) was used as a base. ² Determined by GPC calibrated with poly(methyl methacrylate) standards in 1,1,1,3,3,3-hexafluoro-2-propanol (HFIP). ³ Determined by GPC calibrated with polystyrene standards in CHCl_3 .

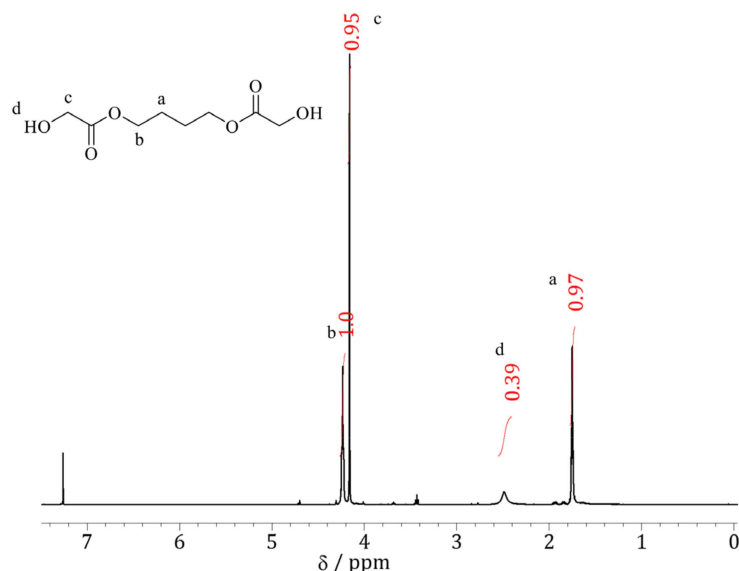


Figure 1. ^1H NMR spectrum of GBG (CDCl_3 , 500 MHz, r.t.). Red color: relative intensity.

3.1.3. Synthesis of Poly(GBGF) and Poly(GPGF)

2,5-Furandicarboxylic acid (FDCA) is currently attracting attention as a renewable bio-based chemical [20,21]. Poly(ethylene furanoate) (PEF) [22,23], poly(1,3-propylene furanoate) (PPF) [24,25], and poly(butylene furanoate) (PBF) [17] made from FDCA and ethylene glycol, 1,3-propanediol, or 1,4-butanediol, respectively, are potential alternatives to PET, PTT, and PBF having high gas-barrier properties [17,23]. Similar to the synthesis of poly(GBGT) and poly(GPGT), the polycondensation of GBG or GPG with 2,5-furandicarbonyl dichloride (FC) also gave the corresponding sequence-controlled copolyesters, poly(GBGF) and poly(GPGF), respectively (Scheme 3, Table 2, Figures S3 and S4). The obtained poly(GBGF)s were soluble in CHCl_3 , and their GPC analyses were performed using CHCl_3 as an eluent. A poly(GBGF) with relatively high molecular weight ($M_n = 14$ kg mol^{−1}) was obtained from the polycondensation

of GBG with FC at 70 °C in pyridine without additional solvent (run 7). The molecular weights of the obtained poly(GPGF)s were lower than those of poly(GBGF)s. The higher molecular weight poly(GPGF) (run 11, $M_n = 10 \text{ kg mol}^{-1}$) was obtained by re-precipitation of the lower molecular weight poly(GPGF) (run 10, $M_n = 6 \text{ kg mol}^{-1}$) in MeOH.

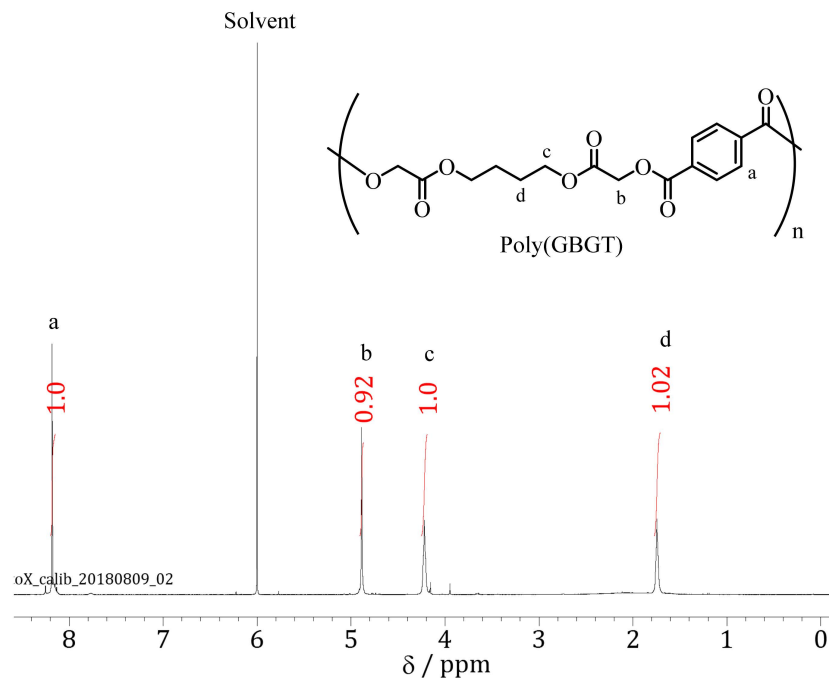


Figure 2. ^1H NMR spectrum of poly(GBGT) (Table 1, Run 1) ($\text{C}_2\text{D}_2\text{Cl}_4$, 500 MHz, 130 °C). Red color: relative intensity.


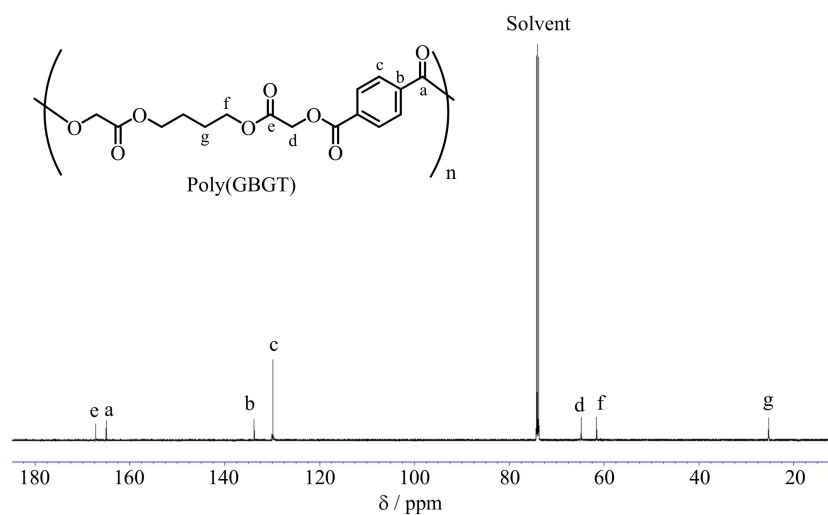


Figure 3. ^{13}C NMR spectrum of poly(GBGT) (Table 1, Run 1) ($\text{C}_2\text{D}_2\text{Cl}_4$, 125 MHz, 130 °C).

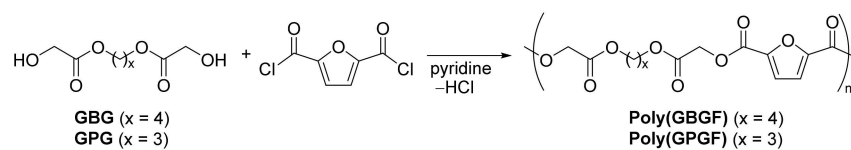

Scheme 3. Synthesis of poly(GBGF) and poly(GPGF).


Table 2. Synthesis of Poly(GBGF) and Poly(GPGF) ¹.

Run	Sample	Temp. (°C)	Yield (%)	M_n^2 (kg mol ⁻¹)	M_w/M_n^2
5	Poly(GBGF)	r.t.	79	10	1.7
6	Poly(GBGF)	50	84	11	1.6
7	Poly(GBGF)	70	92	14	1.6
8	Poly(GBGF)	100	19	2	1.8
9 ³	Poly(GPGF)	r.t.	92	4	1.4
10	Poly(GPGF)	r.t.	94	6	1.9
11 ⁴	Poly(GPGF)	-	72	10	1.2

¹ Polymerization conditions: FC = 0.23–0.33 g, [GXG]₀: [FC]₀ = 1: 1.1, time = 2 h, solvent = pyridine (2 mL) was used as a base. ² Determined by GPC calibrated with polystyrene standards in CHCl₃. ³ Polymerization conditions: temp = r.t., time = 2 h, solvent = C₂H₂Cl₄ (TCE), [FC]₀ = 0.1 M, pyridine (2 mL) was used as a base. ⁴ Obtained by the reprecipitation of the poly(GPGF) sample (run 10) in MeOH.

3.1.4. Synthesis of Poly(GBGA)

Because aliphatic polyesters tend to show higher biodegradability than aromatic polyesters in general, the polycondensation reaction of GBG with adipoyl dichloride was also performed to produce poly(GBGA) using TCE as a solvent (Scheme 4, Table 3, Figure S5). The polymerization was conducted at r.t., 50 °C, and 70 °C, and produced poly(GBGA) with the highest molecular weight (M_n) of 21 kg mol⁻¹ in the highest yield at 50 °C. The polycondensation of GBG and adipoyl dichloride at 70 °C resulted in a much lower yield than that at 50 °C and gave an orange-colored polymer with lower molecular weight, suggesting some side reactions at 70 °C.

**Scheme 4.** Synthesis of poly(GBGA).**Table 3.** Synthesis of Poly(GBGA) ¹.

Run	Temp. (°C)	Time (h)	Yield (%)	M_n^2 (kg mol ⁻¹)	M_w/M_n^2
11	r.t.	2	70	8	1.5
12	50	2	84	21	1.5
13	50	3.5	92	21	1.5
14	70	2	19	17	1.5

¹ Polymerization conditions: AC = 0.22–0.27 g (1.07 mmol–1.31 mmol), [GBG]₀: [AC]₀ = 1: 1, [GBG]₀ = 1.0 M, Solvent = C₂H₂Cl₄ (TCE), pyridine (2 mL) was used as a base. ² Determined by GPC calibrated with polystyrene standard in THF.

3.2. Thermal Properties of the Polymers

The thermal properties of the obtained copolyesters were evaluated by DSC analysis, summarized in Table 4, which includes the data of the reported poly(GEGT), poly(GEGF), and poly(GEGA) [13] for comparison.

Among the terephthalate polymers, poly(GBGT) showed T_m at 202 °C, which is similar to those of homopolymers PGA (around 220 °C [26,27]) and PBT (around 225 °C [28,29]). In general, random copolymers tend to show lower T_m than each homopolymer [10]. We believe that the regular sequence of poly(GBGT) should contribute to its relatively high T_m . In contrast, the T_m of poly(GPGT) was observed at 121 °C, which is significantly lower than those of the poly(GBGT) and poly(GEGT) (209 °C) [13]. The ΔH_m value of the poly(GPGT) (12 J/g) was also lower than those of the poly(GBGT) (28 J/g) and poly(GEGT) (20 J/g). These results indicate that the crystallinity of the poly(GPGT) is lower than those of the poly(GBGT) and poly(GEGT). We speculate that these data suggest the odd–even

effect of the diol carbon numbers (“x” in Schemes 1–4) on their crystallization, where the polymers with diols composed of even number carbon atoms tend to have higher T_m than odd ones [14,15]. It is notable that the poly(GBGT) showed a melting transition also in the second heating scan (Figure S6) in contrast to the poly(GEGT) [13] and poly(GPGT) (Figure S7) showing no melting transition in the second heating scan, indicating a faster crystallization rate of the poly(GBGT) than those of the poly(GEGT) and poly(GPGT). The T_g values of these polymers were lowered with an increased diol carbon number, where the T_g of poly(GBGT) (9 °C) was lower by 39 °C than that of poly(GEGT) (48 °C).

Table 4. Comparison of thermal properties of the sequence-controlled copolyesters having different diol units.

Run	Sample	x	M_n^1 (kg mol ^{−1})	M_w/M_n^1	T_g^2 (°C)	T_m^2 (°C)	ΔH_m^2 (J/g)
1	Poly(GBGT)	4	2.4	1.5	9	202	28
4	Poly(GPGT)	3	3.2	3.6	33	121	12
-	Poly(GEGT) [13]	2	8.1	2.4	48	209	20
7	Poly(GBGF)	4	14	1.6	34	93	50
11	Poly(GPGF)	3	10	1.2	43	n.d. ³	n.d. ³
-	Poly(GEGF) [13]	2	17	3.8	68	127	14
12	Poly(GBGA)	4	21	1.5	−31	72	21
-	Poly(GEGA) [13]	2	6.5	1.8	13	67,77	13

¹ Determined by GPC. ² Determined by DSC. The T_m and ΔH_m were read from the first heating scan, while the T_g was read from the second heating scan. ³ Not detected.

The poly(GBGF), which contains 67 mol% of glycolate units, showed T_m at 93 °C (Figure S8). In sharp contrast, the reported random copolymer with a similar composition (glycolate-content = 60 mol%) did not show T_m [30,31]. Thus, the regular sequence of the poly(GBGF) enhanced its crystallinity. The T_m of the poly(GBGF) is lower than those of PGA, PBF (around 170 °C) [17,32,33], and poly(GEGF) (127 °C) [13]. In contrast to the poly(GBGF), poly(GEGF), and reported PPF (T_m = 170–180 °C) [24,25], the poly(GPGF) showed no melting transition, indicating its amorphous nature (Figure S9). These results should also suggest the odd–even effect of the diol carbon numbers (“x” in Schemes 1–4) on their crystallization behaviors. The T_g values of these polymers also decreased with increasing the diol carbon number, where the T_g of poly(GBGF) (33 °C) was lower by 35 °C than that of poly(GEGF) (68 °C).

The poly(GBGA) showed T_m at 72 °C (Figure S10), similar to those of poly(GEGA) (67 and 77 °C) [4] and higher than that of PBA (around 57 °C) [34,35]. These results are in sharp contrast to the fact that the corresponding random copolymer of poly(butylene adipate-co-glycolic acid) with similar composition (glycolate-content = 60 mol%) was reported to have no crystallinity [36]. The T_g of poly(GBGA) (−31 °C) was also lower by 42 °C than that of poly(GEGA) (13 °C) [13].

3.3. Biodegradability of the Polymers

Marine pollution by microplastics is one of the most concerning environmental problems [37,38]. While it is important to prevent plastic runoff by recycling, the use of biodegradable polymers should be effective for applications where recycling is difficult. From this background, the polymers biodegradable in seawater are attracting current attention [39]. Poly(3-hydroxyalkanoate)s such as poly(3-hydroxybutyrate) (PHB), poly(3-hydroxybutyrate-co-3-hydroxyvalerate) (PHBV), and poly(3-hydroxybutyrate-co-3-hydroxyhexanoate) (PHBH) are known for their high biodegradability in seawater, showing almost complete degradation within several weeks [40,41].

The biodegradation tests in seawater were performed using the samples of poly(GBGF) (run 5), poly(GPGF) (run 10), and poly(GBGA) (run 12) at 27 °C (Figure 4). For comparison, purchased PGA (M_n = 38 kg/mol, M_w/M_n = 2.6) and separately synthesized PBF (M_n = 27 kg/mol, M_w/M_n = 1.6) and PBA (M_n = 12 kg/mol, M_w/M_n = 1.3) were also

tested. Because of their very low molecular weights, poly(GBGT) and poly(GPGT) were not used in the biodegradation tests. The degradation degrees in these tests were evaluated by the biochemical oxygen demand (BOD) measurements.

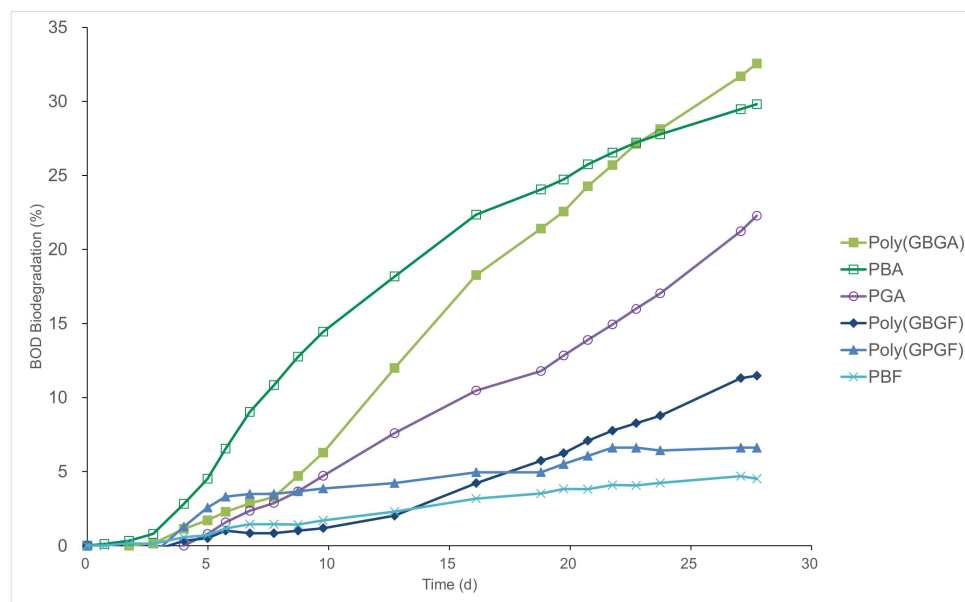


Figure 4. Biodegradation (BOD) of the homo- and copolyesters in seawater at 27 °C.

The poly(GBGF) and poly(GPGF) samples exhibited 11.5% and 6.5% biodegradation after 28 days, respectively, which are intermediate between those of PGA (22.3%) and PBF (4.5%). Therefore, the biodegradability of the poly(GBGF) and poly(GPGF) were improved in comparison with PBF by the introduction of glycolate units. The poly(GBGF) and poly(GPGF) have higher biodegradability than representative biodegradable copolyester, poly(butylene adipate-*co*-terephthalate) (PBAT), which was reported to show the BOD biodegradation of around 1% after 4 weeks in similar laboratory tests [41], although lower than that of poly(GEGT), which showed a biodegradation of 30% within 29 days [13]. The slow but certain biodegradation of the PBF homopolymer sample was observed, possibly due to its relatively low molecular weight. PBA was reported to show higher biodegradability in seawater than poly(butylene succinate) and poly(ethylene succinate) [40]. The poly(GBGA) sample showed a high biodegradation of 32.6% after 28 days similar to that of PBA (29.8%). The slower biodegradation of the PGA than those of the PBA and poly(GBGA) samples could come from the higher molecular weight of the used PGA sample.

PGA has high hydrolyzability, which leads to its high biodegradability and also to low stability in ambient conditions to limit its applications [3,4]. Figure 5 shows the results of the hydrolysis tests of these polymers at 45 °C. The degradation degrees in these tests were determined from the total organic carbon (TOC) measurement of the supernatant solution. The weight loss on the first day is assumed to be due to the elution of the originally contained water-soluble low molecular weight components. Table 5 shows the difference in the weight loss between the first day and the seventh day as an index of hydrolyzability. Among these polymers, PGA showed a much higher hydrolyzability of 7.4% than other polymers despite its higher molecular weight. The poly(GBGF) and poly(GPGF) with furandicarboxylic acid units showed low hydrolyzability of 1.3% and 0.8%, respectively. Poly(GBGA) showed slightly higher hydrolyzability (2.0%) than poly(GBGF) and poly(GPGF) but still much lower than PGA. Thus, the poly(GBGF), poly(GPGF), and poly(GBGA) have improved stability in comparison with PGA. PBA and poly(GBGA) have both high biodegradability in seawater and low hydrolyzability. The corresponding random copolymer of poly(butylene adipate-*co*-glycolic acid) with a similar composition (glycolate-content = 60 mol%) was reported to show higher hydrolyzability than PGA [26]. We speculate that the lack of con-

tinuous glycolate units in the poly(GBGA) should contribute to its lower hydrolyzability. Thus, the controlled incorporation of glycolate units into copolyesters realized both the suppression of hydrolysis as well as improved biodegradability.

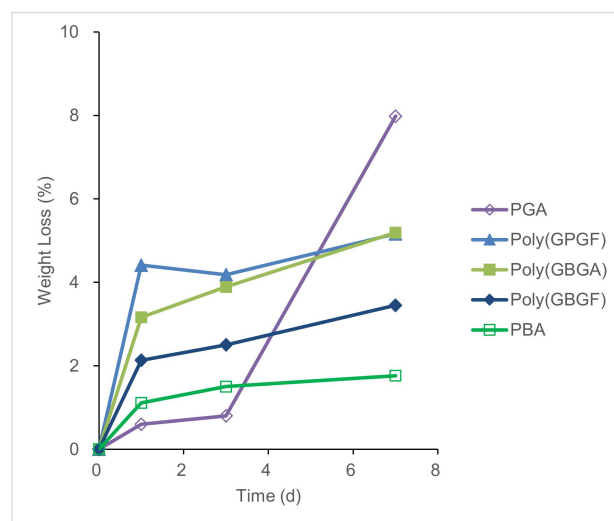


Figure 5. Hydrolytic degradation of the homo- and copolyesters at 45 °C.

Table 5. Differences in hydrolysis degree between the first day and the seventh day.

Polymer	Differences in Weight Loss between the First Day and Seventh Day (%)
Poly(GBGF)	1.3
Poly(GPGF)	0.8
PGA	7.4
Poly(GBGA)	2.0
PBA	0.7

4. Conclusions

Novel sequence-controlled copolyesters composed of glycolic acid, 1,4-butanediol or 1,3-propanediol, and dicarboxylic acids were synthesized from the polycondensation of alkylene diglycolate and the chloride of the corresponding dicarboxylic acid. The T_m of the poly(GBGT) (202 °C) is comparable to that of poly(GEGT) and higher than that of the poly(GPGT) (121 °C), suggesting an odd–even effect of the diol carbon numbers on their crystallization properties. In contrast to the fact that the corresponding random copolymers are amorphous, the poly(GBGF) showed T_m at 90 °C, indicating its enhanced crystallinity by its regular sequence. Biodegradation tests in seawater showed that poly(GBGF) and poly(GPGF) have intermediate biodegradability between PGA and PBF. poly(GBGA) showed high seawater-biodegradability, similar to PBA. On the other hand, the hydrolysis of poly(GBGF), poly(GPGF), and poly(GBGA) was slower than that of PGA. Thus, these sequence-controlled copolyesters have both improved biodegradability compared to PBF and lower hydrolyzability than PGA.

Supplementary Materials: The following supporting information can be downloaded at: <https://www.mdpi.com/article/10.3390/polym15051155/s1>, Figure S1: ¹H NMR spectrum of GPG (CDCl₃, 500 MHz, r.t.). Figure S2: ¹H NMR spectrum of poly(GPGT) (run 4) (CDCl₃, 500 MHz, r.t.). Figure S3: ¹H NMR spectrum of poly(GBGF) (Run 5) (CDCl₃, 500 MHz, r.t.). Figure S4: ¹H NMR spectrum of poly(GPGF) (Run 9) (CDCl₃, 500 MHz, r.t.). Figure S5: ¹H NMR spectrum of spectrum of poly(GBGA) (Run 14) (CDCl₃, 500 MHz, r.t.). Figure S6: DSC profiles of poly(GBGT) (Run 1). Figure S7: DSC profiles of poly(GPGT) (Run 4). Figure S8: DSC profiles of poly(GBGF) (Run 7). Figure S9: DSC profiles of poly(GPGF) (Run 11). Figure S10: DSC profiles of poly(GBGA) (Run 12).

Author Contributions: Conceptualization, Y.N.; methodology, Y.N., R.T., T.S. and A.N.; investigation, K.F., Y.K., N.K., N.Y. and A.N.; resources, Y.N., R.T., T.S. and A.N.; data curation, Y.N., K.F. and Y.K.; writing—original draft preparation, Y.N., K.F. and Y.K.; writing—review and editing, Y.N.; visualization, Y.N., K.F. and Y.K.; supervision, Y.N. and T.S.; project administration, Y.N. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Institutional Review Board Statement: Not applicable.

Data Availability Statement: The data presented in this study are available on request from the corresponding author.

Conflicts of Interest: The authors declare no conflict of interest. The funders had no role in the design of the study; in the collection, analyses, or interpretation of data; in the writing of the manuscript; or in the decision to publish the results.

References

1. Castro-Aguirre, E.; Iñiguez-Franco, F.; Samsudin, H.; Fang, X.; Auras, R. Physical and mechanical properties of PLA, and their functions in widespread applications—A comprehensive review. *Adv. Drug Deliv. Rev.* **2016**, *107*, 367–392. [\[CrossRef\]](#)
2. Garlotta, D. A Literature Review of Poly(Lactic Acid). *J. Polym. Environ.* **2001**, *9*, 63–84. [\[CrossRef\]](#)
3. Jem, K.J.; Tan, B. The development and challenges of poly(lactic acid) and poly(glycolic acid). *Adv. Ind. Eng. Polym. Res.* **2020**, *3*, 60–70. [\[CrossRef\]](#)
4. Samantaray, P.K.; Little, A.; Haddleton, D.M.; McNally, T.; Tan, B.; Sun, Z.; Huang, W.; Ji, Y.; Wan, C. Poly(glycolic acid) (PGA): A versatile building block expanding high performance and sustainable bioplastic applications. *Green Chem* **2020**, *22*, 4055–4081. [\[CrossRef\]](#)
5. Shah, A.A.; Kato, S.; Shintani, N.; Kamini, N.R.; Nakajima-Kambe, T. Microbial degradation of aliphatic and aliphatic-aromatic co-polyesters. *Appl. Microbiol. Biotechnol.* **2014**, *98*, 3437–3447. [\[CrossRef\]](#)
6. Kijchavengkul, T.; Auras, R.; Rubino, M.; Selke, S.; Ngouajio, M.; Fernandez, R.T. Biodegradation and hydrolysis rate of aliphatic aromatic polyester. *Polym. Degrad. Stab.* **2010**, *95*, 2641–2647. [\[CrossRef\]](#)
7. Jian, J.; Xiangbin, Z.; Xianbo, H. An overview on synthesis, properties and applications of poly(butylene-adipate-co-terephthalate)–PBAT. *Adv. Ind. Eng. Polym. Res.* **2020**, *3*, 19–26. [\[CrossRef\]](#)
8. Olewnik, E.; Czerwiński, W.; Nowaczyk, J.; Sepulchre, M.-O.; Tessier, M.; Salhi, S.; Fradet, A. Synthesis and structural study of copolymers of l-lactic acid and bis(2-hydroxyethyl terephthalate). *Eur. Polym. J.* **2007**, *43*, 1009–1019. [\[CrossRef\]](#)
9. Gara, M.B.; Kammoun, W.; Delaite, C.; Abid, S. Synthesis and Characterization of Aliphatic-Aromatic Copolyesters PET-PLA From PET Waste and Lactide. *J. New Technol. Mater.* **2016**, *6*, 42–48. [\[CrossRef\]](#)
10. Olewnik, E.; Czerwinski, W. Synthesis, structural study and hydrolytic degradation of copolymer based on glycolic acid and bis-2-hydroxyethyl terephthalate. *Polym. Degrad. Stab.* **2009**, *94*, 221–226. [\[CrossRef\]](#)
11. Ding, Y.; Wang, J.; Luo, C.; Yao, B.; Dong, L.; Du, X.; Ji, J. Modification of poly(butylene succinate) with biodegradable glycolic acid: Significantly improved hydrolysis rate retaining high toughness property. *J. Appl. Polym. Sci.* **2022**, *139*, 52106. [\[CrossRef\]](#)
12. Tian, W.; Tu, Z.; Liu, L.; Wei, Z. A comparative study of glycolic acid and L-lactic acid on modification of poly(butylene succinate). *Polym. Degrad. Stab.* **2022**, *206*, 110194. [\[CrossRef\]](#)
13. Nakayama, Y.; Yagumo, W.; Tanaka, R.; Shiono, T.; Inumaru, K.; Tsutsumi, C.; Kawasaki, N.; Yamano, N.; Nakayama, A. Synthesis, properties and biodegradation of periodic copolyesters composed of hydroxy acids, ethylene glycol, and terephthalic acid. *Polym. Degrad. Stab.* **2020**, *174*, 109095. [\[CrossRef\]](#)
14. Bunn, C.W. The melting points of chain polymers. *J. Polym. Sci. Part B Polym. Phys.* **1996**, *34*, 799–819. [\[CrossRef\]](#)
15. Zhou, C.; Wei, Z.; Yu, Y.; Shao, S.; Leng, X.; Wang, Y.; Li, Y. Biobased long-chain aliphatic polyesters of 1,12-dodecanedioic acid with a variety of diols: Odd-even effect and mechanical properties. *Mater. Today Commun.* **2019**, *19*, 450–458. [\[CrossRef\]](#)
16. Tsanaktsis, V.; Terzopoulou, Z.; Nerantzaki, M.; Papageorgiou, G.Z.; Bikiaris, D.N. New poly(pentylene furanoate) and poly(heptylene furanoate) sustainable polyesters from diols with odd methylene groups. *Mater. Lett.* **2016**, *178*, 64–67. [\[CrossRef\]](#)
17. Zhu, J.; Cai, J.; Xie, W.; Chen, P.-H.; Gazzano, M.; Scandola, M.; Gross, R.A. Poly(butylene 2,5-furan dicarboxylate), a Biobased Alternative to PBT: Synthesis, Physical Properties, and Crystal Structure. *Macromolecules* **2013**, *46*, 796–804. [\[CrossRef\]](#)
18. Nikolic, M.S.; Djonlagic, J. Synthesis and characterization of biodegradable poly(butylene succinate-co-butylene adipate)s. *Polym. Degrad. Stab.* **2001**, *74*, 263–270. [\[CrossRef\]](#)
19. Gomes, M.; Gandini, A.; Silvestre, A.J.D.; Reis, B. Synthesis and characterization of poly(2,5-furan dicarboxylate)s based on a variety of diols. *J. Polym. Sci. Part A Polym. Chem.* **2011**, *49*, 3759–3768. [\[CrossRef\]](#)
20. Bozell, J.J.; Petersen, G.R. Technology development for the production of biobased products from biorefinery carbohydrates—The US Department of Energy’s “Top 10” revisited. *Green Chem.* **2010**, *12*, 539–554. [\[CrossRef\]](#)
21. Dutta, S.; De, S.; Saha, B. A Brief Summary of the Synthesis of Polyester Building-Block Chemicals and Biofuels from 5-Hydroxymethylfurfural. *ChemPlusChem* **2012**, *77*, 259–272. [\[CrossRef\]](#)

22. Gandini, A.; Silvestre, A.J.D.; Neto, C.P.; Sousa, A.F.; Gomes, M. The furan counterpart of poly(ethylene terephthalate): An alternative material based on renewable resources. *J. Polym. Sci. Part A Polym. Chem.* **2009**, *47*, 295–298. [\[CrossRef\]](#)
23. Burgess, S.K.; Leisen, J.E.; Kraftschik, B.E.; Mubarak, C.R.; Kriegel, R.M.; Koros, W.J. Chain Mobility, Thermal, and Mechanical Properties of Poly(ethylene furanoate) Compared to Poly(ethylene terephthalate). *Macromolecules* **2014**, *47*, 1383–1391. [\[CrossRef\]](#)
24. Vannini, M.; Marchese, P.; Celli, A.; Lorenzetti, C. Fully biobased poly(propylene 2,5-furandicarboxylate) for packaging applications: Excellent barrier properties as a function of crystallinity. *Green Chem.* **2015**, *17*, 4162–4166. [\[CrossRef\]](#)
25. Papageorgiou, G.Z.; Papageorgiou, D.G.; Tsanaktsis, V.; Bikiaris, D.N. Synthesis of the bio-based polyester poly(propylene 2,5-furan dicarboxylate). Comparison of thermal behavior and solid state structure with its terephthalate and naphthalate homologues. *Polymer* **2015**, *62*, 28–38. [\[CrossRef\]](#)
26. Starkweather, H.W., Jr.; Avakian, P.; Fontanella, J.J.; Wintersgill, M.C. Internal motions in polylactide and related polymers. *Macromolecules* **1993**, *26*, 5084–5087. [\[CrossRef\]](#)
27. Tao, D.; Higaki, Y.; Ma, W.; Wu, H.; Shinohara, T.; Yano, T.; Takahara, A. Chain orientation in poly(glycolic acid)/halloysite nanotube hybrid electrospun fibers. *Polymer* **2015**, *60*, 284–291. [\[CrossRef\]](#)
28. Rodríguez, J.L.; Eguiazabal, J.I.; Nazabal, J. Phase Behavior and Interchange Reactions in Poly(butylene terephthalate)/Poly(ester-carbonate) Blends. *Polym. J.* **1996**, *28*, 501–506. [\[CrossRef\]](#)
29. Guo, M.; Zachmann, H.G. Structure and Properties of Naphthalene-Containing Polyesters. 2. Miscibility Studies of Poly(ethylene naphthalene-2,6-dicarboxylate) with Poly(butylene terephthalate) by ¹³C CP/MAS NMR and DSC. *Macromolecules* **1997**, *30*, 2746–2750. [\[CrossRef\]](#)
30. Hu, H.; Zhang, R.; Wang, J.; Ying, W.B.; Shi, L.; Yao, C.; Kong, Z.; Wang, K.; Zhu, J. A mild method to prepare high molecular weight poly(butylene furandicarboxylate-co-glycolate) copolyesters: Effects of the glycolate content on thermal, mechanical, and barrier properties and biodegradability. *Green Chem.* **2019**, *21*, 3013–3022. [\[CrossRef\]](#)
31. Ding, Y.; Huang, D.; Ai, T.; Zhang, C.; Chen, Y.; Luo, C.; Zhou, Y.; Yao, B.; Dong, L.; Du, X.; et al. Different Aquatic Environments for Water Degradation Application. *ACS Sustain. Chem. Eng.* **2021**, *9*, 1254–1263. [\[CrossRef\]](#)
32. Zhou, W.; Zhang, Y.; Xu, Y.; Wang, P.; Gao, L.; Zhang, W.; Ji, J. Synthesis and characterization of bio-based poly(butylene furandicarboxylate)-b-poly(tetramethylene glycol) copolymers. *Polym. Degrad. Stab.* **2014**, *109*, 21–26. [\[CrossRef\]](#)
33. Jiang, M.; Liu, Q.; Zhang, Q.; Ye, C.; Zhou, G. A series of furan-aromatic polyesters synthesized via direct esterification method based on renewable resources. *J. Polym. Sci. Part A Polym. Chem.* **2012**, *50*, 1026–1036. [\[CrossRef\]](#)
34. Sonnenschein, M.F.; Lysenko, Z.; Brune, D.A.; Wendt, B.L.; Schrock, A.K. Enhancing polyurethane properties via soft segment crystallization. *Polymer* **2005**, *46*, 10158–10166. [\[CrossRef\]](#)
35. Minke, R.; Blackwell, J. Single crystals of poly(tetramethylene adipate). *J. Macromol. Sci. Part B Phys.* **1980**, *18*, 233–255. [\[CrossRef\]](#)
36. Soulis, S.; Triantou, D.; Weidner, S.; Falkenhagen, J.; Simitzis, J. Structural analysis of biodegradable low-molecular mass copolyesters based on glycolic acid, adipic acid and 1,4 butanediol and correlation with their hydrolytic degradation. *Polym. Degrad. Stab.* **2012**, *97*, 2091–2103. [\[CrossRef\]](#)
37. Isobe, A.; Iwasaki, S.; Uchida, K.; Tokai, T. Abundance of non-conservative microplastics in the upper ocean from 1957 to 2066. *Nat. Commun.* **2019**, *10*, 417. [\[CrossRef\]](#)
38. Lim, X. Microplastics are everywhere—But are they harmful? *Nature* **2021**, *593*, 22–25. [\[CrossRef\]](#)
39. Wang, G.-X.; Huang, D.; Ji, J.-H.; Völker, C.; Wurm, F.R. Seawater-Degradable Polymers—Fighting the Marine Plastic Pollution. *Adv. Sci.* **2021**, *8*, 2001121. [\[CrossRef\]](#)
40. Kasuya, K.-I.; Takagi, K.-I.; Ishiwatari, S.-I.; Yoshida, Y.; Doi, Y. Biodegradabilities of various aliphatic polyesters in natural waters. *Polym. Degrad. Stab.* **1998**, *59*, 327–332. [\[CrossRef\]](#)
41. Nakayama, A.; Yamano, N.; Kawasaki, N. Biodegradation in seawater of aliphatic polyesters. *Polym. Degrad. Stab.* **2019**, *166*, 290–299. [\[CrossRef\]](#)

Disclaimer/Publisher’s Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.