applied sciences

MDPI

Review

Strength, Durability, and Aesthetics of Corner Joints and Edge Banding in Furniture Design: A Review

Zoran Vlaović, Tomislav Gržan *, Ivica Župčić, Danijela Domljan and Goran Mihulja

Faculty of Forestry and Wood Technology, University of Zagreb, 10000 Zagreb, Croatia; zvlaovic@sumfak.unizg.hr (Z.V.); izupcic@sumfak.unizg.hr (I.Ž.); ddomljan@sumfak.unizg.hr (D.D.); gmihulja@sumfak.unizg.hr (G.M.)

* Correspondence: tgrzan@sumfak.unizg.hr

Abstract: Corner joints and edge banding are essential components that significantly impact the strength, durability, and aesthetic appeal of particleboard furniture. This review examines the critical role of edge banding in enhancing the performance of corner joints, which are fundamental to the overall quality of panel furniture. A targeted literature search was conducted across key databases, including the Web of Science Core Collection (WoS CC), Scopus, and Google Scholar, focusing on scientific resources in the technical and biotechnical sciences. The selection of joint types, materials, and construction methods can substantially influence both the structural integrity and visual design of the furniture. Well-designed corner joints improve durability and longevity by ensuring that furniture can withstand various forces and loads without failure or deformation. These joints enhance the aesthetics of furniture by providing seamless and visually appealing connections between different elements. Edge banding is vital for reinforcing corner joint strength, as different materials exhibit varying degrees of resistance to impact, scratches, and abrasion, thereby safeguarding furniture surfaces. Also, edge banding contributes to the furniture's longevity, ensuring durability during use as well as through disassembly and transport during remodeling or relocation. This review aims to consolidate existing knowledge and establish parameters for future research on the quality and performance of corner joints and edge bands in particleboard furniture.

Keywords: edge banding; corner joints; furniture design; strength; durability; aesthetics; particleboard; glue

check for updates

Citation: Vlaović, Z.; Gržan, T.; Župčić, I.; Domljan, D.; Mihulja, G. Strength, Durability, and Aesthetics of Corner Joints and Edge Banding in Furniture Design: A Review. *Appl. Sci.* **2024**, *14*, 10285. https://doi.org/10.3390/app142210285

Academic Editor: Stefano Invernizzi

Received: 9 October 2024
Revised: 28 October 2024
Accepted: 1 November 2024
Published: 8 November 2024

Copyright: © 2024 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (https://creativecommons.org/licenses/by/4.0/).

1. Introduction

Corner joints and edge bandings play a key role in the overall quality of furniture made from particleboards, especially in improving the strength, aesthetics, protection, and structural integrity of the furniture. The choice of joint type, materials, and construction techniques can significantly influence the overall appearance and design of the furniture. Therefore, paying attention to the strength and aesthetics of corner joints and edge bands is essential for creating high-quality, visually pleasing furniture. They are the primary connection points between different components, such as panels and frames, and are responsible for providing rigidity and structural integrity to the furniture.

The quality and design of corner joints directly affect the durability and longevity of furniture. Strong and well-designed corner joints ensure that furniture can withstand various forces and loads without failure or deformation. In addition, corner joints contribute to the aesthetics of furniture by providing seamless and visually appealing connections between different elements.

Edge banding plays a crucial role in influencing the strength of corner joints in the furniture. Jivkov [1] highlighted that edge banding affects the bending strength of the end-corner joints in particleboard furniture. Cai and Wang [2] emphasized that the stiffness of corner joints in furniture is influenced by edge banding, as discussed in research on case

furniture. Factors such as the type, thickness, and material of edge banding, as well as the gluing parameters, angularity of boards, and panel properties, all contribute to determining the overall quality of joints in furniture.

The choice of edge banding materials, such as polyvinyl chloride (PVC), melamine, or wood veneers, can affect the overall look and feel of furniture [3]. It is used to cover the exposed sides of wood materials such as plywood, particleboard, and medium-density fiberboard (MDF), giving the appearance of a solid or more valuable material [4]. Miškinytė and Juknelevičius [5] highlight the importance of edge banding materials and their thickness in improving the quality of furniture. Zhou et al. [4] identified potential factors leading to edge banding cracking in panel furniture, emphasizing the need for proper wood moisture content and adhesives. Different edge banding materials have varying levels of resistance to impacts, scratches, and abrasion, providing protection to the furniture surface. Edge banding helps to suppress the absorption of water and humidity, preventing damage to furniture [5,6], which is especially pronounced when using laser technology [7]. For some materials, such as particleboard, which has a lower resistance to delamination, the presence of some edge material certainly increases this resistance, but also increases the resistance of the edge to impact, preventing damage to the edge when assembling/disassembling furniture. Even so, if the strength of edge banding (edge material and its bonding to the base material) is sufficiently high, it can also be expected to strengthen the joints and corners of the furniture, improving its structural integrity. Overall, edge banding not only enhances the visual appeal of furniture but also ensures its durability and longevity.

Studies have specifically examined the effects of adhesives, wood species, and modifications on the withdrawal strength and durability of dowels and their interactions with wood composite materials [8–13]. Research includes the impact of dowel materials, diameter, and direction of withdrawal strength, particularly the withdrawal strength from the faces and edges of materials, such as MDF and particleboard, highlighting the influence of material properties and manufacturing processes. The polyurethane adhesive (PUR-D4) demonstrated a higher embedded strength than polyvinyl acetate (PVAC-D4), with PUR-D4 expanding to fill gaps and enhance mechanical adhesion [12,13]. According to the above-mentioned papers, respecting the mutual differences of the experiments, beech dowels exhibited the highest embedded strength, attributed to the density and structural properties of the wood, while Scots pine dowels showed lower strength due to their lower density and structural characteristics. The thickness of PVC edge banding significantly influenced embedded strength, with 0.8 mm thickness showing superior performance over 1 mm and 2 mm thicknesses, suggesting that thinner edge banding may provide better adhesion and mechanical strength.

This study aims to review previous research and highlight the importance of using edge banding on corner joints to increase the strength, visual aesthetics, protection, and structural integrity of furniture made of wooden panels, especially particleboards. The purpose of the analysis of previous research was to unify the knowledge and set parameters for further research on the quality of corner joints and edge bands on wooden panels and furniture made of particleboards.

Also, this study represents the first phase of research within the project “The role of edge covering in the aesthetic and technical improvement of panel furniture”, which is carried out at the Faculty of Forestry and Wood Technology University of Zagreb, funded by the Ministry of Science and Education, Republic of Croatia.

2. Methods

A targeted literature search was conducted across key databases, including the Web of Science Core Collection (WoS CC), Scopus, and Google Scholar, focusing on scientific resources in the technical and biotechnical sciences. The search strategy employed both controlled vocabulary and keywords, with the main search concepts being “edge-banding”, “corner joints”, “corner joint visual design”, “particleboard”, and “adhesive application techniques”. No filters were applied to limit the retrieval by study type, but editorials,

letters, newspaper articles, and opinion pieces were excluded. Where possible, the search was restricted to English-language documents published between 1993 and 2024.

A single reviewer screened and selected studies. Initially, titles and abstracts were scrutinized, and potentially relevant articles were retrieved for further analysis. Full-text articles were then evaluated based on the inclusion criteria outlined in Table 1. Articles were excluded if they did not meet the selection criteria described in Table 1, were duplicate publications, or were published prior to 1993.

Table 1. Studies selection criteria.

Criteria	Description
Subject	Furniture design studies or material sciences, specifically focusing on edge banding and corner joints in wood materials, including particleboard, medium-density fiberboard (MDF), and similar materials used in furniture design and manufacturing.
Intervention	Studies examining the application of edge banding techniques and adhesive methods to corner joints, specifically aimed at improving visual design and structural stability in wood-based materials.
Comparator	Studies comparing traditional or alternative methods of edge banding and adhesive application to untreated wood or particleboard edges, including various techniques for edge banding and corner joints or variations in adhesive methods.
Outcomes	Measures of adhesive performance, edge banding durability, aesthetic quality of corner joints, structural integrity, and ease of application during manufacturing, including strength, durability, adhesion quality, and overall effectiveness in furniture design
Study design	Experimental studies, case studies, technical reports, and systematic reviews relevant to adhesive and edge banding technology, including design comparisons and investigations specifically focused on edge banding and corner joints.

3. Results and Discussion

In the analysis, the studies that dealt with the research on corner joints and those that described the research results on edge banding were separated. Although corner joints and edge bands in particleboard furniture are often interdependent, most studies separate these two concepts, and research rarely unites them to achieve interdisciplinary parameters of aesthetics and overall product quality. Therefore, the articles were first divided into two groups: those that investigated the parameters and application of edge bands (e.g., studies that investigated the influence of particleboard processing on the joint with the edge band, the influence of the type of glue, and the technique of applying glue on the quality of the glued joint), and studies that dealt with the research of corner joints (e.g., investigate the influence of different types of corner joints and numerous factors on the overall strength, load-bearing capacity, and durability of particleboard furniture, or investigate the influence of the design of corner joints on the visual appeal of particleboard furniture). Finally, key points and cluster possibilities for further research are discussed.

Several types of corner joints are commonly used in furniture construction, such as dowel joints, biscuit joints, confirmat screw joints, and cam lock joints. The type of joint, such as dowel joints, and factors such as dowel size and edge banding thickness are crucial for furniture strength. Dowel joints connect elements with wooden dowels and glue to provide a strong and durable joint. A biscuit joint is a type of joinery technique that involves connecting furniture elements with oval-shaped solid beech wood biscuits inserted in slots and glued with the ability to create strong, invisible joints. Confirmat screw joints using specialized screws were inserted into the pre-drilled holes to provide a secure connection. Each type of joint has advantages and considerations, such as the materials being joined, the desired strength and durability, and the aesthetic preferences of the furniture manufacturer. The factors known to influence corner joint strength include the type of joint, adhesive used, and base material. Different types of joints, such as single-dowel, double-gluing, and

grooved-dowel joints, can significantly affect the strength of the joints. The use of proper adhesives and gluing techniques can improve the nominal strength of joints. Thoroughly covering the walls of dowel holes with adhesives is important for maximizing connection strength [3,14–17]. The type of base material, such as particleboard or medium-density fiberboard (MDF), can also affect the strength of the corner joints. The density and gradation of the materials used in furniture can significantly affect the joint strength. Acrylonitrile butadiene styrene (ABS), polyvinyl chloride (PVC), melamine, and wood veneers are commonly used for edge banding. ABS is known for their impact resistance, durability, and overall appearance. PVC edge banding is manufactured using high-impact modifiers that provide excellent machinability and impact resistance. Melamine-impregnated paper is absorbed with resin and covered with a lacquer surface, resulting in a high strength and resistance to impacts, scratches, and abrasion. Wood veneer edge banding is performed on slices of real wood, allowing it to be painted or varnished to match other furniture parts [3–6]. Each material has unique properties and advantages, making it suitable for different applications in edge banding (Table 2).

Table 2. Overview of edge banding materials.

Material	Advantages	Disadvantages	Use Cases	Key Insights
PVC	■ Cost-effective and widely available ■ Water and moisture-resistant ■ Comes in a variety of colors and textures ■ Easy to process and apply	■ Environmental concerns due to harmful chemicals released during production and disposal ■ Can appear less premium than natural materials ■ Limited heat resistance	■ Kitchens and bathrooms ■ Budget-friendly furniture designs	PVC is a cost-effective choice for moisture-prone environments but has environmental drawbacks.
ABS	■ High impact resistance ■ Durable and scratch-resistant ■ More environmentally friendly than PVC ■ UV resistant ■ Lightweight	■ More expensive than PVC ■ Lower heat resistance than some other materials ■ Limited flexibility for complex shapes	■ High-end, durable furniture ■ Office and commercial furniture exposed to wear and tear	ABS offers a more durable alternative to PVC, particularly suited for high-traffic or commercial settings, though it comes at a higher cost.
Wood veneer	■ Provides a natural, authentic appearance ■ Luxurious, premium feel ■ Can be FSC/PEFC certified for sustainability ■ Can be refinished	■ Sensitive to humidity (warping/swelling) ■ Requires careful maintenance ■ More expensive and less impact-resistant than plastics	■ High-quality furniture ■ Furniture for living rooms, dining rooms, and bedrooms where aesthetics matter	Wood veneer is preferred for high-end furniture due to its natural beauty but requires careful handling and environmental controls.

Table 2. *Cont.*

Material	Advantages	Disadvantages	Use Cases	Key Insights
Aluminum	■ Modern, sleek appearance ■ Excellent impact resistance ■ Lightweight and corrosion-resistant ■ Durable and low maintenance	■ Higher cost than plastic edges ■ Requires specialized application techniques ■ Cold appearance may not fit all design aesthetics	■ Modern or industrial-style furniture ■ Decorative furniture ■ Areas requiring high durability	Aluminum is visually striking and durable, making it ideal for contemporary designs, though it can be costly.
Edges for Special Applications	■ Available in various textures, like on panel surfaces. ■ Ideal for profiled furniture edges	■ Some materials may lack the flexibility needed for profiled forms. ■ Higher production costs due to special machines ■ Not applicable for curved panel edges	■ Furniture with profiled edges ■ Machines for soft and/or post-forming processes	Special application edges offer flexibility for unique designs but require higher production investment and specific material selection, making them suitable for complex, custom furniture.

3.1. Edge Band Studies

Edge banding, particularly melamine, has been found to improve the strength of corner joints in furniture, particularly in tension and compression tests [3]. This improvement in strength is further enhanced when using coated MDF with edge banding because it can increase the load-bearing capacity and service life of cabinets [18]. The use of rebated and covered edges in case furniture can further enhance the tension and compressive strength of corner joints [19]. However, [20], in their research on corner joints constructed with wood biscuits, found that the strength of corner joints was primarily derived from the edge gluing of the face and butt member rather than the glued biscuits. Tankut and Tankut [3] found that melamine-edge banding material provided better structural integration and higher strength compared to PVC and wood-veneer edge banding materials, with the positive role of its 0.4 mm edge banding on 18 mm particleboard of corner joints in case furniture. Miškinytė and Juknelevičius [5] found that the type and thickness of the edge banding material can influence the bending and tensile strength of the particleboard, which in turn can affect the quality of different glued joints.

Different methods can be found in the literature to investigate edge bonding quality: from a pull-off test in accordance with EN ISO 4624:2017 [21] to measure the force required to detach the edge band from the wood-based panel Džinčić and Palija [22] or EN 28510-1:2014 [23], which involves peeling of glued flexible and rigid specimens together at an angle of 90° [5]; or EN 311:2004 standard [24], which, among others, specifies assessing the surface soundness of coated wood-based panels and uncoated particle boards, used to determine the adhesion of the edge banding to the particleboard samples [25]; and up to the test on the peel strength of PVC edge bands on curved edge parts in accordance with Chinese standard QB/T3655 [26,27]. The mentioned methods are illustrated in Figure 1.

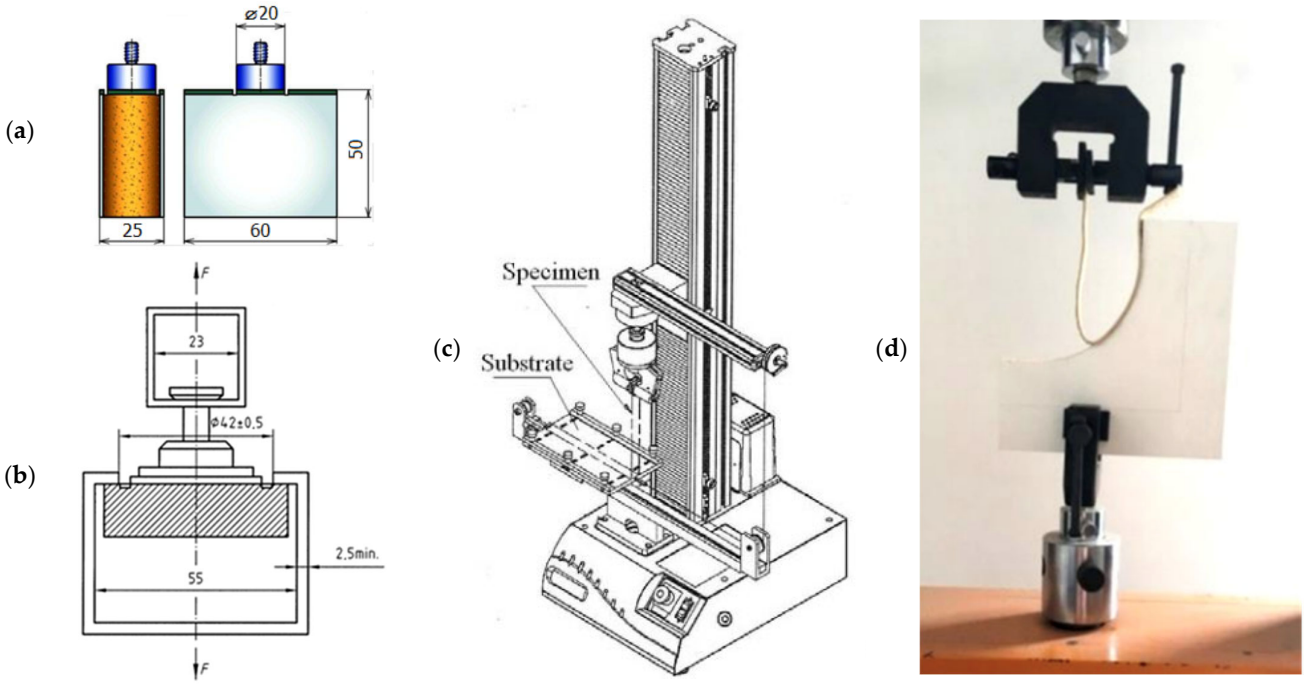


Figure 1. Test samples and appropriate devices for various methods to evaluate the edge bonding quality: (**a**) pull-off test according to EN 311:2014 [24] adapted to EN ISO 4624:2017 [21]; (**b**) adhesion test using EN 311:2004 [24] to evaluate surface soundness and adhesion of edge banding; (**c**) peeling test in line according to EN 28510-1:2014 [23]; (**d**) peeling test for curved edges according to Chinese standard QB/T3655 [27] ((**a**,**c**) were reprinted from Hlavatý and Tesařová [28], Figure 1d was reprinted from Lyu et al. [26]).

3.1.1. The Influence of the Type of Glue on Quality of the Glued Joint

The type of glue used in furniture construction significantly affects the strength and durability of joints. Different types of glue have different adhesive properties and bonding strengths, which can affect joints of different edge band material and/or overall furniture joint performance (Table 3). Altinok et al. [29] found that the combined use of dowel and spline joints with polyvinyl acetate (PVAC) glue resulted in the highest tension strength in the corner joints. Tankut and Tankut [15] further emphasized the importance of the glue type, with PVAC adhesive leading to higher diagonal tension and compression strength in case-type furniture corner joints. Dizel and Uzun [30] investigated the gluing of a wooden edge strip to the edge of a particleboard and found that the use of a PVAC adhesive resulted in the highest bonding strength. Imirzi et al. [31] further emphasized the importance of the type of adhesive, where the PVAC adhesive along with the screw provides the highest moment-carrying capacity in L-type corner joints. Therefore, it is crucial to consider glue application techniques, surface quality, and edge banding materials when aiming for high-quality glued joints in furniture design.


Different glue application techniques can also affect the quality of the glued joint of the edge band on a three-layer particleboard in the furniture design. The surface quality of the particleboard plays a significant role in the wetting and adhesion of glue. Preparation of the surface before gluing can affect superficial deterioration and local weaknesses in the joint [32]. Hlavatý and Tesařová [28] highlighted the potential impact of temperature on the stability of glue joints, with a decrease in the joint stability observed at higher temperatures. Tankut and Tankut [3] explained the correlation between pressure and tension forces on adhesive tapes and the quality of furniture. Džinčić and Palija [22] pointed out the variability in glue applications owing to gaps between the edge material and the application roller due to deviation of the edge to the wider side of the panel in terms of the angle and

straightness of the joint, which occurred during the milling process before the edge banding and can lead to uneven adhesive layers with potentially weaker bonds.

Table 3. Comparative analysis of glue type, edge band material, and joint design on bond strength and practical applications in wood panel furniture.

Glue Type	Material	Joint Type/Design	Key Findings	Practical Implications	Paper
PVAC	Particleboard	Dowel and spline joints	PVAC glue provided the highest tension strength	PVAC glue is highly effective for corner joint durability	Altinok et al. [29]
PVAC	Melamine-coated MDF	Case furniture corner joints	Higher diagonal tension and compression strength	PVAC glue enhances overall structural integrity	Tankut and Tankut [15]
PVAC	Wooden edge strip on particleboard	Edge strip	PVAC glue resulted in the highest bonding strength	PVAC is preferred for strong adhesive bonds on edges	Dizel and Uzun [30]
PVAC + screws	L-type corner joints	Corner joints	PVAC with screws offers the highest moment-carrying capacity	Combined PVAC glue and screws improve load-bearing joints	Imirzi et al. [31]
EVA	Particleboard	Edge band on three-layer particleboard	Glue temperature and application affect bonding	Optimal glue temperature and parameters critical for edge bonding strength	Džinčić and Palija [22]
Temperature variations	Particleboard	Glued joints	Temperature decreases joint stability at high temps	Careful glue selection and temperature control are needed to ensure joint stability	Hlavatý and Tesařová [28]
PVAC-D4, PUR-D4	Particleboard with dowels	Dowels with PVC edge banding	Polyurethane glue provided the highest strength, a 0.8 mm edge band was most effective	Thinner edge bands perform better in dowel joints when combined with polyurethane glue	Karaman [13]
Laser technology	Particleboard and edge band	Edge band materials	Laser technology melts a pre-applied adhesive layer on edge bands, allowing precise adhesive distribution and strengthening the bond with the panel.	Laser-based edge banding provides high precision and consistency, suitable for high-quality, modern furniture with "zero joint"	Jansen et al. [7].

Also, the introduction of laser technology in edge banding enhances the conventional gluing process by melting a pre-applied adhesive layer on edge bands using a laser to generate controlled heat (Figure 2). This precise application allows optimal adhesive distribution and strengthens the bond between the edge band and the panel [7].

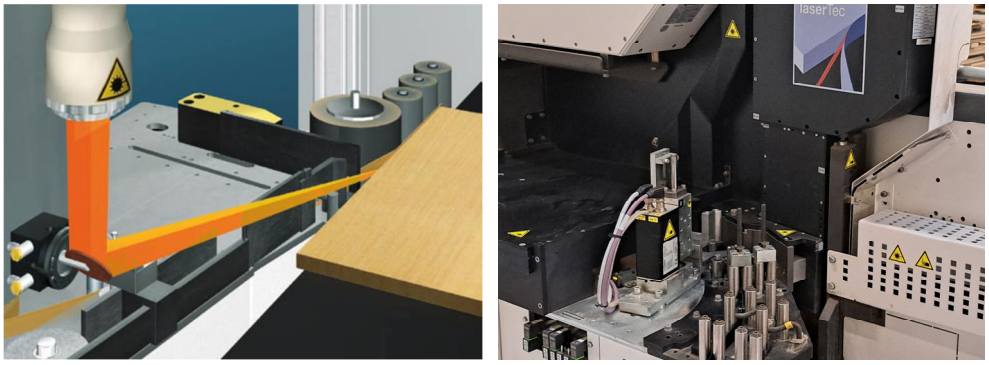

(**a**) (**b**)

Figure 2. Schematic view of laser edge band gluing (**a**) (reprinted from Jansen et al. [7], copyright (2009), with permission from Springer) and view of the laser-glue unit on the edge banding machine (**b**) (Photo by G. Mihulja).

3.1.2. The Influence of the Edge Surface Treatment of Wood Based Panels

The state of the edge of particleboard is an important criterion for assessing the quality of wood-based materials [4]. According to Triboulot et al. [33], the thickness of the glue joint is related to the surface quality, and it is important to determine the optimal machining conditions for preparing the surface for gluing. Sawing and milling can damage the laminate in the vicinity of the processing zone and bead of the particleboard edge, leading to delamination during machining [32]. Wear of the cutting tool also plays a significant role in the delamination process [6]. Therefore, the processing method and tool wear should be carefully considered to minimize delamination and ensure the quality of gluing the edge band on the three-layer particleboard. The findings of Džinčić and Palija [22] have significant practical implications for the edge-bonding quality. This study highlights the critical influence of panel squareness on edge bonding strength, suggesting that maintaining minimal angular deviation during manufacturing can enhance joint strength. In particular, the influence of squareness after processing using pre-cutters and the position of the glue application roller were investigated. This insight is crucial for manufacturers aiming to improve product durability and reduce failure rates. The lack of defined minimum strength standards for edge bonding in existing regulations underscores the need for industry-wide benchmarks to ensure consistent quality.

These findings collectively suggest that the selection of glue, application technique, preparation of the gluing surface, and gluing parameters are crucial in ensuring the strength and durability of edge banding.

Edge banding improves corner joint strength compared with unbanded joints in cabinet furniture. The ultimate strength of cabinets constructed with edge banding was found to be 1.8 times greater than that of cabinets made without edge banding [18]. Based on the results of Tankut and Tankut [3], cabinets made of melamine-coated MDF with edge bands had a higher load-bearing capacity than cabinets made of uncoated MDF without edge bands. The type of edge banding material used also has a significant impact on the strength of the corner joints, with melamine edge banding material providing the highest diagonal tension and compression strength [4].

During the testing of the edge bonding quality (EN ISO 4624:2017 [21]), several factors were considered: the squareness of wood-based panels after processing by pre-cutters, position of the glue application roller, and angular deviation of the edge to the wider side of the panel. The properties of the particleboard (density, moisture content, and delamination strength of the layers) were considered but were not directly investigated [22]. The influence of glue parameters, including the glue temperature and method of application, was found to affect the bonding quality. The research indicated that the optimal glue temperature for the EVA adhesive used in this study was 210 °C, with an application quantity of 110 g/m^2 and a feed speed of 15 m/min. The gluing parameters were controlled using an automatic edge banding machine. Variations in these parameters can lead to changes in the bonding strength, with the highest strength observed in the samples with the smallest angular deviation from the edge to the wider side of the panel. The study also highlighted that the properties of the glue, such as its ability to fill gaps, are crucial, as evidenced by the performance of EVA glues in accommodating a gap created by a 2° slope.

The study in [5] utilized SolidWorks simulation for both static and thermal analysis, applying mathematical finite element method (FEM) virtual modeling to assess the mechanical properties of ABS and oak veneer lamination materials, suggesting that oak veneer edges offer superior mechanical properties and adhesion to particleboard compared to ABS edges. During the peel-off testing phase (EN 28510-1:2014 [23]), researchers considered mechanical properties, such as resistance to peeling forces, which were evaluated using a standard test method. The thickness of the lamination material is another critical factor, as it was hypothesized to influence the strength and quality of the furniture. Their research indicated that a thicker edge band (i.e., 2 mm oak veneer) could potentially enhance the strength and quality of the furniture, as well as improve its resistance to peeling forces. Static analysis showed that the probability of deformation of furniture boards/elements

decreased with thicker lamination, suggesting that thicker edges adhered more strongly to the particleboard. Additionally, thermal analysis revealed that the 2 mm thick ABS edge was the most heat-resistant, while the 1 mm thick oak veneer edge retained the most heat, indicating that the thickness also affected the thermal properties of the materials. This research also highlights the importance of considering the elasticity of lamination materials, especially for curved parts, where ABS's higher modulus of elasticity could reduce lamination issues.

The findings of Lyu et al. [26] have significant practical implications for the furniture manufacturing industry, particularly for small- and medium-sized enterprises specializing in panel furniture with curved edges. The optimal technical parameters were identified: temperature of applying EVA glue at 140–150 °C, glue dosage of 363–379 g/m^2, feed rate of 13–15 m/min—can be directly applied to improve the peel strength of PVC edge bands, thereby enhancing product durability and reducing failure rates during use. This study also highlights the importance of maintaining these parameters within specific ranges to avoid issues such as insufficient peel strength due to premature drying of the adhesive or inadequate pressure application, which are critical for ensuring the quality and longevity of edge-banded furniture components. This study is structured into three separate experiments, each focusing on one of these factors. The glue dosage was carefully measured to balance between sufficient bond strength and the avoidance of quality issues, such as glue line and glue stain. The feed rate was assessed to find a balance between the adhesive opening time and the workers' ability to apply proper pressure, which is crucial for achieving adequate peel strength without causing edge breakage. A universal testing machine was used for the peel tests, with the peel speed set to 48 mm/min. The results were calculated and analyzed according to the Chinese standard QB/T3655 [27].

Saçli [6] showed that the type and thickness of edge banding materials, as well as the duration of heat exposure, substantially affect the bending and tensile strength of MCP, with thicker PVC edge banding showing increased strength over time. This knowledge can guide manufacturers to select appropriate edge banding materials and thicknesses to enhance furniture durability and performance. PVC (0.4, 0.8, 1, and 2 mm) and melamine (0.4 mm) were used as edge banding materials. The edge bands were affixed using hot-melt adhesive with iron at 200 °C for melamine and with an auto edge banding machine for PVC (at 200 °C and feed speed of 12 m/min). The mechanical properties, including the bending and tensile strengths, were measured using a universal testing machine 20, 30, 40, and 50 days after edge-bending and product weathering treatment at different indoor temperatures. Edge banding significantly influences the bending and tensile strengths of melamine-coated particleboards (MCP). Thicker PVC edge bands, specifically 2 mm, have been shown to provide the highest bending and tensile strengths after 50 days, indicating that edge banding can effectively enhance the mechanical properties of MCP over time. Conversely, non-banding or the use of thinner edge bands, such as 0.4 mm melamine, results in lower strength.

Borysiuk et al. [25] indicated that the choice of edge band material and thickness has a significant impact on the mechanical and physical properties of particleboard slats, which are critical in furniture design and manufacturing. Contrary to expectations, the use of 2 mm thick PVC and ABS edges notably reduced the modulus of rupture (MOR) and modulus of elasticity (MOE), which could influence the structural integrity and load-bearing capacity of furniture components. Additionally, these materials significantly limit swelling and water absorption, thereby enhancing the durability of the furniture under humid conditions. However, the susceptibility of PVC and ABS to deformation compared to other materials, such as veneers, must be considered in applications where dimensional stability is crucial. This study underscores the need for further research on the influence of edge bands on furniture strength, particularly for narrow slats, to inform material selection and design decisions in the furniture industry. The application of 2 mm thick PVC and ABS edges decreased the MOR and MOE values, potentially affecting the structural integrity of furniture components. Despite this, 1 mm thick PVC and ABS edges exhibit the best

adhesion to particleboard when using EVA hot-melt adhesive, indicating a strong bond and finish quality. It is important to note that the adhesion of the edges was tested using different methods in various tests, which could influence the outcomes. It is also important to consider environmental implications, as PVC waste requires specialized processing owing to the release of toxic compounds upon uncontrolled burning, whereas ABS is safer for human health and the environment. ABS edges are gaining popularity for ecological reasons, despite PVC's current market dominance due to its lower cost.

Özcan et al. [9] and Kurt et al. [8] were motivated by the increased use of composite materials and wooden dowels in furniture. However, they noted a lack of detailed information on the best ways to combine these materials to achieve the maximum strength. This study tested dowels made from different types of wood, including beech, oak, mulberry, apple, and fir, to determine which works best with particleboard and MDF. Dowels with different diameters (6, 8, and 10 mm) were tested to determine how well they were held on boards when bonded with two types of adhesives: PVAC and polyurethane (desmodur-vinyl trieketonol acetate (D-VTKA). The researchers followed specific standards, such as TS 4539 [34] for testing the withdrawal strength and ASTM D1037 [35] for setting the loading rate during the tests, ensuring the consistency and reliability of the methodology. The results showed that the face direction in MDF had the highest withdrawal strength, D-VTKA adhesive outperformed PVAC adhesive in terms of withdrawal strength, and MDF showed better results than particleboard owing to its higher density and more homogeneous structure. Similar to the previous two papers, Karaman [13] tested dowels made from five different types of wood—beech, Scots pine, Turkish fir, chestnut, and olive—to see how well they worked when used in particleboards for furniture making. PVC edge banding with thicknesses of 0.8 mm, 1 mm, and 2 mm was used to understand its impact on the strength of the dowel joints in the particleboard by using two types of water-resistant adhesives: polyvinyl acetate (PVAC-D4) and polyurethane (PUR-D4). The study found that dowels made from beech wood and bonded with polyurethane adhesive showed the highest strength, while PVC edge banding with a thickness of 0.8 mm significantly increased the strength of the dowel joints compared to other thicknesses, indicating that thinner edge banding performs better in this application.

Merdzhanov [11] optimized the edge banding process by developing mathematical models and a computerized program that could predict the best settings for different materials, ensuring that the adhesive layer was minimal and the bond strength was maximized under varying conditions. This study aimed to understand how well different types of edge banding materials stick to particleboards when using a specific hot-melt adhesive, focusing on determining the best conditions for a strong bond by examining various factors such as the glue amount, temperature, and pressure applied during the process. This study tested three types of edge banding materials on particleboards: beech veneer edge strips, melamine edge foil, and PVC edge foil. The adhesive compound was applied with a tensile load perpendicular to the veneering surface using a T-shaped steel body attached to the edge material by a cyanoacrylate adhesive to evenly spread the tensile forces. The author found that not all materials worked in the same way; therefore, he had to adjust the glue temperature and pressure to obtain the best stickiness. For example, melamine foil requires higher pressure when the glue is hotter, and PVC materials work best at a specific temperature and lower pressure.

Kubit et al. [12] wanted to understand whether increasing the thickness of the glue layer at certain points could help absorb more energy and reduce the risk of joint breakage under repeated use, which is crucial for industries that require lightweight and strong connections. This study explored how making small changes to the edges of the parts being glued together can significantly improve how long and well they hold up under repeated use. Specifically, it looks at adding a slant (chamfer) or rounded edge (fillet) to the part where the glue is applied, aiming to make the glue layer thicker in spots where stress is high, which helps the joint last longer and perform better under fatigue or repeated stress. Researchers have conducted tests using a special machine that shakes parts at a


specific frequency to mimic the stress of repeated use. They found that these small changes, especially the rounded edge, greatly increased the strength and lifetime of the glued joints under stress, showing a notable improvement in how the glue absorbs energy and handles stress without breaking. The best improvement was observed with a rounded edge (fillet R2), which made the glued joint last over three times longer and increased its strength by 33.1% compared to a standard joint without these modifications. This improvement occurs because the changes in shape help spread the stress and allow the glue to absorb more energy, which slows down the damage caused by repeated bending and pulling.

Table 4 presents a comparative analysis of edge surface treatments and their influence on wood-based panel performance, highlighting key findings regarding various techniques and their impact on performance characteristics.

Table 4. Comparative analysis of edge surface treatments and their influence on wood-based panel performance.

Material Type	Treatment/ Technique	Testing Standards/ Methods	Key Findings	Practical Implications	Paper
Particleboard	Sawing and milling	-	Surface quality influences glue thickness	Surface preparation is crucial for optimal glue performance	Triboulot et al. [33]
Particleboard	Pre-cutters, glue application	EN ISO 4624:2017 [21]	Angular deviation affects bonding strength	Maintaining minimal angular deviation improves bonding strength	Džinčić and Palija [22]
PVC edge bands	Temperature, glue dosage, feed rate	Chinese standard QB/T3655 [27]	Higher peel strength with optimal parameters	Guidelines for improving edge band durability and adhesion in furniture	Lyu et al. [26]
PVC and Melamine edge bands	Edge banding using hot-melt adhesive	Universal testing machine (bending and tensile test)	Thicker edge bands increase strength over time	Thicker edge bands, such as 2 mm PVC, enhance bending and tensile strength	Saçli [6]
Particleboard, glued joints	Chamfer, rounded edge (fillet)	Fatigue testing (frequency, stress application)	Rounded edges increase strength and fatigue resistance	Rounded edge modifications improve joint durability and lifetime	Kubit et al. [12]

Jansen et al. [7] demonstrated that laser edge banding technology not only improves the efficiency of the bonding process but also enhances bond strength and durability (Figure 3a). Their thermal aging tests (30 days at 60 °C) showed that laser-bonded edges achieve comparable strength to conventional methods. The ability to use high-temperature adhesives reduces joint failure and enhances impermeability, verified by ISO 15148:2002 [36] water absorption tests, which showed lower water uptake in laser-bonded samples (Figure 3b). The laser process minimizes chipping and creates a strong bond even in deeper wood layers, offering a clean appearance with no visible adhesive joints. This method allows quick adjustments for different materials, saving time by eliminating preheating or cleaning downtime. The technology's flexibility and strength make it ideal for mass production, leading to the "laserTec" concept winning the innovation prize and the Wilhelm-Klauditz Prize at Ligna 2009.

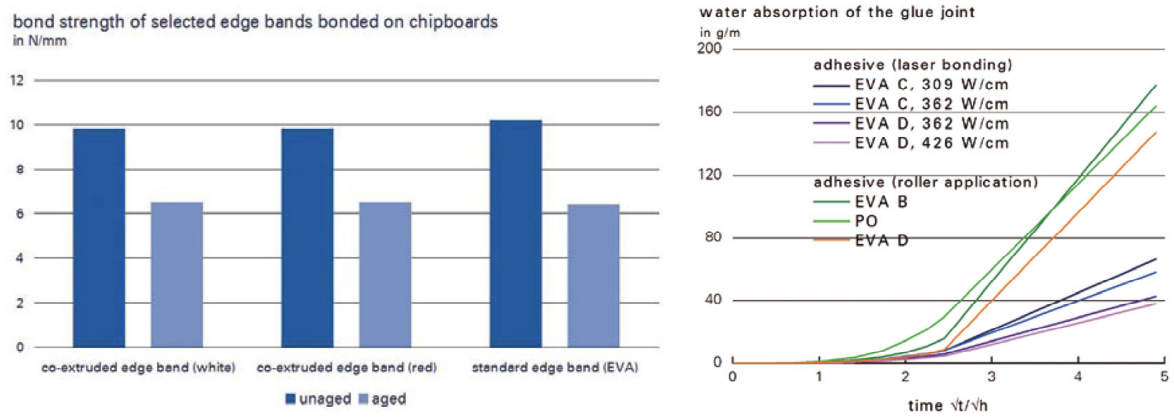


(**a**) (**b**)

Figure 3. Bonding strength of edge bands tested (**a**) and water absorption through glued joints (**b**) (reprinted from Jansen et al. [7], copyright (2009), with permission from Springer).

3.2. Corner Joints Studies

When selecting corner joints (Figure 4) for particleboard furniture, trade-offs exist between strength, durability, and aesthetics. Research indicates that the type of fastener used significantly affects joint strength and bending moment resistance [37]. For instance, cam-connecting fittings and glued dowel joints can enhance strength but may not be as durable as other options [38]. Additionally, the thickness of the edge banding materials can influence the joint strength under compression tests, highlighting the importance of material choice for durability [1]. Moreover, the number and spacing of dowels in ready-to-assemble furniture joints can affect the bending moment capacity, showcasing the interplay between strength and aesthetics [39]. Therefore, when choosing corner joints, it is crucial to balance these factors to achieve the desired strength, durability, and visual appeal of the particleboard furniture.

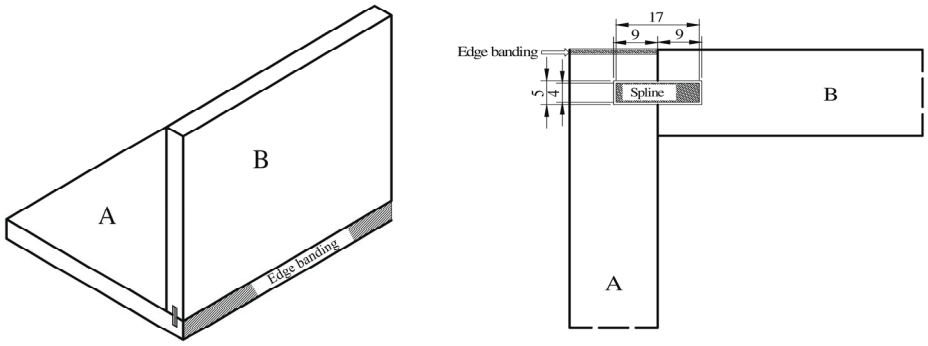

(**a**) (**b**)

Figure 4. Typical configuration (**a**) and detail (**b**) of L-type corner joints used in the tests (in mm) (reprinted from Tankut and Tankut [3], copyright (2010), with permission from Elsevier).

3.2.1. The Influence of Different Types of Corner Joints on the Overall Strength and Durability of Panel Furniture

The corner joint design choices affect the overall strength of particleboard furniture. Particleboards exhibit higher creep deflection under cyclic conditions, indicating susceptibility to stress over time. However, certain joint types can mitigate this effect [40]. Research has shown that factors such as the type of composite board, gluing technique, and spacing between fitting elements such as biscuits or dowels play a crucial role in determining the strength of corner joints in particleboard furniture [10,41,42]. For example, corner joints constructed with wood biscuits glued in slots tend to be stronger than those made

with plastic biscuits, demonstrating the importance of material and construction method choices [43]. Glued-in dowel joints show lower strength loss after cyclic loading than other types of joints [44]. Additionally, the spacing between biscuits in multiple-biscuit corner joints can affect the total strength in tension and compression tests, highlighting the need for strategic design decisions to optimize the strength and durability of particleboard furniture joints [20]. Using wood biscuits with edge-banded MDF, joints are stiffer than those constructed with edge-banded particleboards [10,37]. The bending moment capacity of corner joints increases with the number of dowels and decreases with a certain dowel spacing. Tankut and Tankut [20] showed that the composite board used influences the strength of the joints, with melamine-coated fiberboards exhibiting a 40% higher bending moment resistance than melamine-coated particleboards.

The type of fastener used, quality of the particleboard, and method of loading affect the joint capacity and bending moment resistance [37,45]. By comparing the strengths of different types of corner joints using various fittings and inserts, Prekrat et al. [46] explained how each element of an angle joint affects and contributes to durability. The strength of corner joints varies with the type of fastener used, impacting the technical quality of the furniture. For example, confirmat screws exhibited the highest strength among the tested fasteners, providing four times the momentum value compared to the weakest connection with the Lamello Clamex fittings. This suggests that confirmats are particularly suitable for applications requiring a high load-bearing capacity, but they are aesthetically less acceptable than dowels or elliptical fittings unless the screw head is hidden. In contrast, Lamello Clamex P 15 and Lamello Invis Mx offer lower strength values, indicating their suitability for lighter applications. The Minifix bolts, which are 34 and 24 mm in size, show a nuanced difference in strength, with the longer bolt slightly outperforming the shorter bolt, although the difference is not significant. As a supplement to previous research, Imirzi et al. [31] found that particleboard demonstrated lower moment-carrying capacities than other wood and wood-based materials, indicating a relatively weaker performance in load-bearing applications. When applied to particleboards, the Minifix fasteners produced the lowest moment-carrying capacity values, suggesting that the choice of fastener type is crucial for enhancing the structural integrity of the corner joints. In addition, the Clamex P fasteners exhibited high-resistance characteristics in diagonal compression and withdrawal tests, which could imply a potential for better performance in joints under specific conditions. However, the inherent material properties of particleboard, such as its susceptibility to breakage owing to excessive channel widths, can negatively impact the overall performance and durability of the joint. This analysis underscores the importance of selecting an appropriate fastener type based on the specific load requirements and structural considerations of furniture design.

Miter corner joints, studied in [38], when compared to conventional cam-connecting fittings and screw joints, exhibit a superior load-bearing capacity, enhancing the overall strength of the furniture by 8.1 and 2.6 times, respectively. This is attributed to the efficient utilization of the mechanical characteristics of the particleboard, particularly when the joints are bonded with the PVAC adhesive, and the surface is veneered. Veneering the particleboard not only increases the aesthetic appeal but also strengthens the outer layer, thereby improving the joint's capacity to carry loads by 19.5%. The application of thin veneer overlays on particleboards reduces creep potential, indirectly mitigating warping over time [47]. The application of adhesive joints in furniture construction contributes to a longer exploitation duration and higher load tolerance than those of dismantlable joints. However, despite the enhanced strength and aesthetic benefits of miter joints, their complexity in manufacturing and assembly limits their widespread application in furniture with large dimensions and complex construction. The strength of furniture corner joints is primarily derived from edge gluing of the face and butt members, emphasizing the importance of joint tightness for durability [20]. The polyurethane adhesive provides a higher bending strength for the corner joints than the PVAC adhesive, indicating that superior glue quality enhances joint durability [43].

The strength and durability assessment of various corner joint types in panel furniture, which is crucial for ensuring the structural integrity and longevity of furniture designs, is presented in Table 5.

Table 5. Strength and durability assessment of various corner joint types in panel furniture.

Corner Joint Type	Effect on Strength	Effect on Durability	Papers
Cam connectors and dowels	High strength; varies by dowel number	Less durable under long-term stress	Jivkov [1], Tankut and Tankut [20], Jansen et al. [7]
Biscuits (wood vs. plastic)	Wood biscuits increase bending moment resistance	Wood biscuits last longer under cyclic loading	Imirzi et al. [31], Jivkov [1]
Confirmat screws	Superior strength in load-bearing applications	Aesthetic limitations unless concealed	Kasal et al. [39], Tankut and Tankut [20]
Lamello Clamex P and Invis Mx	Lower strength; suitable for lighter applications	Limited by low load-bearing capacity	Kasal et al. [39], Jansen et al. [7]
Miter joints	8× higher strength than cam fittings with PVAC adhesive	Higher durability with veneered particleboard	Jansen et al. [7], Jivkov [1], Kasal et al. [39]
Edge banding thickness	Enhanced compression strength with 0.4 mm edge-banding	Increases joint stiffness	Jivkov [1], Jansen et al. [7]

3.2.2. The Influence of Different Factors on Load-Bearing Capacity and Failure Points Specific to Panel Corner Joints

Factors such as the type of joint reinforcement, such as wood biscuits, significantly impact the failure load and strength of the joints [14,41]. The type of material used, whether particleboard or MDF, and the specific insert fittings utilized in the joints play a crucial role in determining the bending strength of the furniture corner joints [20]. The manner in which the joints are loaded, the gluing techniques employed, and the distribution of stresses within the joint also affect the failure points and load-bearing capacity of the corner joints [37].

Increasing the number of dowels enhances the bending moment resistance, indicating a direct correlation between dowel quantity and joint strength. Optimal dowel spacing is also critical, while increasing the spacing up to 160 mm improves the moment resistance, and further increasing it to 192 mm reduces it, suggesting a nonlinear relationship between dowel spacing and joint performance [48]. Moreover, the type of board material affects the load-bearing capacity, with melamine-coated fiberboards demonstrating superior bending moment resistance compared to melamine-coated particleboards, which is attributed to better adhesive interactions and material properties.

The load-bearing capacity and failure points of particleboard corner joints are also influenced by the moisture content of the environment, the type of adhesive used, and the method of joint construction, according to [47]. Higher humidity environments (with 90% relative humidity compared to a dry environment with 45% relative humidity) during the gluing process significantly increased the load-carrying capacity and stiffness of the glued dowel joints on the particleboard. This was attributed to the more effective penetration of the polyurethane adhesive and swelling of the dowel and particleboard, which resulted in a stronger joint. The mechanical properties of these joints, including their failure points, are affected by the type of mechanical fasteners and the joining method, with demountable joints showing a higher loading capacity under varying humidity conditions.

Kasal et al. [39] found that corner joints are significantly influenced by the number of screws, screw size (diameter and length), and loading type (compression or tension). Specifically, increasing the number of screws enhanced the moment resistance of the particleboard corner joints, with a notable improvement observed when four screws were used compared with two or three screws. Screw length had a more pronounced effect on bending moment resistance than screw diameter, indicating that longer screws contributed more effectively to joint strength. However, the observed joints exhibited a differential

response to loading types, whereas there was no significant difference in moment resistance between compression and tension loadings for joints connected with 2 mm to 5 mm diameter screws. Particleboard joints with 5 mm diameter screws with a length of 60 mm showed significantly greater moment resistance to compression loads than to tension loads. The failure modes for these corner joints typically involve the crushing of screw heads into the face member, followed by screw withdrawal from the butt members along with base material and edge splitting around the screws.

According to Jivkov [1], the load-bearing capacity of particleboard corner joints is significantly influenced by the presence and thickness of edge banding. Edge banding enhances the bending strength under compression tests, with a thickness of 0.4 mm being sufficient for Minifix and Rafix connectors to achieve 15–25% higher bending strength. The type of edging material, specifically the ABS band, and its application process also play a crucial role in the joint strength. Furthermore, the ultimate bending moment, which is a critical measure of the load-bearing capacity, was positively affected by edge banding, as evidenced by the statistical analysis of different joint types. Notably, edge banding prevents the splitting of the particleboard edge, which is a common failure point in unedged joints, thereby enhancing the overall structural integrity of the furniture.

Table 6 presents a comprehensive overview of the factors that influence the load-bearing capacity and potential failure points in the design of panel corner joints.

Table 6. Overview of load-bearing capacity influences and failure points in panel corner joint design.

Factor	Influence on Load-Bearing Capacity	Failure Points	Papers
Joint reinforcement (wood biscuits)	Enhances joint strength and failure load	High bending strength achieved with optimized spacing	Imirzi et al. [31], Kasal et al. [39], Jivkov [1]
Material type (particleboard, MDF)	Determines bending strength of corner joints	Particleboard is more susceptible to breakage than MDF	Tankut and Tankut [20], Jivkov [1], Jansen et al. [7]
Moisture content	Higher humidity improves load capacity	Swelling of dowels and adhesives may lead to stronger joints	Jivkov [1], Jansen et al. [7], Kasal et al. [39],
Dowel quantity and spacing	Increased dowel number and specific spacing enhances strength	Nonlinear response to spacing, optimal at 160 mm	Kasal et al. [39], Tankut and Tankut [20]
Adhesive type	PU adhesive offers superior strength over PVAC	Better penetration and swelling lead to stronger joints	Jivkov [1], Jansen et al. [7]
Loading method	Impacts joint performance under cyclic conditions	Screw crushing in face member, edge splitting	Kasal et al. [39], Tankut and Tankut [20]

3.2.3. Influences of Corner Joint Design on the Visual Appeal of Particleboard Furniture

In the context of panel furniture manufacturing, the aesthetic components of corner joints are crucial for the overall appearance and consumer satisfaction. The quality of edge banding, which includes corner joints, significantly affects the aesthetic appeal of furniture, with defects such as edge collapse, glue leakage, and uneven trimming directly impacting the appearance of furniture. Specifically, for corner joints, rounded corners are an essential aesthetic component as well as safety, where edge banding with a thick edge on both sides should feature a radius of at least 1.5 mm to prevent hand scratching, indicating the importance of smooth transitions and safety in design. It should be emphasized that the possibility of edge damage to furniture is reduced if this radius exists because it is more difficult to catch the edge material and mechanical damage if it is not rounded. This detail underscores the critical role of precision in the edge banding process, particularly at corner joints, in enhancing the visual and tactile qualities of furniture [49]. For example, according to Jansen et al. [7], zero-joint edge banding technology enhances aesthetic quality by providing an invisible gluing joint line, which is not achievable with conventional

edge banding methods. This technology ensures a flawless transition between the edge band and the board surface, making the joint appear seamless to the human eye, thereby improving the furniture's visual appeal. The resistance of the adhesive bond to aging is increased, minimizing the impact of external influences such as water or dirt, which further contributes to the aesthetic durability of the corner joint. Aging significantly affects the aesthetics of edge banded furniture, particularly at corners, where exposure to moisture is the most critical factor. Over time, visual appearance can deteriorate owing to factors such as discoloration, rough surfaces, and gloss changes, which are more pronounced in conventional edge banding than in zero-joint technologies. Zero-joint edge banding, which avoids the use of conventional hot-melt adhesives, offers a seamless appearance that is less susceptible to the aging effects of external influences such as water or dirt, thereby maintaining a more consistent aesthetic appeal over time [50]. The thickness swelling of the zero joints was significantly lower after moisture exposure, highlighting the effectiveness of edge sealing in enhancing joint durability against moisture [51].

The quality of gluing the edge band to the three-layer particleboard was influenced by the processing method used. Szwajka and Trzepieciński [32] found that the cutting speed and feed per tooth during milling can affect the delamination factor, which may in turn affect the quality of gluing. Denkena et al. [52] further emphasized the importance of cutting-edge design, with rounded cutting edges improving the tool life and product quality.

Table 7 provides an overview of the design elements that significantly influence the visual appeal and durability of particleboard furniture, highlighting how various factors contribute to both aesthetic quality and structural longevity.

Table 7. Overview of design elements affecting the visual appeal and durability of particleboard furniture.

Design Element	Aesthetic Influence	Additional Benefits	Papers
Edge banding quality	Defects (e.g., edge collapse, glue leakage) reduce appeal	Improves durability with ABS bands	Jivkov [1], Jansen et al. [7]
Radius on corners (≥1.5 mm)	Smooth edges improve visual and tactile appeal	Reduces edge damage, enhances safety	Jansen et al. [7], Kasal et al. [39],
Zero-joint edge banding	Seamless, invisible glue line	Enhanced moisture resistance, aesthetic durability	Jansen et al. [7], Tankut and Tankut [20]
Precision in edge-banding	High precision enhances overall appearance	Contributes to tactile quality and longevity	Jivkov [1],
Aging resistance of adhesives	Maintains aesthetic appeal over time	Minimizes discoloration and gloss changes	Jansen et al. [7], Tankut and Tankut [20]
Moisture resistance	Reduces visual deterioration at corners	Enhances durability against moisture damage	Jansen et al. [7], Tankut and Tankut [20] Antal et al. [50]
Cutting speed and feed	Influences edge banding quality, impacting visual appearance	Affects delamination factor and overall glue quality	Szwajka and Trzepieciński [32]
Thickness swelling resistance	Maintains visual integrity after moisture exposure	Improves joint durability against moisture	Jansen et al. [7], Yerlikaya [51]

Finally, based on the results of the literature review, an overview map of quality parameters along with future research directions was created (Figure 5).

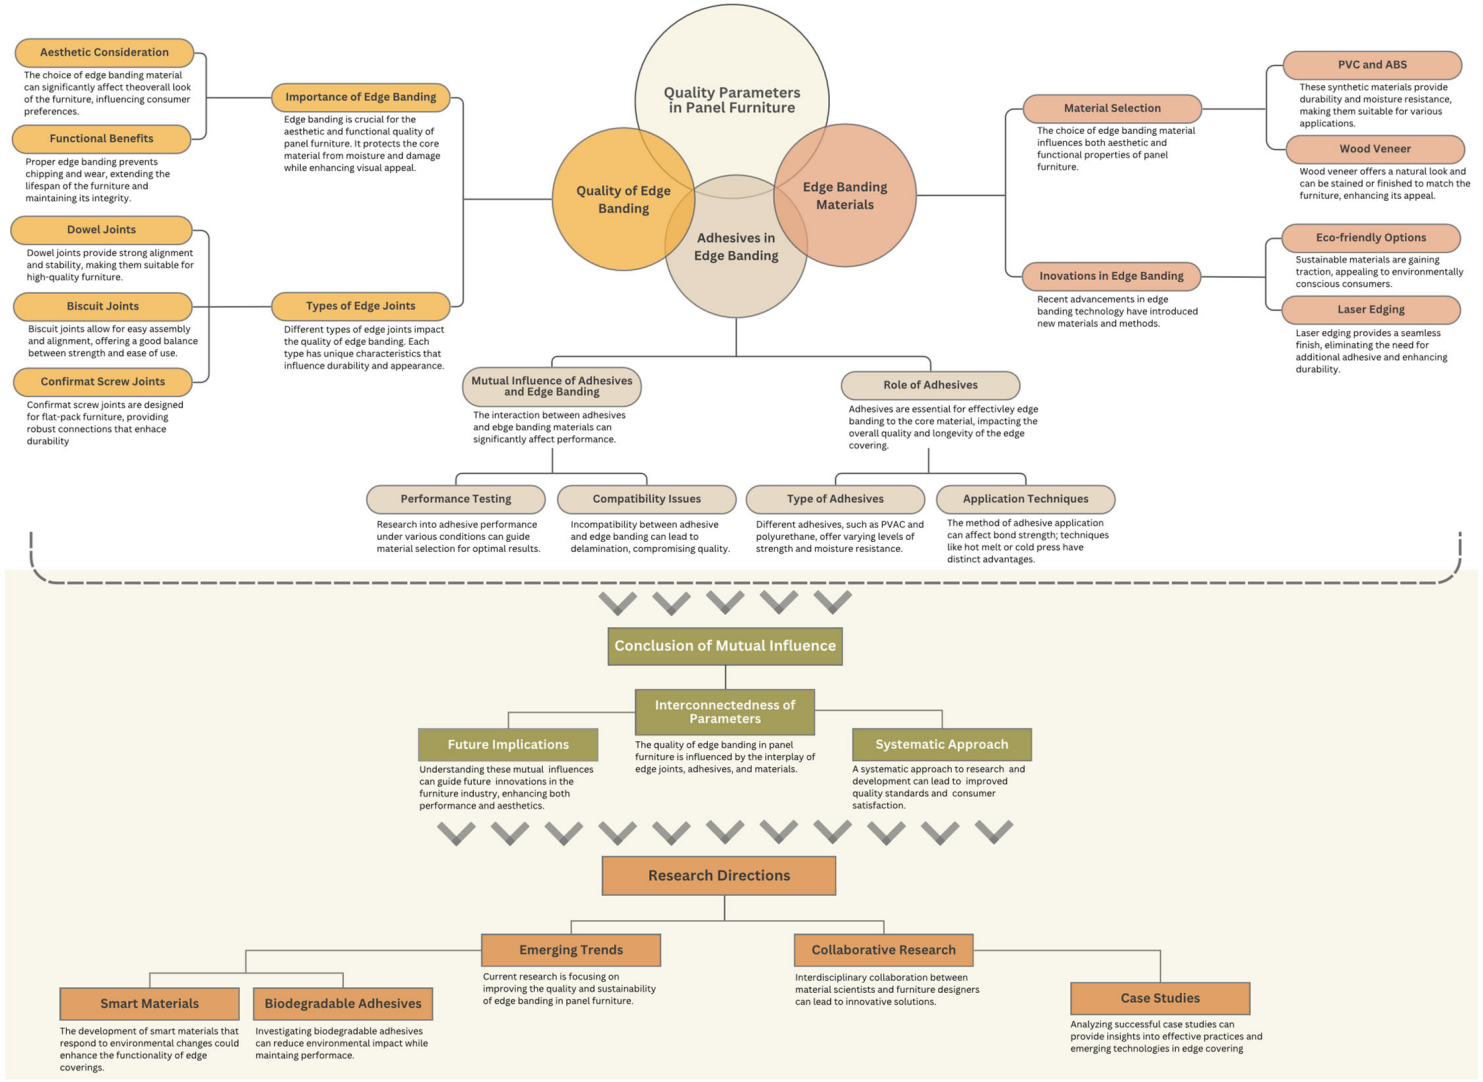


Figure 5. Overview map of quality parameters with future research directions. Designed using Canva.

4. Conclusions

This review offers valuable insights into enhancing the quality of edge bandings and corner joints in furniture made from wood-based materials, identifying potential areas for further research in material properties, adhesive types, and application methods. The review of the literature covered several key factors. However, guidance for further research can be found in three directions in which there is a lack of knowledge for more effective application of materials and edge banding procedures. These are primarily comparisons of the use of possible different methods of applying edge materials, which should be observed through two different edge materials, such as wood in the form of slats or veneers and "its substitute", ABS. Secondly, the need to compare different types of adhesives for the same or different application procedures, again divided into edge materials, can be highlighted. The third direction of research that would enrich the user's knowledge and contribute to a comprehensive understanding of the application of edge materials refers to the comparison of different application techniques on the strength of corner joints and aesthetic properties in furniture production.

Finally, this study provides a comprehensive overview and provides guidelines for further research on the quality parameters in panel furniture (Figure 5). So, the mutual influence between edge banding techniques and adhesive performance can enhance quality parameters in furniture design, emphasizing the importance of effective integration for better aesthetic and structural outcomes. Both aesthetic and functional aspects of edge banding and corner joints are crucial for consumer satisfaction and market competitiveness. The durability and visual appeal of these joints significantly impact overall furniture quality. Also, a shift towards sustainable practices is evident, with an increasing focus on biodegradable adhesives and innovative materials in response to environmental concerns.

In order to advance the field, future research should concentrate on the following areas:

- Comparison of edge materials: Investigating different methods for applying edge materials, focusing on wood slats or veneers versus ABS. Understanding the performance implications of these materials can improve edge banding procedures.
- Adhesive evaluation: Comparing various adhesive types across the same or different application procedures, considering the implications for edge materials. This will help identify the most effective adhesives for specific applications.
- Application techniques: Researching the impact of different application techniques on the strength and aesthetic properties of corner joints. This comparison will enhance knowledge of edge banding effectiveness in furniture design.
- Interdisciplinary collaboration: Encouraging collaboration across disciplines such as material science, engineering, and design to advance edge banding techniques and adhesive applications that meet industry needs.
- Long-term performance evaluation: Conducting longitudinal studies to assess the durability and performance of new edge banding methods and adhesives over time, providing insights into the lifecycle and reliability of furniture designs.
- Compatibility testing: Systematically investigating the compatibility and performance of various adhesive types under different environmental conditions to identify optimal solutions for furniture manufacturing.
- Sustainability focus: Prioritizing the exploration of biodegradable adhesives and smart materials to develop functional and environmentally responsible furniture solutions.

Author Contributions: Conceptualization, Z.V., G.M., D.D. and T.G.; methodology, Z.V. and D.D.; software, T.G.; validation, all authors; formal analysis, all authors; investigation, Z.V. and D.D.; data curation, T.G.; writing—original draft preparation, Z.V. and D.D.; writing—review and editing, G.M., I.Ž. and T.G.; visualization, T.G.; supervision, G.M.; project administration, G.M.; funding acquisition, G.M. All authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by the Ministry of Science and Education, Republic of Croatia, through the University of Zagreb, which allocated short-term support to the Faculty of Forestry and Wood Technology No. 10729, Ur.br. 251-72-08-24-15.

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: The data presented in this study are available upon request from the corresponding author.

Conflicts of Interest: The authors declare no conflicts of interest.

References

1. Jivkov, V. Influence of Edge Banding on Banding Strength of End Corner Joints from 18 Mm Particleboard. In *Proceedings of the International Conference of Nábytok 2002*; University of Forestry: Sofia, Bulgaria, 2016.
2. Cai, L.; Wang, F. Influence Of the Stiffness of Corner Joint an Case Furniture Deflection. *Holz Als Roh Werkst. Eur. J. Wood Wood Ind.* **1993**, *51*, 406–408. [CrossRef]
3. Tankut, A.N.; Tankut, N. Evaluation the Effects of Edge Banding Type and Thickness on the Strength of Corner Joints in Case-Type Furniture. *Mater. Des.* **2010**, *31*, 2956–2963. [CrossRef]
4. Zhou, C.M.; Wu, Z.H.; Ma, D.D. Study on the Solid Edge Banding Cracking of Panel Furniture. *Adv. Mat. Res.* **2011**, *337*, 418–421. [CrossRef]
5. Miškinytė, U.; Juknelevičius, R. Quality Research of Edge Banding of Unit Furniture. *IOP Conf. Ser. Mater. Sci. Eng.* **2022**, *1239*, 012014. [CrossRef]
6. Saçli, C. The Effect of Time and Edge Banding Type and Thickness on the Bending and Tensile Strength of Melamine Coated Particleboard. In Proceedings of the 27th International Conference Research for Furniture Industry, Ankara, Turkey, 17–18 September 2015; pp. 468–480.
7. Jansen, I.; Rechner, R.; Beyer, E. Using Lasers in Edge Banding. *Adhes. Adhes.* **2009**, *6*, 36–40. [CrossRef]
8. Kurt, Ş.; Uysal, B.; Özcan, C.; Yildirim, M.N. The Effects of Edge Banding Thickness of Uludag Fir Bonded with Some Adhesives on Withdrawal Strengths of Beech Dowel Pins in Composite Materials. *Bioresources* **2009**, *4*, 1682–1693. [CrossRef]
9. Özcan, C.; Uysal, B.; Kurt, Ş.; Esen, R. Effect of Dowels and Adhesive Types on Withdrawal Strength in Particleboard and MDF. *J. Adhes. Sci. Technol.* **2013**, *27*, 843–854. [CrossRef]
10. Yuksel, M.; Fathollahzadem, A.; Kuskun, T.; Kilic, H.; Kasal, A. Effect of the Diameter and Penetration of Dowels on Withdrawal Force Capacity of Medium Density Fiberboard and Particleboard. In Proceedings of the 2nd International Furniture Congress, Mugla, Turkey, 13–15 October 2016; pp. 605–611.
11. Merdzhanov, V. Comparative Study of Tensile Bond Strength for Melted EVA Glue on Particle Boards with Different Edge Banding Materials. In Proceedings of the 5th International Conference on Processing Technologies for the Forest and Bio-Based Products Industries (PTF BPI 2018), Freising/Munich, Germany, 20–21 September 2018; pp. 1–6.
12. Kubit, A.; Zielecki, W.; Kaščák, Ľ.; Szawara, P. Experimental Study of the Impact of Chamfer and Fillet in the Frontal Edge of Adherends on the Fatigue Properties of Adhesive Joints Subjected to Peel. *Technol. I Autom. Montażu* **2023**, *119*, 23–29. [CrossRef]
13. Karaman, A. Effects of Wooden Dowel Species, Edge Banding Thickness, and Adhesive Types on Embedded Strength in Particleboard. *Drv. Ind.* **2022**, *73*, 205–214. [CrossRef]
14. Vassiliou, V.; Barboutis, I. Bending Strength of Furniture Corner Joints Constructed with Insert Fittings. *Ann. Wars. Univ. Life Sci. For. Wood Technol. SGGW* **2009**, *274*, 268–274.
15. Tankut, A.N.; Tankut, N. Investigations the Effects of Fastener, Glue, and Composite Material Types on the Strength of Corner Joints in Case-Type Furniture Construction. *Mater. Des.* **2009**, *30*, 4175–4182. [CrossRef]
16. Yapici, F.; Likos, E.; Esen, R. The Effect of Edge Banding Thickness of Some Trees on Withdrawal Strength of Beech Dowel Pins in Composite Material. *Wood Res.* **2011**, *56*, 601–612.
17. Śmietańska, K.; Mielczarek, M. Strength Properties of Furniture Corner Joints Constructed with Different Wooden Connectors and Wood-Based Materials. *Ann. Wars. Univ. Life Sci.-SGGW. For. Wood Technol.* **2022**, *118*, 55–66. [CrossRef]
18. Fathollahzadeh, A.; Enayati, A.A.; Erdil, Y.Z. Effect of Laboratory-Accelerated Aging Treatment on the Ultimate Strength of a 4-Sided MDF Kitchen Cabinet. *Turk. J. Agric. For.* **2013**, *37*, 649–656. [CrossRef]
19. Atar, M.; Özçifçi, A. The Effects of Screw and Back Panels on the Strength of Corner Joints in Case Furniture. *Mater. Des.* **2008**, *29*, 519–525. [CrossRef]
20. Tankut, A.N.; Tankut, N. Effect of Some Factors on the Strength of Furniture Corner Joints Constructed with Wood Biscuits. *Turk. J. Agric. For.* **2004**, *28*, 301–309.
21. European Committee for Standardization. *Paints and Varnishes—Pull-Off Test for Adhesion—Test Method (EN ISO 4624:2017)*; European Committee for Standardization: Geneva, Switzerland, 2017.
22. Džinčić, I.; Palija, T. The Influence of Particleboard Squareness on the Edge Bonding Quality. In Proceedings of the 6th International Scientific Conference "Wood Technology & Product Design", Ohrid, North Macedonia, 13–15 September 2023; pp. 157–162.

23. International Organization for Standardization. *Adhesives—Determination of Strength of Bonded Joints—Part 1: Wedge Rupture Test (ISO 28510-1:2014)*; International Organization for Standardization: Geneva, Switzerland, 2014.
24. European Committee for Standardization. *Wood-Based Panels—Surface Soundness—Test Method (EN 311:2014)*; European Committee for Standardization: Geneva, Switzerland, 2014.
25. Borysiuk, P.; Wacikowski, B.; Jasiński, W.; Adamik, Ł.; Auriga, R. Influence of Edge Band Material on Selected Properties of Particleboard Slats. *Biul. Inf. OB-RPPD* **2023**, *1–2*, 5–13.
26. Lyu, J.; Jiang, L.; Chen, M. Influence of Temperature of Applying Glue, Glue Dosage and Feed Rate on Peel Strength of Edge Band from Curved Edge Part. *IOP Conf. Ser. Mater. Sci. Eng.* **2017**, *274*, 012159. [CrossRef]
27. Ministry of Light Industry of the Republic of China. *Test of Peeling Strength of Soft Covering Material from Furniture (QB/T 3655-1999)*; Ministry of Light Industry of the Republic, Press of China: Beijing, China, 1999.
28. Hlavatý, J.; Tesařová, D. Temperature-Related Resistance of Bonds between Wood Particleboard and Surface Finishing Materials. *Acta Fac. Xylologiae* **2015**, *57*, 89–97.
29. Altinok, M.; Taş, H.H.; Çimen, M. Effects of Combined Usage of Traditional Glue Joint Methods in Box Construction on Strength of Furniture. *Mater. Des.* **2009**, *30*, 3313–3317. [CrossRef]
30. Dizel, T.; Uzun, İ. The Effects of Used Glue Type That Jointed with Particalboard on the Edge Bonding Strength. *Artvin Çoruh Univ. Fac. For. J.* **2007**, *8*, 15–25.
31. Imirzi, H.O.; Ozkaya, K.; Efe, H. Determination of the Strength of L-Type Corner Joints Obtained from Wood-Based Board Materials Using Different Joining Techniques. *Prod. J.* **2016**, *66*, 214–224. [CrossRef]
32. Szwajka, K.; Trzepieciński, T. The Influence of Machining Parameters and Tool Wear on the Delamination Process during Milling of Melamine-Faced Chipboard. *Drewno* **2017**, *60*, 117–131. [CrossRef]
33. Triboulot, P.; Sales, C.; Zerizer, A.; Martin, P. Correlation of Fracture Toughness of Bonded Joints with Quality (Roughness) of Knife-Planed MDF Surfaces. *Holzforschung* **1995**, *49*, 465–470. [CrossRef]
34. Institute of Turkish Standards. *Wood Joints—The Rule of Dowel Joints TS 4539 (1983)*; Institute of Turkish Standards: Ankara, Turkey, 1983.
35. American Society for Testing and Materials. *Standard Methods of Evaluating the Wood-Base Fiber and Particle Materials (ASTM D1037)*; American Society for Testing and Materials: West Conshohocken, PA, USA, 1988.
36. International Organization for Standardization. *Hygrothermal Performance of Building Materials and Products—Determination of Water Absorption Coefficient by Partial Immersion (ISO 15148:2002)*; International Organization for Standardization: Geneva, Switzerland, 2002.
37. Simek, M.; Haviarova, E.; Eckelman, C. The Effect of End Distance and Number of Ready-Toassemble Furniture Fasteners on Bending Moment Resistance of Corner Joints. *Wood Fiber Sci.* **2010**, *42*, 92–98.
38. Norvydas, V.; Baltrušaitis, A.; Juodeikieno, I. Investigation of Miter Corner Joint Strength of Case Furniture from Particleboard. *Medziagotyra* **2012**, *18*, 352–357. [CrossRef]
39. Kasal, A.; Erdil, Y.Z.; Zhang, J.; Efe, H.; Avci, E. Estimation Equations for Moment Resistances of L-Type Screw Corner Joints in Case Goods Furniture. *Prod. J.* **2008**, *58*, 21–27.
40. Denizli, N. *Improving the Strength and Durability of Panel-Based Cabinet Furniture*; Purdue University: West Lafayette, IN, USA, 2001.
41. Žulj, I.; Župčić, I.; Grbac, I.; Trupković, M. Research of Strength of Corner L Joints. In Proceedings of the 26th International Conference on Wood Science and Technology, ICWST 2015: Implementation of Wood Science in Woodworking Sector, Zagreb, Croatia, 16 October 2015; pp. 221–226.
42. Župčić, I.; Žulj, I.; Kamerman, I.; Grbac, I.; Vlaović, Z. Research into Corner L Separable Assemblies in Storage Furniture. *Drv. Ind.* **2021**, *72*, 89–98. [CrossRef]
43. Vassiliou, V.; Barboutis, I. Bending Strength of Corner Joints Constructed with Biscuits. In Proceedings of the International Conference of Nábytok, Zvolen, Slovakia, 13–15 May 2008; pp. 1–8.
44. Vassiliou, V.; Barboutis, I. Screw Withdrawal Capacity Used in the Eccentric Joints of Cabinet Furniture Connectors in Particleboard and MDF. *J. Wood Sci.* **2005**, *51*, 572–576. [CrossRef]
45. Smardzewski, J. The Reliability of Joints and Cabinet Furniture. *Wood Res.* **2009**, *54*, 67–76.
46. Prekrat, S.; Janković, L.; Brezović, M. Design Analysis of Showcase Cabinet with Console Shelves. In Proceedings of the 29th International Conference Research for Furniture Industry, Ankara, Turkey, 19–20 September 2019; pp. 2–9.
47. Máchová, E.; Langová, N.; Réh, R.; Joščák, P.; Krišťák, L.; Holouš, Z.; Igaz, R.; Hitka, M. Effect of Moisture Content on the Load Carrying Capacity and Stiffness of Corner Wood-Based and Plastic Joints. *Bioresources* **2019**, *14*, 8641–8655. [CrossRef]
48. Malkoçoğlu, A.; Yerlikaya, N.Ç.; Çakiroğlu, F.L. Effects of Number and Distance between Dowels of Ready-to-Assemble Furniture on Bending Moment Resistance of Corner Joints. *Wood Res.* **2013**, *58*, 671–680.
49. Lu, G.; Xiong, X.; Lu, D. Research on Visualization Method of Edge Banding Appear-Ance Quality Based on YOLOv7. *Xresearch Squarex* **2023**, 1–19. [CrossRef]
50. Antal, M.R.; Dénes, L.; Vas, Z.A.; Polgár, A. Comparative Study of Conventional and Zero-Joint Edgebanding. *Acta Silv. Lignaria Hung.* **2021**, *17*, 21–35. [CrossRef]

51. Yerlikaya, N.C. Failure Load of Corner Joints, Which Are Reinforced with Glass-Fiber Fabric in Case-Type Furniture. *Sci. Res. Essays* **2013**, *8*, 325–339.
52. Denkena, B.; Köhler, J.; Mengesha, M.S. Influence of the Cutting Edge Rounding on the Chip Formation Process: Part 1. Investigation of Material Flow, Process Forces, and Cutting Temperature. *Prod. Eng.* **2012**, *6*, 329–338. [CrossRef]

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.