

Synthesis and Photophysical Characterization of 2'-Aminochalcones [†]

Cátia I. C. Esteves ¹, Luís F. B. Fontes ^{1,2}, A. Filipa N. Borges ¹, João Rocha ², Artur M. S. Silva ¹ and Samuel Guieu ^{1,2,*}

¹ LAQV-REQUIMTE; catiaiesteves@ua.pt (C.I.C.E.); lfontes@ua.pt (L.F.B.F.); filipa.borges@ua.pt (A.F.N.B.); artur.silva@ua.pt (A.M.S.S.); sguieu@ua.pt (S.G.)

² CICECO-Aveiro Institute of Materials, Universidade de Aveiro, Campus de Santiago, 3810-193 Aveiro, Portugal; rocha@ua.pt

* Correspondence: sguieu@ua.pt

[†] Presented at the 24th International Electronic Conference on Synthetic Organic Chemistry, 15 November–15 December 2020; Available online: <https://ecsoc-24.sciforum.net/>.

Abstract: Chalcones present biological activity and are, therefore, currently studied for their therapeutic potential. They have shown antitumor, anti-inflammatory, antifungal and antibacterial properties. These compounds occur in nature as secondary metabolites of plants and are precursors of flavonoid biosynthesis. Generally, they are not luminescent, but derivatives with some particular patterns of substitution can present fair quantum yields. Excited State Intramolecular Proton Transfer (ESIPT) is a particular case of tautomerization, and some molecules can exhibit ESIPT fluorescence if their structures incorporate an intramolecular hydrogen bonding interaction between a hydrogen donor (-OH or -NH) and a hydrogen acceptor. If the dye is fluorescent, emission from both tautomers may be observed, leading to a dual emission. The chalcones with a strong push-pull character, compounds **2c**, **3c** and **4c**, presented dual emission of keto-enol tautomerism as a consequence of ESIPT.

Keywords: aminochalcones; Excited State Intramolecular Proton Transfer; synthesis; fluorescence

Citation: Esteves, C.I.C.E.; Fontes, L.F.B.; Borges, A.F.N.; Rocha, J.; Silva, A.M.S.; Guieu S. Synthesis and Photophysical Characterization of 2'-Aminochalcones. *Chem. Proc.* **2021**, *3*, 29. <https://doi.org/10.3390/ecsoc-24-08301>

Published: 14 November 2020

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2020 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Chalcone (1,3-diphenylprop-2-en-1-one) is an aromatic ketone, where the two aromatic nuclei are joined by an α,β -unsaturated carbonyl bridge, which forms the central nucleus of a variety of important biological compounds [1]. Chalcone exists as *trans* (*E*)- or *cis* (*Z*)-isomers, with the most stable and predominant stereoisomer being the (*E*)-isomer [2]. There are several methods for the synthesis of chalcones, with Claisen-Schmidt condensation being the classic method [3]. Chalcones and their derivatives have been extensively studied because of their wide range of applicability [4]. Chalcones have several applications such as anti-inflammatory, Reference [5] anti-HIV, Reference [6] antibacterial, Reference [7] anticancer, Reference [8] antituberculosis, Reference [9] antileishmanial, Reference [10] therapeutical activity, and Reference [11], among others.


Structural changes in chalcone derivatives can modify different optical properties such as refractive index, absorption magnitude and spectral position, as well as the optical energy gap [4]. These examples indicate that structurally modified chalcones can exhibit variable physical properties.

Within this class of compounds, 2'-aminochalcone derivatives still represent a recent field of investigation [12]. They have antitumor activity [13] and have been shown to be photoprotectors [14].

Generally, they are not luminescent, but derivatives with some particular patterns of substitution can present fair quantum yields [15].

Excited State Intramolecular Proton Transfer (ESIPT) is a particular case of tautomerization, and molecules can exhibit ESIPT fluorescence if their structures incorporate an intramolecular hydrogen bonding interaction between a hydrogen donor (-OH or -NH) and a hydrogen acceptor [16]. The intramolecular hydrogen bond plays a crucial role in the proton transfer process [17]. If the dye is fluorescent, emission from both tautomers may be observed, leading to a dual emission [18]. ESIPT fluorophores have some beneficial photophysical properties such as intense luminescence, photostability and an unusually large Stokes Shift [3]. The proton-transfer tautomer emits fluorescence at longer wavelengths and will result in larger Stokes shifts.

ESIPT is a system with four energy levels ($L \rightarrow L^* \rightarrow E^* \rightarrow E$). The two forms of the chalcone (L and ESIPT form) are in equilibrium (Scheme 1). In the ground state, the chalcone is in the L form. After absorption of a photon, the L^* suffers an ESIPT tautomerization equilibrium to the E^* , and both tautomers can emit light. After relaxation to the E form, the chalcone goes back to the keto form through reverse proton transfer (RPT). This equilibrium may be influenced by the environment of the chalcone, especially the polarity and proticity of the solvent, leading to different proportion of both tautomers, and therefore to different emission intensities in the two bands when dual emission is observed. As such, these fluorophores may be found in such applications as molecular probes, giving an insight into the properties of their environment, including the polarity of an organelle.

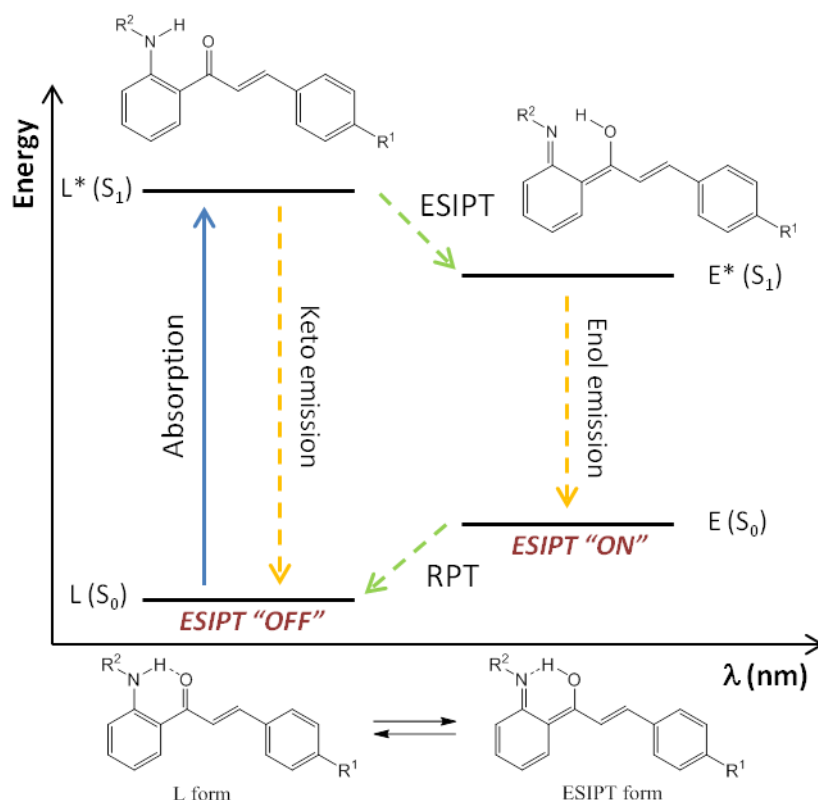

Scheme 1. Description of the Excited State Intramolecular Proton Transfer (ESIPT) process [16].

Here, we report the synthesis and photophysical characterizations of 2'-aminochalcones, substituted with electron donating or withdrawing groups, which could be used as markers to study the environment of cellular organelles.

2. Experimental

2.1. General Procedure for the Synthesis of 2'-Aminochalcones **2a–c**

The 2'-aminochalcone derivatives were obtained via aldol condensation reaction of 2'-aminoacetophenone (2 mmol) with the appropriate substituted benzaldehyde **1a–c** (2

mmol) catalyzed by potassium hydroxide (4 mmol) in methanol (5 mL). The reaction mixture was stirred at 60 °C overnight followed by addition of H₂O (100 mL), the pH was adjusted to 3–4 with dilute HCl and the solution extracted with CH₂Cl₂ (3 × 30 mL). The organic layer was collected, dried over anhydrous sodium sulfate, and the solution was concentrated to dryness. The resulting oil was purified by silica gel column chromatography, using dichloromethane as eluent.

2.1.1. (E)-1-(2-aminophenyl)-3-(4-methylphenyl)prop-2-en-1-one (**2a**)

The product was isolated as a yellow solid (1.139 g, 4.81 mmol, 80%). M.p. = 91–92 °C. ¹H NMR (300 MHz, CDCl₃) δ = 2.39 (s, 3H, CH₃), 6.44 (br s, 2H, NH₂), 6.71 (d, *J* = 8.1 Hz, 1H, H-3), 6.72 (dt, *J* = 8.1 and 1.2 Hz, 1H, H-4), 7.22 (d, *J* = 8.1 Hz, 2H, H-3',5'), 7.30 (dt, *J* = 8.1 Hz, 1.2 Hz, 1H, H-4), 7.54 (d, *J* = 8.1 Hz, 2H, H-2',6'), 7.61 (d, *J* = 15.6 Hz, 1H, α-H), 7.78 (d, *J* = 15.3 Hz, 1H, β-H), 7.89 (dd, *J* = 8.1 and 1.2 Hz, 1H, H-6) ppm. ¹³C NMR (75 MHz, CDCl₃) δ = 21.6 (CH₃), 115.8 (C-5), 117.4 (C-3), 119.2 (C-1), 122.1 (α-C), 128.4 (C-2',6'), 129.7 (C-3',5'), 131.1 (C-6), 132.6 (C-1'), 134.3 (C-4), 140.6 (C-4'), 143.0 (β-C), 151.2 (C-2), 191.8 (CO) ppm. MS *m/z* (ESI %): 238.1 ([M+H]⁺); HMRS: *m/z* (ESI) calc. for C₁₆H₁₆NO 238.1226, found 238.1230. UV/Vis (CHCl₃, nm): λ_{max} (log ε) = 317 (4.59).

2.1.2. (E)-1-(2-aminophenyl)-3-(4-methoxyphenyl)prop-2-en-1-one (**2b**)

The product was isolated as a dark yellow solid (0.214 g, 0.81 mmol, 43%). M.p. = 68–69 °C. ¹H NMR (300 MHz, CDCl₃) δ = 3.81 (s, 3H, OCH₃), 6.25 (br s, 2H, NH₂), 6.65–6.70 (m, 2H, H-3 and H-5), 6.90 (d, *J* = 8.8 Hz, 2H, H-3',5'), 7.26 (dt, *J* = 8.4 and 1.5 Hz, 1H, H-4), 7.48 (d, *J* = 15.6 Hz, 1H, α-H), 7.56 (d, *J* = 8.8 Hz, 2H, H-2',6'), 7.71 (d, *J* = 15.6 Hz, 1H, β-H), 7.84 (dd, *J* = 8.4 and 1.5 Hz, 1H, H-6) ppm. ¹³C NMR (75 MHz, CDCl₃) δ = 55.4 (OCH₃), 114.4 (C-3',5'), 115.8 (C-5), 117.3 (C-3), 119.3 (C-1), 120.8 (α-C), 128.0 (C-1'), 130.0 (C-2',6'), 130.9 (C-6), 134.1 (C-4), 142.8 (β-C), 151.0 (C-2), 161.3 (C-4'), 191.8 (CO) ppm. MS *m/z* (ESI %): 254.1 ([M+H]⁺); HMRS: *m/z* (ESI) calc. for C₁₆H₁₆NO₂ 254.1176, found 254.1172. UV/Vis (CHCl₃, nm): λ_{max} (log ε) = 333 (4.51).

2.1.3. (E)-1-(2-aminophenyl)-3-[4-(dimethylamino)phenyl]prop-2-en-1-one (**2c**)

The product was isolated as an orange solid (1.210 g, 4.51 mmol, 75%). M.p. = 120–121 °C. ¹H NMR (300 MHz, CDCl₃) δ = 3.00 (s, 6H, N(CH₃)₂), 6.26 (br s, 2H, NH₂), 6.67 (d, *J* = 8.7 Hz, 2H, H-3',5'), 6.66–6.71 (m, 2H, H-3 and H-5), 7.25 (dt, *J* = 8.1 and 1.2 Hz, 1H, H-4), 7.41 (d, *J* = 15.4 Hz, 1H, α-H), 7.52 (d, *J* = 8.7 Hz, 2H, H-2',6'), 7.73 (d, *J* = 15.4 Hz, 1H, β-H), 7.86 (dd, *J* = 8.1 and 1.2 Hz, 1H, H-6) ppm. ¹³C NMR (75 MHz, CDCl₃) δ = 40.2 (N(CH₃)₂), 111.9 (C-3',5'), 115.8 (C-5), 117.3 (C-3), 117.9 (α-C), 119.9 (C-1), 123.0 (C-1'), 130.2 (C-2',6'), 130.8 (C-6), 133.7 (C-4), 144.0 (β-C), 150.7 (C-2), 151.8 (C-4'), 192.0 (CO) ppm. MS *m/z* (ESI %): 267.1 ([M+H]⁺); HMRS: *m/z* (ESI) calc. for C₁₇H₁₉N₂O 267.1492, found 267.1499. UV/Vis (CHCl₃, nm): λ_{max} (log ε) = 418 (4.59).

2.2. General Procedure for the Synthesis of 2'-(methanesulfonylamino)chalcones **3a–c**

2'-Aminochalcone derivatives **2a–c** (1 mmol), methane sulfonyl chloride (1 mmol) and triethylamine (1 mmol) were stirred in dichloromethane (5 mL) overnight at room temperature. Following the addition of H₂O (50 mL), the pH was neutralized with dilute HCl and the solution extracted with CH₂Cl₂ (3 × 20 mL). The organic layer was collected, dried over anhydrous sodium sulfate, and the solution was concentrated to dryness. The resulting solid was purified by silica gel column chromatography, using dichloromethane as eluent.

2.2.1. (E)-N-[2-[3-(4-methylphenyl)acryloyl]phenyl]methanesulfonamide (**3a**)

The product was isolated as a yellow solid (0.148 g, 0.47 mmol, 56%) M.p. = 125–126 °C. ¹H NMR (300 MHz, CDCl₃) δ = 2.40 (s, 3H, CH₃), 3.06 (s, 3H, SO₂CH₃), 7.21 (dt, *J* = 7.8 and 1.2 Hz, 1H, H-5), 7.24 (d, *J* = 8.4 Hz, 2H, H-3',5'), 7.55 (d, *J* = 15.5 Hz, 1H, α-H), 7.56 (d, *J* =

8.4 Hz, 2H, H-2',6'), 7.57 (dt, $J = 7.8$ and 1.2 Hz, 1H, H-4), 7.79 (dd, $J = 8.4$ and 1.2 Hz, 1H, H-3), 7.83 (d, $J = 15.5$ Hz, 1H, β -H), 8.03 (dd, $J = 7.8$ and 1.2 Hz, 1H, H-6), 11.27 (br s, 1H, NH) ppm. ^{13}C NMR (75 MHz, CDCl_3) $\delta = 21.6$ (CH_3), 40.1 (SO_2CH_3), 118.8 (C-3), 120.7 (α -C), 122.8 (C-5), 123.6 (C-1'), 128.8 (C-2',6'), 129.8 (C-3',5'), 131.1 (C-6), 131.7 (C-2), 134.8 (C-4), 140.6 (C-1), 141.8 (C-4'), 146.4 (β -C), 192.7 (CO) ppm. MS m/z (ESI %): 316.1 ($[\text{M}+\text{H}]^+$); HMRS: m/z (ESI) calc. for $\text{C}_{17}\text{H}_{18}\text{NO}_3\text{S}$ 316.1002, found 316.1008. UV/Vis (CHCl_3 , nm): λ_{max} (log ϵ) = 336 (4.56).

2.2.2. (E)-N-[2-[3-(4-methoxyphenyl)acryloyl]phenyl]methanesulfonamide (**3b**)

The product was isolated as a yellow solid (0.109 g, 0.33 mmol, 42%). M.p. = 135–136 °C. ^1H NMR (300 MHz, CDCl_3) $\delta = 3.06$ (s, 3H, SO_2CH_3), 3.86 (s, 3H, OCH_3), 6.94 (d, $J = 8.7$ Hz, 2H, H-3',5'), 7.21 (dt, $J = 8.1$ and 1.2 Hz, 1H, H-5), 7.46 (d, $J = 15.3$ Hz, 1H, α -H), 7.56 (dt, $J = 8.1$ and 1.2 Hz, 1H, H-4), 7.60 (d, $J = 8.7$ Hz, 2H, H-2',6'), 7.77 (dd, $J = 8.1$ and 1.2 Hz, 1H, H-3), 7.81 (d, $J = 15.3$ Hz, 1H, β -H), 8.03 (dd, $J = 8.1$ and 1.2 Hz, 1H, H-6), 11.32 (br s, 1H, NH) ppm. ^{13}C NMR (75 MHz, CDCl_3) $\delta = 40.1$ (SO_2CH_3), 50.5 (OCH_3), 114.6 (C-3',5'), 118.8 (C-3), 119.3 (α -C), 122.8 (C-5), 123.7 (C-1), 127.2 (C-1'), 130.6 (C-2',6'), 131.0 (C-6), 134.7 (C-4), 140.6 (C-2), 146.2 (β -C), 162.2 (C-4'), 192.6 (CO) ppm. MS m/z (ESI %): 332.1 ($[\text{M}+\text{H}]^+$); HMRS: m/z (ESI) calc. for $\text{C}_{17}\text{H}_{18}\text{NO}_4\text{S}$ 332.0951, found 332.0965. UV/Vis (CHCl_3 , nm): λ_{max} (log ϵ) = 361 (4.57).

2.2.3. (E)-N-[2-[3-(4-(dimethylamino)phenyl)acryloyl]phenyl]methanesulfonamide (**3c**)

The product was isolated as a red solid (0.142 g, 0.41 mmol, 55%). M.p. = 155–156 °C. ^1H NMR (300 MHz, CDCl_3) $\delta = 3.03$ (s, 3H, SO_2CH_3), 3.06 (s, 6H, $\text{N}(\text{CH}_3)_2$), 6.69 (d, $J = 8.8$ Hz, 2H, H-3',5'), 7.19 (dt, $J = 8.1$ and 1.2 Hz, 1H, H-5), 7.36 (d, $J = 15.0$ Hz, 1H, α -H), 7.53 (dt, $J = 8.1$ and 1.2 Hz, 1H, H-4), 7.55 (d, $J = 8.8$ Hz, 2H, H-2',6'), 7.77 (dd, $J = 8.1$ and 1.2 Hz, 1H, H-3), 7.83 (d, $J = 15.0$ Hz, 1H, β -H), 8.02 (dd, $J = 8.1$ and 1.2 Hz, 1H, H-6), 11.40 (br s, 1H, NH) ppm. ^{13}C NMR (75 MHz, CDCl_3) $\delta = 39.9$ (SO_2CH_3), 40.1 ($\text{N}(\text{CH}_3)_2$), 111.8 (C-3',5'), 116.0 (α -C), 119.1 (C-3), 122.1 (C-1'), 122.8 (C-5), 124.5 (C-1), 130.7 (C-6), 131.0 (C-2',6'), 134.1 (C-4), 140.3 (C-2), 147.5 (β -C), 152.5 (C-4'), 192.4 (CO) ppm. MS m/z (ESI %): 345.1 ($[\text{M}+\text{H}]^+$); HMRS: m/z (ESI) calc. for $\text{C}_{18}\text{H}_{21}\text{N}_2\text{O}_3\text{S}$ 345.1267, found 345.1263. UV/Vis (CHCl_3 , nm): λ_{max} (log ϵ) = 439 (4.65).

2.3. General Procedure for the Synthesis of 2'-(Acetylaminophenyl)Chalcones **4a–c**

2'-Aminochalcone derivatives **2a–c** (1 mmol), acetyl chloride (1 mmol) and triethylamine (1 mmol) in dichloromethane (5 mL) were stirred overnight at room temperature. Following the addition of H_2O (50 mL), the pH was neutralized with dilute HCl and the solution extracted with CH_2Cl_2 (3×20 mL). The organic layer was collected, dried over anhydrous sodium sulfate, and the solution was concentrated to dryness. The resulting solid was purified by silica gel column chromatography, using dichloromethane as eluent.

2.3.1. (E)-N-[2-[3-(4-methylphenyl)acryloyl]phenyl]acetamide (**4a**)

The product was isolated as a yellow solid (0.118 g, 0.42 mmol, 84%). M.p. = 121–122 °C. ^1H NMR (300 MHz, CDCl_3) $\delta = 2.25$ (s, 3H, COCH_3), 2.41 (s, 3H, CH_3), 7.16 (dt, $J = 8.2$ and 1.2 Hz, 1H, H-5), 7.25 (d, $J = 8.4$ Hz, 2H, H-3',5'), 7.52 (d, $J = 15.6$ Hz, 1H, α -H), 7.55 (d, $J = 8.4$ Hz, 2H, H-2',6'), 7.56 (dt, $J = 8.2$ and 1.2 Hz, 1H, H-4), 7.79 (d, $J = 15.6$ Hz, 1H, β -H), 7.97 (dd, $J = 8.2$ and 1.2 Hz, 1H, H-3), 8.70 (d, $J = 8.2$ Hz, 1H, H-6), 11.55 (br s, 1H, NH) ppm. ^{13}C NMR (75 MHz, CDCl_3) $\delta = 21.6$ (CH_3), 25.5 (COCH_3), 121.2 (C-6), 121.8 (α -C), 122.4 (C-5), 123.5 (C-1), 128.7 (C-2',6'), 129.8 (C-3',5'), 130.5 (C-3), 131.9 (C-1'), 134.6 (C-4), 141.0 (C-2), 141.6 (C-4'), 145.8 (β -C), 169.4 (COCH_3), 193.5 (CO) ppm. MS m/z (ESI %): 280.1 ($[\text{M}+\text{H}]^+$); HMRS: m/z (ESI) calc. for $\text{C}_{18}\text{H}_{18}\text{NO}_2$ 280.1332, found 280.1337. UV/Vis (CHCl_3 , nm): λ_{max} (log ϵ) = 334 (4.49).

2.3.2. (E)-N-[2-[3-(4-methoxyphenyl)acryloyl]phenyl]acetamide (**4b**)

The product was isolated as a yellow solid (0.101 g, 0.34 mmol, 43%). M.p. = 121–122 °C. ^1H NMR (300 MHz, CDCl_3) δ = 2.23 (s, 3H, COCH_3), 3.84 (s, 3H, OCH_3), 6.93 (d, J = 8.7 Hz, 2H, H-3',5'), 7.13 (dt, J = 8.1 and 1.2 Hz, 1H, H-5), 7.42 (d, J = 15.6 Hz, 1H, α -H), 7.53 (dt, J = 8.1 and 1.2 Hz, 1H, H-4), 7.59 (d, J = 8.7 Hz, 2H, H-2',6'), 7.76 (d, J = 15.6 Hz, 1H, β -H), 7.94 (dd, J = 8.1 and 1.2 Hz, 1H, H-3), 8.69 (dd, J = 8.1 and 1.2 Hz, 1H, H-6) 11.58 (br s, 1H, NH) ppm. ^{13}C NMR (75 MHz, CDCl_3) δ = 25.5 (COCH_3), 55.4 (OCH_3), 114.5 (C-3',5'), 120.3 (α -C), 121.1 (C-6), 122.4 (C-5), 123.6 (C-1), 127.3 (C-1'), 130.4 (C-3), 130.5 (C-2',6'), 134.4 (C-4), 140.9 (C-2), 145.5 (β -C), 162.0 (C-4'), 169.3 (COCH_3), 193.3 (CO) ppm. MS m/z (ESI %): 296.1 ($[\text{M}+\text{H}]^+$); HMRS: m/z (ESI) calc. for $\text{C}_{18}\text{H}_{18}\text{NO}_3$ 296.1281, found 296.1272. UV/Vis (CHCl_3 , nm): λ_{max} (log ϵ) = 359 (4.54).

2.3.3. (E)-N-(2-[3-(4-(dimethylamino)phenyl)acryloyl]phenyl)acetamide (4c)

The product was isolated as an orange solid (0.162 g, 0.52 mmol, 66%). M.p. = 129–131 °C. ^1H NMR (300 MHz, CDCl_3) δ = 2.23 (s, 3H, COCH_3), 3.04 (s, 6H, $\text{N}(\text{CH}_3)_2$), 6.67 (d, J = 8.7 Hz, 2H, H-3',5'), 7.13 (dt, J = 8.1 and 1.2 Hz, 1H, H-5), 7.34 (d, J = 15.3 Hz, 1H, α -H), 7.51 (dt, J = 8.1 and 1.2 Hz, 1H, H-4), 7.54 (d, J = 8.7 Hz, 2H, H-2',6'), 7.78 (d, J = 15.3 Hz, 1H, β -H), 7.95 (dd, J = 8.1 and 1.2 Hz, H-3), 8.68 (dd, J = 8.1 and 1.2 Hz, 1H, H-6), 11.66 (br s, 1H, NH) ppm. ^{13}C NMR (75 MHz, CDCl_3) δ = 25.5 (COCH_3), 3.04 ($\text{N}(\text{CH}_3)_2$), 111.8 (C-3',5'), 117.2 (α -C), 121.0 (C-6), 122.3 (C-1'), 122.3 (C-5), 124.3 (C-1), 130.2 (C-3), 130.8 (C-2',6'), 133.8 (C-4), 140.7 (C-2), 146.8 (β -C), 152.3 (C-4'), 169.3 (COCH_3), 193.2 (CO) ppm. MS m/z (ESI %): 309.2 ($[\text{M}+\text{H}]^+$); HMRS: m/z (ESI) calc. for $\text{C}_{19}\text{H}_{21}\text{N}_2\text{O}_2$ 309.1598, found 309.1595. UV/Vis (CHCl_3 , nm): λ_{max} (log ϵ) = 432 (4.61).


2.4. Photophysical Characterization of 2'-aminochalcones 2, 3 and 4

Solutions of 2'-aminochalcones **2a–c**, **3a–c** and **4a–c** (10^{-4} to 10^{-6} M) were prepared in solvents with different character (polar-apolar, protic-aprotic), and their absorption and emission spectra were recorded. Relative fluorescence quantum yields were calculated using fluorescein (Φ_F = 0.95 in NaOH 0.1 M) and anthracene (Φ_F = 0.27 in ethanol) as standard [19].

3. Results and Discussion

3.1. Synthesis

The synthetic route chosen to obtain the 2'-aminochalcones comprised two steps (Scheme 1). First, the aminochalcones were synthesized by base-catalyzed aldol condensation using potassium hydroxide, in 43–80% yields. Then, the electron-withdrawing groups were introduced to obtain the final compounds **3** (sulfonamide formation) and **4** (acylation), in 42–84% yields. All new compounds were fully characterized by ^1H -NMR, ^{13}C -NMR and MS.

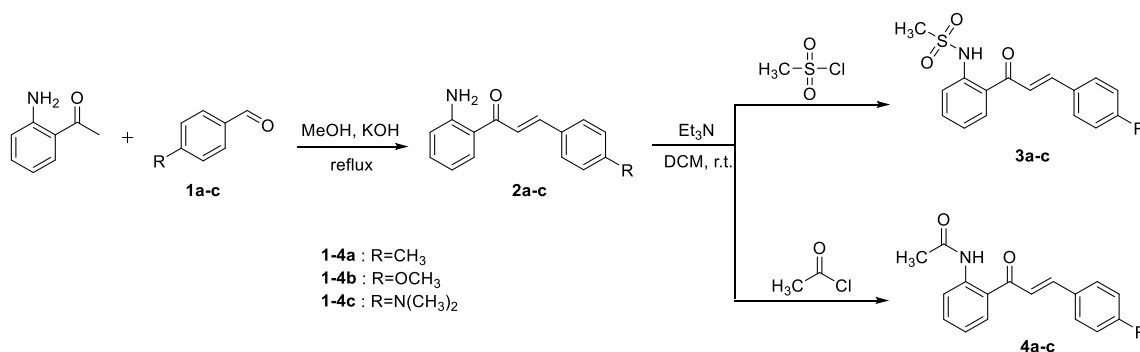

Scheme 2. Synthesis of the 2'-aminochalcones **2a–c**, **3a–c** and **4a–c**.

The main features of the ^1H NMR spectra of compounds **2**, **3** and **4** are the signals corresponding to the vinylic protons of their characteristic α,β -unsaturated moieties. The protons H- α and H- β appear at δ 7.34–7.61 and 7.71–7.83 ppm, respectively, as two doublets with a coupling constant of ca. 15 Hz, which indicates an (*E*)-configuration for the vinylic system. Another important characteristic of the ^1H NMR spectra of **3** and **4** is a singlet with high frequency values (δ 11.27–11.66 ppm) attributed to 2'-NH₂, due to the intramolecular hydrogen bond with the carbonyl group. This signal is not observed for compounds **2a–c** that have a broad singlet with lower frequency values, between 6.25 and 6.44 ppm.

3.2. Photophysical Study of 2'-Aminochalcones **2**, **3** and **4**

The photophysical properties of the chalcones **2a–c**, **3a–c** and **4a–c** were evaluated. First, the absorption and emission spectra of all compounds were measured in acetonitrile (Figures 1 and 2). The 2'-aminochalcones **2–4** show low to moderate fluorescence quantum yields, and large Stokes' shifts (5058–9883 cm^{−1}) (Table 1). The influence of the electron-donating group is observed, and compounds **2c**, **3c** and **4c**, bearing a dimethylamino substituent, present a red shift on the absorption and emission maxima. They are also more emissive, with higher quantum yields of 0.03–0.35. For some compounds, the emission profile is not symmetric, and a second emission band appears with a lower intensity. This is consistent with the proposed ESIPT model.

Table 1. UV-visible absorption and emission data for 2'-aminochalcones **2**, **3** and **4** in organic solvents with different characteristics.

Cpd	Solvent (π^*)	UV/Vis		Fluorescence		
		λ_{max} (nm)	$\log \epsilon$	λ_{em} (nm)	Stokes' Shift (cm ^{−1})	Φ_F
2a	Diethyl ether (0.27)	308	4.58	---	---	---
	Chloroform (0.58)	317	4.59	459	9759	<0.01
	ACN (0.75)	311	4.57	449	9883	<0.01
	DMSO (1.00)	317	4.57	460	9807	<0.01
2b	Diethyl ether (0.27)	324	4.51	---	---	---
	Chloroform (0.58)	333	4.51	455	8052	<0.01
	ACN (0.75)	327	4.52	448	8260	<0.01
	DMSO (1.00)	335	4.52	454	7824	<0.01
2c	Diethyl ether (0.27)	404	4.58	493	4468	<0.01
	Chloroform (0.58)	418	4.59	497/532	3803/5126	0.03
	ACN (0.75)	418	4.57	540	5405	0.03
	DMSO (1.00)	429	4.58	540	4792	0.03
3a	Diethyl ether (0.27)	329	4.57	417/441	6414/7719	<0.01
	Chloroform (0.58)	336	4.56	440	7035	<0.01
	ACN (0.75)	333	4.59	438	7199	<0.01
	DMSO (1.00)	332	4.58	413/438	5907/7289	<0.01
3b	Diethyl ether (0.27)	354	4.53	---	---	---
	Chloroform (0.58)	361	4.57	454	5674	<0.01
	ACN (0.75)	358	4.50	445	5461	<0.01
	DMSO (1.00)	363	4.52	455	5570	<0.01
3c	Diethyl ether (0.27)	424	4.62	---	---	---
	Chloroform (0.58)	439	4.66	535	4087	0.10
	ACN (0.75)	437	4.60	561	5058	0.10
	DMSO (1.00)	445	4.61	557	4519	0.11
4a	Diethyl ether (0.27)	325	4.51	---	---	---

	Chloroform (0.58)	334	4.49	440	7213	<0.01
	ACN (0.75)	326	4.49	432	7527	<0.01
	DMSO (1.00)	327	4.50	458	8747	<0.01
4b	Diethyl ether (0.27)	349	4.53	---	---	---
	Chloroform (0.58)	359	4.54	437	4972	<0.01
	ACN (0.75)	352	4.51	431	5207	<0.01
	DMSO (1.00)	352	4.52	437	5526	<0.01
4c	Diethyl ether (0.27)	417	4.59	492	3656	<0.01
	Chloroform (0.58)	432	4.61	553	5065	0.32
	ACN (0.75)	428	4.60	556	5379	0.35
	DMSO (1.00)	437	4.60	558	4962	0.36

Considering the results obtained in acetonitrile, the photophysical properties of 2'-aminochalcones **2**, **3** and **4** were evaluated in other organic solvents presenting different polarity. The solvents tested were dimethylsulfoxide, chloroform and diethyl ether, as examples of solvents with different polarity and proticity, with π^* values determined by Kamlet and Taft [20] indicating the ability of a particular solvent to stabilize a charge or a dipole due to its dielectric effect, normalized between cyclohexane ($\pi^* = 0$) and DMSO ($\pi^* = 1$). The collected data revealed similar maxima wavelengths of absorption, but some differences in the emission maxima wavelengths (two maxima can be observed in some solvents, for compounds **2c**, **3a**, **3c** and **4c**) and the fluorescence quantum yield do not vary significantly (Table 1). The general trend revealed that 2'-aminochalcone **4c** (*para*-position of ring B with dimethylamine and in ring A the acetyl-protected amine group) is the most fluorescent (with Φ_F in the range of 0.32–0.36).

The absorption and emission spectra of **2c** and **4c** in different solvent are presented in Figures 3 and 4. For both compounds, a small shift is observed in the absorption spectra in different solvents, probably due to the solvatochromism expected for push–pull dyes. Two emission bands are clearly visible for **2c**, with variable intensities depending on the solvent. They are less obvious for **4c**. In diethyl ether (less polar solvent), the band at shorter wavelengths is predominant, corresponding to the L form (Scheme 1). In DMSO and ACN (more polar), the band at longer wavelengths is predominant, corresponding to the E form. In Chloroform, both bands are present, witnessing the ESIPT equilibrium. These bands are probably merged into a single one for **4c**.

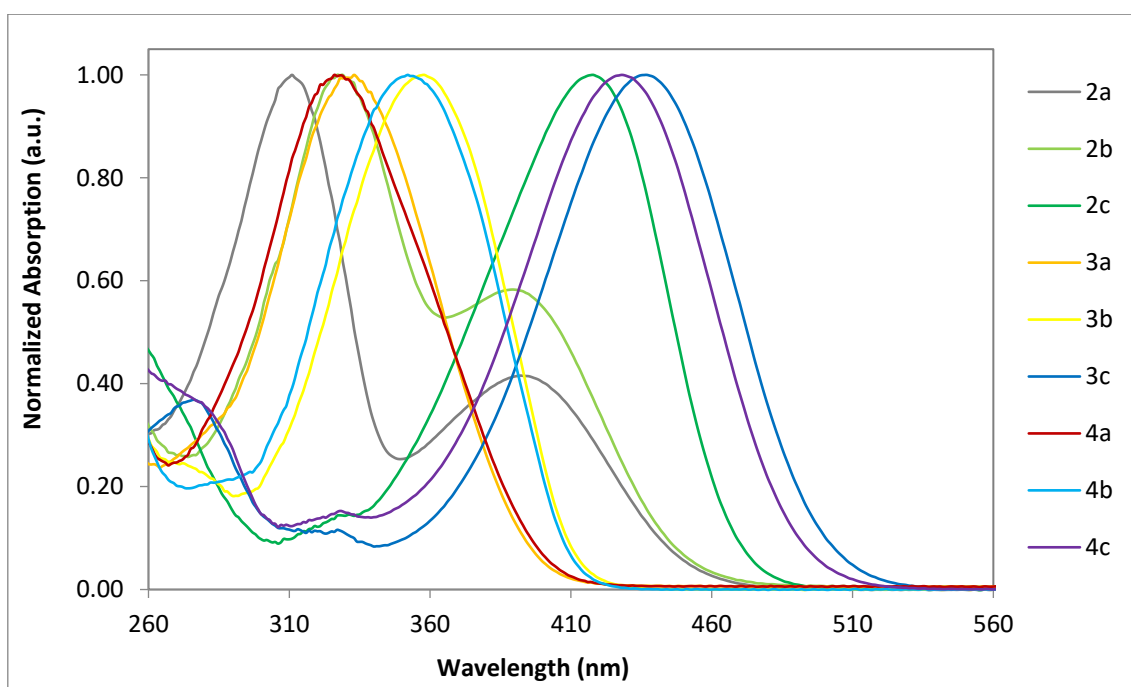


Figure 1. Normalized absorption spectra of 2'-aminochalcones **2**, **3** and **4** in acetonitrile.

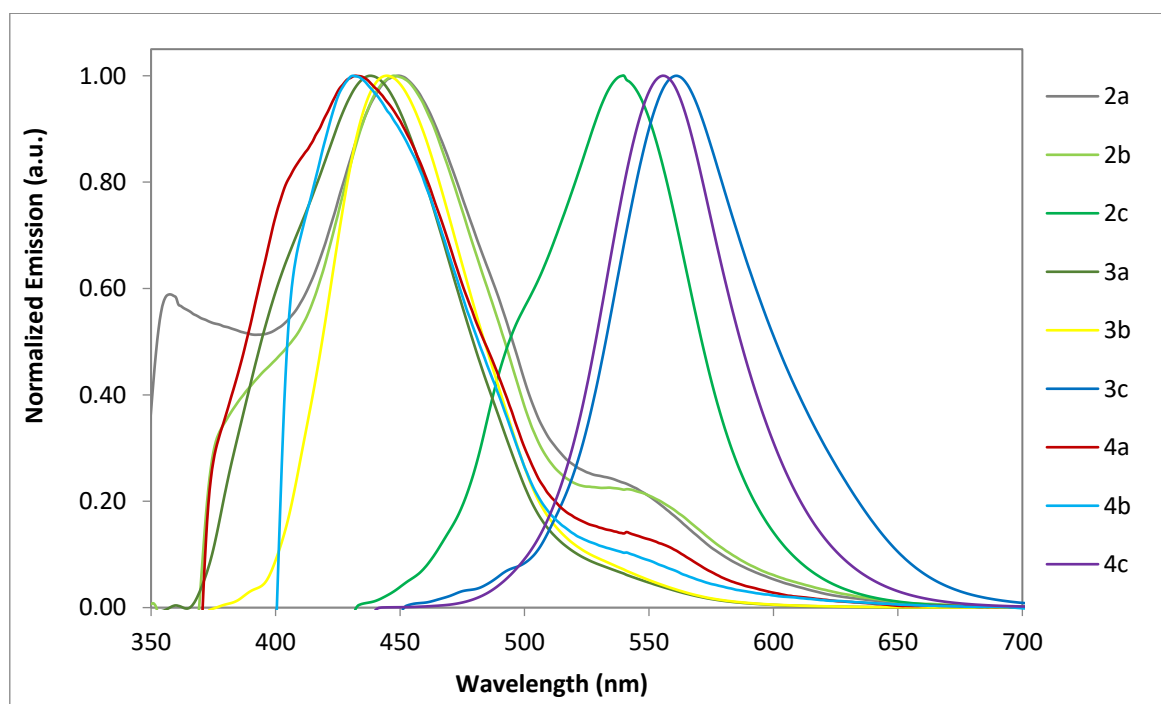


Figure 2. Normalized emission spectra of 2'-aminochalcones **2**, **3** and **4** in acetonitrile.

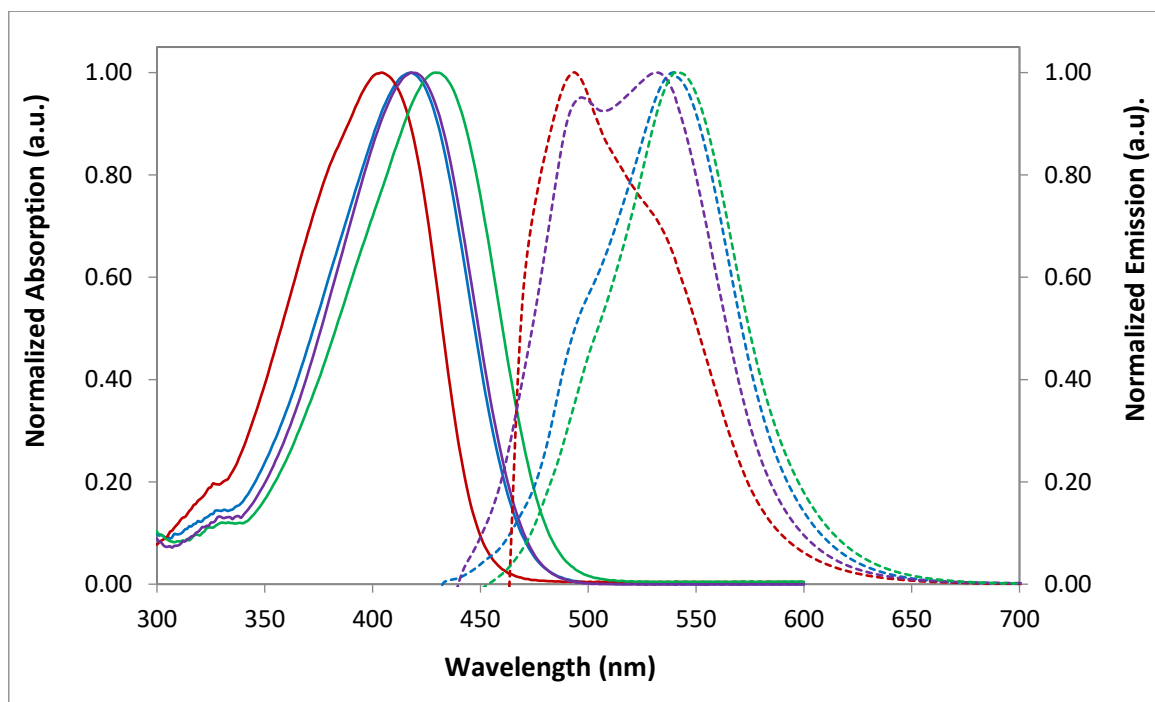


Figure 3. Normalized absorption and emission spectra of chalcone **2c** in acetonitrile, diethyl ether, chloroform and dimethyl sulfoxide (λ_{exc} = 418 nm, 404 nm, 418 nm and 429 nm, respectively; absorption, full line; emission, dotted line).

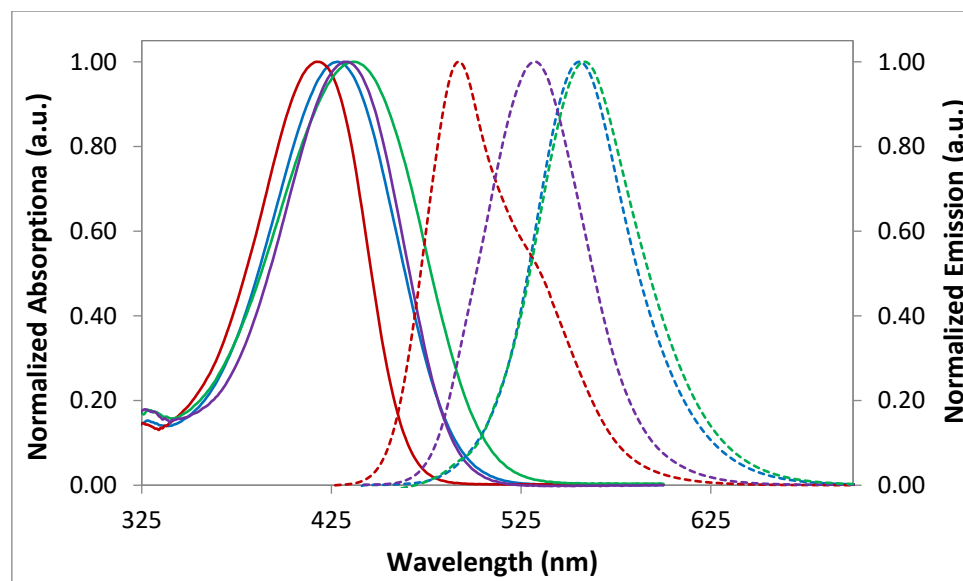


Figure 4. Normalized absorption and emission spectra of chalcone **4c** in acetonitrile, diethyl ether, chloroform and dimethyl sulfoxide (λ_{exc} = 428 nm, 417 nm, 432 nm and 437 nm, respectively; absorption, full line; emission, dotted line).

4. Conclusions

The 2'-aminochalcones **2**, **3** and **4** are emissive, especially derivatives **c** (*N,N*-dimethyl-amine as a substituent) with moderate fluorescence quantum yields (Φ_F = 0.03 for **2c**; Φ_F = 0.10 for **3c**; Φ_F = 0.35 for **4c**) and large Stokes' shifts (5405, 5058 and 5379 cm^{-1} , respectively) in acetonitrile. Compound **4c** (acetyl group as a substituent on the amine) displayed the highest fluorescence. Fluorophores **2c** and **4c** present an interesting ESIPT, with a dual emission. The intensity of each emission band is strongly influenced by the solvent and witnesses a dramatic shift in the ESIPT equilibrium. These compounds could, therefore, find applications as molecular probes of organelles polarity, and this study is ongoing.

Acknowledgments: Thanks are due to University of Aveiro, FCT/MEC, Centro 2020 and Portugal2020, the COMPETE program, and the European Union (FEDER program) via the financial support to the LAQV-REQUIMTE (UIDB/50006/2020), to the CICECO-Aveiro Institute of Materials (UID/CTM/50011/2019, UIDB/50011/2020 and UIDP/50011/2020), financed by national funds through the FCT/MCTES, to the Portuguese NMR Network, and to the PAGE project “Protein aggregation across the lifespan” (CENTRO-01-0145-FRDER-000003, C.I.C. Esteves research contract). SG is supported by national funds (OE), through FCT, I.P., in the scope of the framework contract foreseen in the numbers 4, 5, and 6 of the article 23, of the Decree-Law 57/2016, of August 29, changed by Law 57/2017, of July 19. L.F.B. Fontes thanks the FCT for his PhD grant (SFRH/BD/150663/2020).

References

1. Zhuang, C.; Zhang, W.; Sheng, C.; Zhang, W.; Xing, C.; Miao, V. Chalcone: A privileged structure in medicinal chemistry. *Chem. Rev.* **2017**, *117*, 7762–7810.
2. Gomes, M.N.; Braga, R.C.; Grzelak, E.M.; Neves, B.J.; Muratov, E.; Ma, R.; Klein, L.L.; Cho, S.; Oliveira, G.R.; Franzblau, S.G.; et al. QSAR-driven design, synthesis and discovery of potent chalcone derivatives with antitubercular activity. *Eur. J. Med. Chem.* **2017**, *137*, 126–138.
3. Patil, C.B.; Mahajan, S.K.; Katti, S.A. Chalcone: A Versatile Molecule. *J. Pharm. Sci. Res.* **2009**, *1*, 11–22.
4. Custodio, J.M.F.; Gotardo, F.; Vaz, W.F.; D'Oliveira, G.D.C.; de Almeida, L.R.; Fonseca, R.D.; Cocco, L.H.Z.; Perez, C.N.; Oliver, A.G.; de Boni, L.; et al. Benzenesulfonyl incorporated chalcones: Synthesis, structural and optical properties. *J. Mol. Struct.* **2020**, *1208*, 127845, doi:10.1016/j.molstruc.2020.127845.
5. Li, Y.-Y.; Huang, S.-S.; Lee, M.-M.; Deng, J.-S.; Huang, G.-J. Anti-inflammatory activities of cardamonin from *Alpinia katsumadai* through heme oxygenase-1 induction and inhibition of NF- κ B and MAPK signaling pathway in the carrageenan-induced paw edema. *Int. Immunopharmacol.* **2015**, *25*, 332–339.
6. Cole, A.L.; Hossain, S.; Cole, A.M.; Phanstiel, O. Synthesis and bioevaluation of substituted chalcones, coumaranones and other flavonoids as anti-HIV agents. *Bioorg. Med. Chem.* **2016**, *24*, 2768–2776.
7. Rudrapal, M.; Satyanandam, R.S.; Swaroopini, T.S.; Lakshmi, T.N.; Jaha, S.K.; Zaheera, S. Naga Lakshmi. *Med. Chem. Res.* **2013**, *22*, 2840–2846.
8. Custodio, J.M.F.; Michelini, L.J.; de Castro, M.R.C.; Vaz, W.F.; Neves, B.J.; Cravo, P.V.L.; Barreto, F.S.; Filho, M.O.M.; Perez, C.N.; Napolitano H.B. Structural insights into a novel anticancer sulfonamide chalcone. *New J. Chem.* **2018**, *42*, 3426–3434.
9. Lin, Y.-M.; Zhou, Y.; Flavin, M.T.; Zhou, L.-M.; Nie, W.; Chen, F.-C. Chalcones and flavonoids as anti-tuberculosis agents. *Bioorg. Med. Chem.* **2002**, *10*, 2795–2802.
10. Boeck, P.; Falcao, C.A.B.; Leal, P.C.; Yunes, R.A.; Filho, V.C.; Torres-Santos, E.C.; Rossi-Bergmann, B. Synthesis of chalcone analogues with increased antileishmanial activity. *Bioorg. Med. Chem.* **2006**, *14*, 1538–1545.
11. Mahapatra, D.K.; Bharti, S.K. Therapeutic potential of chalcones as cardiovascular agents. *Life Sci.* **2016**, *148*, 154–172.
12. Sulpizio, C.; Roller, A.; Giester, G.; Rompel, A. Synthesis, structure, and antioxidant activity of methoxy- and hydroxyl-substituted 2'-aminochalcones. *Mon. Chem.* **2016**, *147*, 1747–1757.
13. Pati, H.N.; Holt, H.L., Jr.; LeBlanc, R.; Dickson, J.; Stewart, M.; Brown, T.; Lee, M. Synthesis and Cytotoxic Properties of Nitro- and Aminochalcones. *Med. Chem. Res.* **2005**, *14*, 19–25.
14. Lazópulos, S.Q.; Svarc, F.; Sagrera, G.; Diclilio, L. Absorption and photo-stability of substituted dibenzoylmethanes and chalcones as UVA filters. *Cosmetics* **2018**, *5*, 33.
15. Vaz, P.A.A.M.; Rocha, J.; Silva, A.M.S.; Guieu S. Aggregation-induced emission enhancement in halochalcones. *New J. Chem.* **2016**, *40*, 8198–8201.
16. Sedgeick, A.C.; Wu, L.; Han, H.; Bull, S.D.; He, X.; James, T.D.; Sessler, J.L.; Tang, V.; Tian, H.; Yoon, J. Excited-state intramolecular proton-transfer (ESIPT) based fluorescence sensors and imaging agents. *Chem. Soc. Rev.* **2018**, *47*, 8842–8880.
17. Yin, H.; Li, H.; Xia, G.; Ruan, C.; Shi, Y.; Wang, H.; Jin, M.; Ding, D. A novel non-fluorescent excited state intramolecular proton transfer phenomenon induced by intramolecular hydrogen bonds: an experimental and theoretical investigation. *Sci. Rep.* **2016**, *6*, 19774.
18. Fontes, L.F.B.; Nunes da Silva, R.; Silva, A.M.S.; Guieu, S. Unsymmetrical 2,4,6-Triarylpyridines as Versatile Scaffolds for Deep-Blue and Dual-Emission Fluorophores. *ChemPhotoChem* **2020**, accepted, doi:10.1002/cptc.202000134.
19. Brouwer, A.M. Standards for photoluminescence quantum yield measurements in solution (IUPAC Technical Report). *Pure Appl. Chem.* **2011**, *83*, 2213–2228.
20. Kamlet, M.J.; Abboud, J.L.M.; Abraham, M.H.; Taft, R.W. Linear solvation energy relationships. 23. A comprehensive collection of the solvatochromic parameters, π^* , α , and β , and some methods for simplifying the generalized solvatochromic equation. *J. Org. Chem.* **1983**, *48*, 2877–2887.