

Tapered Optical Fiber for Hydrogen Sensing Application Based on Molybdenum Trioxide (MoO₃)[†]

Mohammed Majeed Alkhabet ^{1,2}, Saad Hayatu Girei ^{1,3}, Suriati Paiman ⁴, Norhana Arsad ⁵,
Mohd Adzir Mahdi ¹ and Mohd Hanif Yaacob ^{1,*}

- ¹ Wireless and Photonics Network Research Centre, Faculty of Engineering, University Putra Malaysia (UPM), Serdang 43000, Selangor, Malaysia; mohammed.alkhabet@gmail.com (M.M.A.); gireisaad3@gmail.com (S.H.G.); mam@upm.edu.my (M.A.M.)
- ² Department of Computer Engineering Techniques, Al-Rasheed University College, Baghdad 10011, Iraq
- ³ Department of Computer Engineering, Federal Polytechnic Mubi, Mubi 650113, Adamawa State, Nigeria
- ⁴ Department of Physical, Faculty of Science, University Putra Malaysia (UPM), Serdang 43000, Selangor, Malaysia; suriati@upm.edu.my
- ⁵ Department of Electrical, Electronic and System Engineering, Faculty of Engineering and Built Environment, University Kebangsaan Malaysia, Bangi 43600, Selangor, Malaysia; noa@ukm.edu.my
- * Correspondence: hanif@upm.edu.my; Tel.: +60-16-328-9044
- [†] Presented at 8th International Electronic Conference on Sensors and Applications, 1–15 November 2021; Available online: <https://ecsa-8.sciforum.net>.

Abstract: In this work, molybdenum trioxide (MoO₃) was synthesized and deposited on tapered optical fiber using the drop-casting technique for hydrogen (H₂) detection at room temperature. A transducing platform in a transmission mode was constructed using multimode optical fiber (MMF) with a 125 µm cladding and a 62.5 µm core diameter. To enhance the evanescent light field surrounding the fiber, the fibers were tapered from 125 µm in diameter to 20 µm in diameter with a 10 mm waist. The microstructures and chemical compositions of the fabricated sensor were analyzed by field emission scanning electron microscopy (FESEM), energy dispersive X-ray (EDX), differential X-ray (XRD), and atomic force microscopy (AFM). In addition, the gas detection properties of the fabricated sensor were studied by exposing it to various concentrations of hydrogen gas from 0.125% to 2.00%. As a result, the sensitivity, response, and recovery time were 11.96 vol%, 220 s, and 200 s, respectively. Overall, the fabricated sensor exhibits good sensitivity as well as repeatability and stability for hydrogen gas detection.

Keywords: hydrogen (H₂) gas; tapered optical fiber; evanescent wave; molybdenum trioxide (MoO₃) and drop-casting technique



Citation: Alkhabet, M.M.; Girei, S.H.; Paiman, S.; Arsad, N.; Mahdi, M.A.; Yaacob, M.H. Tapered Optical Fiber for Hydrogen Sensing Application Based on Molybdenum Trioxide (MoO₃). *Eng. Proc.* **2021**, *10*, 75. <https://doi.org/10.3390/ecsa-8-11315>

Academic Editors: Stefano Mariani and Sabina Merlo

Published: 1 November 2021

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2021 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Hydrogen gas has a wide explosion range (4–75%), small ignition energy (0.02 mJ), and a high flame propagation speed [1]. It can leak out of storage as H₂ due to the fact that its molecule size is too small [2]. These reasons underscore the importance of H₂ detection to help reduce the risk of human exposure to the gas [3]. The fact that the optical signal is immune to electromagnetic interference, non-inductive with less attenuation than the electrical signal, is ideal for gas detection applications [4]. Therefore, the optical sensors rely on optical fibers, which have unique characteristics, such as lightness, small size, electromagnetic interference resistance, instability, and stiffness in harsh environments [5]. Due to their peculiar properties, optical fibers are perfect candidates for detection in harsh environments. In parallel, depositing the nanostructured metal oxide detection layer can provide new optical detection properties for gas [6]. The basic sensing concept of optical fiber sensors is based on the observation of any changes in the basic parameters of the modified optical signal resulting from the interaction of light through the optical fiber

with external physical, chemical, or biological measurement. The optical parameters that can be modulated are the intensity, phase, and wavelength. Among the above-mentioned parameters, intensity-based measurement is the simplest and the most low-cost technique to detect different measurands. Intensity based sensors usually require additional light to quantify the response. As a result, they use large core multimode optical fibers. This type has many advantages including its simplicity, the possibility of it being multiplexed, and its distributed sensing performance. Optimizing the analytical surface interaction contributed by the higher surface-to-volume ratio of nanostructures improves the performance of optical gas detection. So, the main motivation to improve H_2 sensing is due to the health and safety concerns that have arisen with the vast popular use of H_2 and its associated technologies.

In recent years, improved nanotechnology promises an astonishing evolution in gas sensor design and capabilities. Various hydrogen oxide sensors, including SnO_2 [7,8], ZnO [9,10], and WO_3 [11,12], as well as their mixtures, were examined. However, the response speed and sensitivity are still not satisfactory. Recent work aims to explore another metal oxide that can provide better cross selectivity and response. Molybdenum trioxide (MoO_3) shows promise in energy storage, catalysis, and gas detection applications [13]. Recently, the experiment showed that the interaction of optical fiber-based MoO_3 with hydrogen is highly sensitive, has a fast response to ant time, and an efficient eye-readable gas detection technology has been developed as a bio complement of the conventional H_2 sensors [14]. Yang et al. [15] has prepared a hydrogen sensor based on [001]-oriented α - MoO_3 nanoribbons that has a fast response time of 14.1 s toward 1000 ppm of H_2 at room temperature; Alsaifa et al. [16] has fabricated a hydrogen sensor based on two-dimensional MoO_3 nanoflakes with rapid response time of 7 s and recovery time of 24 s. However, many electrochemical hydrogen sensors based on MoO_3 carry the risk of electric sparks and have to work under elevated temperatures [17].

In this work, a tapered optical fiber coated with MoO_3 is used to detect hydrogen gas. It also explains the possible interaction mechanisms between the MoO_3 sensing layer and hydrogen gas.

2. Experimental

2.1. Tapering Process of Optical Fiber

The H_2 gas sensor was fabricated utilizing a multimode fiber (MMF) with cladding and core diameters of 125 μm and 62.5 μm , respectively, as a conversion platform. A Vytran glass (Vytran GPX-3400) processing machine was used for the taper. To obtain the desired geometry of the tapered fibers, the machine heating and pulling the fiber uses graphite filament as a heater. The MMF was tapered from the cladding with a 125 μm to a waist diameter of 20 μm , a waist length of 10 mm, and a top and bottom taper of 5 mm. Figure 1 depicts the fabricated tapered optical fiber with the tapered region. According to [18], this tapered shape responds significantly between the gas sensing layer and the evanescent field.

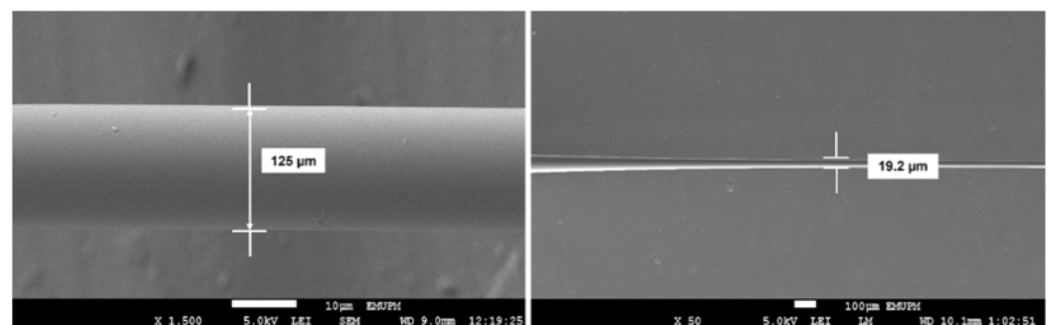


Figure 1. FESEM image of the multimode optical fiber (MMF) before and after tapering.

2.2. Fabrication of MoO_3 on Tapered Optical Fiber

Molybdenum trioxide (MoO_3) powder was synthesized by the simple solid decomposition method [19]. A 2.50 g of ammonium heptamolybdate tetrahydrate was taken and ground in suspension for one hour and annealed in an alumina crucible at 500°C for three hours in the air. The resulting product was washed with distilled water and dried in an air oven. Prepared MoO_3 (0.25 g) was dispersed in 10 mL of deionized water to obtain a milk-white suspension after ultrasonic treatment for 30 min.

The tapered optical fiber was coated with MoO_3 using the drop-casting technique. Using a micropipette, we drooped about $15\ \mu\text{L}$ of the mixture to the tapered base and heated the sample in the oven at 80°C for 30 min to complete evaporation of the aqueous medium.

The experimental equipment's of the optical gas sensing system includes a light source with a wavelength of 360 to 2500 nm (tungsten halogen, HL-2000, Ocean Optics, Dunedin, FL, USA) and spectrophotometer (USB 4000, Ocean Optics, Dunedin, FL, USA). The detection range of the optical absorbance spectrum is 200–1100 nm. Use standard (S.M.A. fiber) cables to connect the light source to the fiber optic. The inside diameter of the S.M.A. cable is $600\ \mu\text{m}$, and the FC/PC type is used as the MMF terminal. The adapter data file recognizes the standard input loss format for MMF terminated with FC/PC-SMA cables determined to be 1.4 dB. Figure 2 shows the experimental installation of sensor H_2 . Before the computer-controlled mass flow controller performs the gas purification at a gas flow rate of 200 sccm, the MoO_3 coated-based sensor is placed in a closed gas unit. The H_2 gas is purified by pure synthetic air to achieve a concentration range from 0.125% to 2.00%. The dynamic response and cumulative absorbance were determined while purging synthetic air.

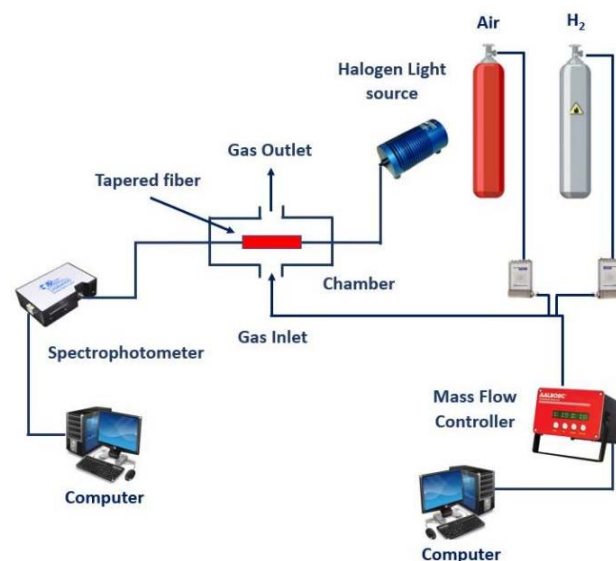


Figure 2. H_2 sensor experimental setup.

2.3. Structural Characterization of MoO_3

Various characterization techniques have been applied to characterize MoO_3 thin film. The morphology was observed by FESEM (Nova Nanosem 230), while the initial composition was determined by EDX analysis. The identification of the material, crystallization, and the phase transition of the MoO_3 , was determined by analysis of XRD (PW 3040-Philips) and AFM (Dimension Edge with ScanAsyst).

The FESEM images demonstrate the successful deposition of MoO_3 on the surfaces of the tapered optical fibers, as shown in Figure 3a. The standard features of the MoO_3 nanoparticles are shown in Figure 3b,c. The particles agglomerated in nature after attempting to form thin plate or flake-like formations. The gas analyte will interact more effectively with this plate-like structure [20].

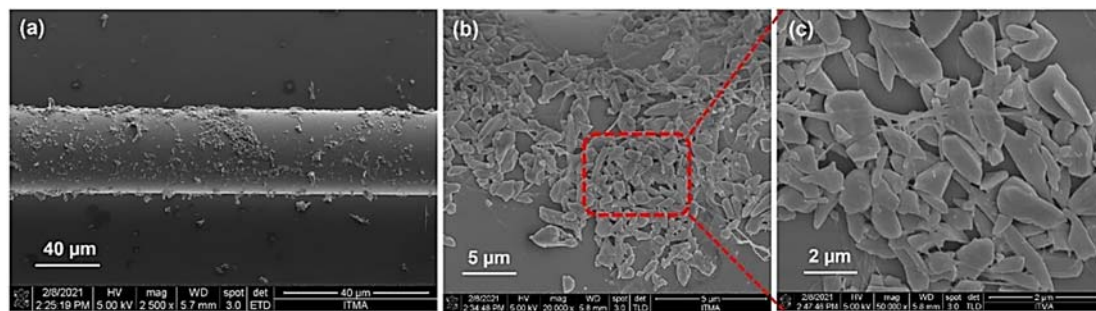


Figure 3. FESEM micrographs of (a) tapered MMF covered with MoO_3 , (b,c) pure MoO_3 .

As illustrated in Figure 4a, EDX was used to identify the elements in the synthesized MoO_3 . The MoO_3 film shows the presence of Mo, O, and Si. The silicon peak (Si) was used by the silica fibers used as a substrate. The X-ray diffraction (XRD) patterns of MoO_3 were recorded within the 2θ range of 5° to 70° , as shown in Figure 4b. The sample shows highly crystalline hexagonal and orthogonal structures, respectively, since the intensity is strong and sharp enough with narrow full-width maximum half (FWHM) of diffraction peaks such as 11.25° (100), 34.80° (101), 17.40° (110), 20.10° (200), 27.32° (210), 30.02° (300), 36.15° (310), 44.20° (320), 46.60° (410), 51.15° (002), 56.55° (211), and 58.24° (042). All of the XRD peaks can be distinguished for the sample, and single-phase can be assigned to crystal structures. The prominent diffraction peak corresponding to planes (100) and (210) was placed at the highest density of MoO_3 .

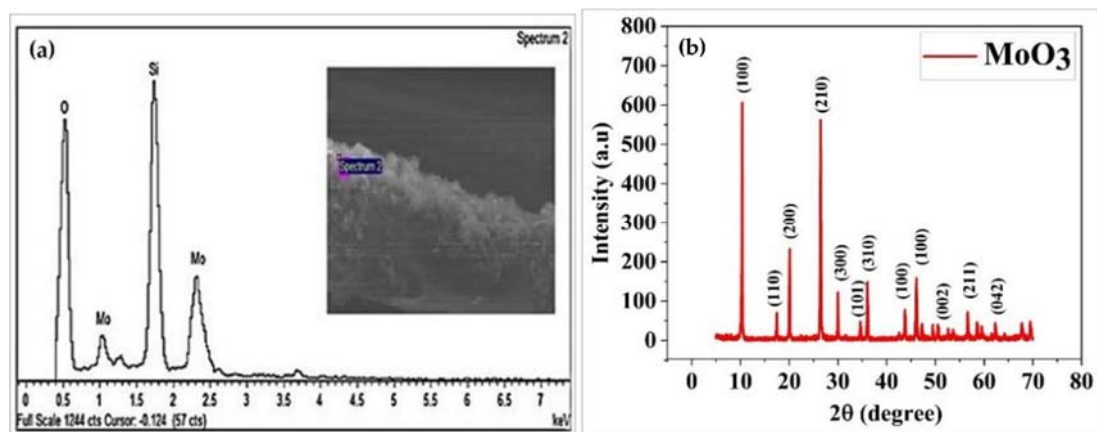


Figure 4. (a) EDX measurement of MoO_3 and (b) XRD pattern of MoO_3 .

Atomic force microscopy (AFM) was conducted to characterize the average surface roughness and thicknesses of MoO_3 . Figure 5a depict 3D AFM image of the MoO_3 . A $10 \times 10 \mu\text{m}$ section of the boundary area was scanned for the AFM analysis. The average surface roughness values were 44.98 nm. Such low roughness levels indicate that light scattering has no significant effect on sensing performance [21].

As part of this study, the thicknesses of the MoO_3 coatings were measured. Measurements were taken by covering portions of fibers with aluminum tape and then determining the differences between the thicknesses of coated and uncoated fibers. The average thickness of the MoO_3 coatings was 181 nm, as shown in Figure 5b.

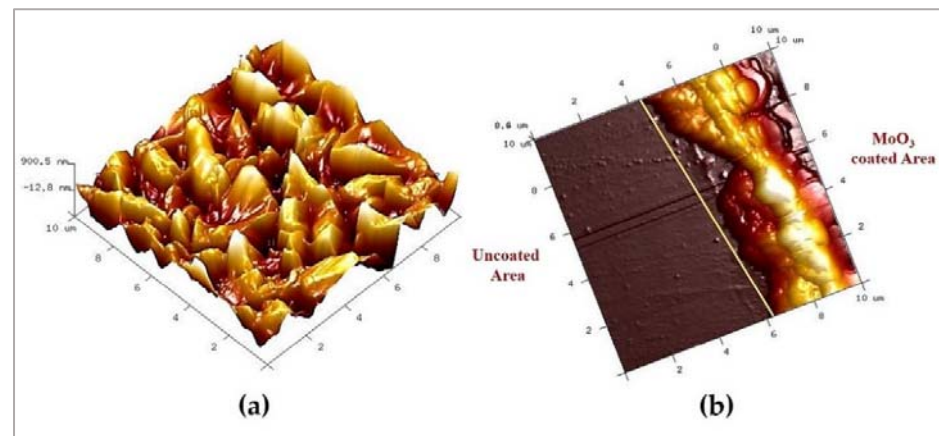


Figure 5. (a) 3D AFM image of MoO_3 , and (b) 3D AFM topography images of the boundary region between the uncoated and coated fibers of MoO_3 .

3. Results and Discussion

The relationship between the sensing layer absorption and operating temperature is shown in Figure 6a. The sample was tested with 1% H_2 on different operating temperatures from room temperature to 200 °C. According to the curve, it indicates that the absorption capacity decreases with increasing temperature, possibly due to the faster reaction rate of the absorbed hydrogen atoms at the active sites at higher temperatures. In this work, the optimum operating temperature of Pd NPs based tapered optical fiber sensors to H_2 is 25 °C.

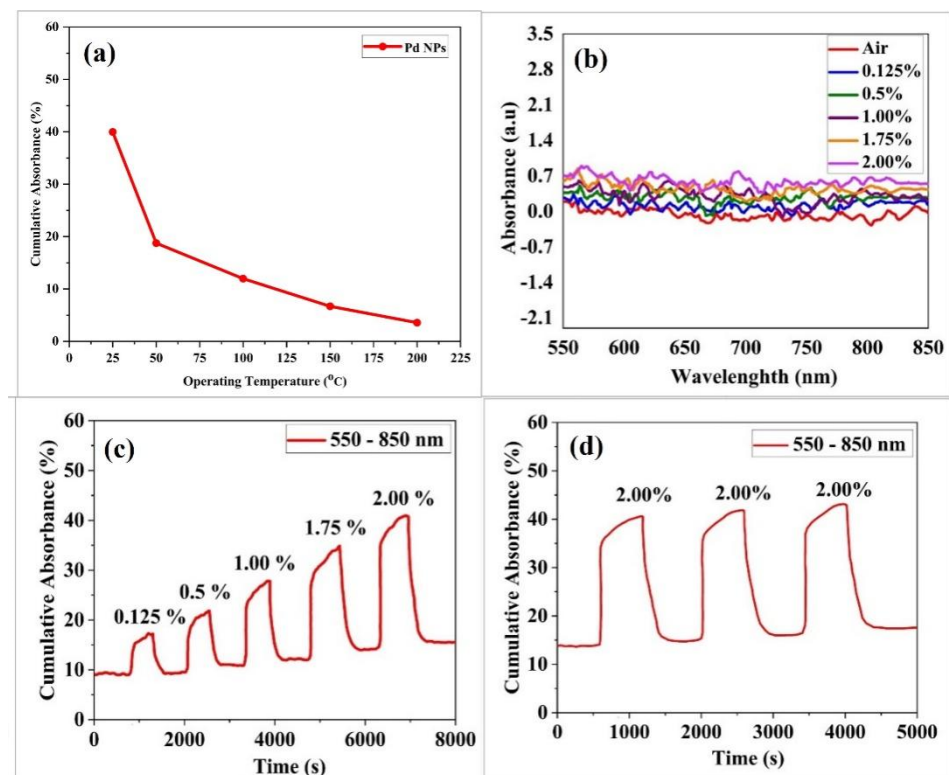


Figure 6. (a) The change of cumulative absorbance with the operating temperature, (b) the absorbance with various concentrations, (c) dynamic response, and (d) repeatability of MoO_3 .

At room temperature, the absorption spectra of the developed sensor was coated with MoO₃ to synthetic air and 2.00% H₂. The MoO₃ coated sensor exhibits noticeable changes in absorption, as illustrated in Figure 6b (especially in the wavelength range of 550 to 850 nm). The cumulative absorbance of the MoO₃ coated sensor was analyzed to determine its performance. The dynamic response of a MoO₃ coating based sensor toward H₂ concentrations (synthetic) from 0.125% to 2.00% at room temperature is shown in Figure 6c. The response and recovery times of the developed sensor were 220 s and 200 s, respectively. At 0.125% H₂, the absorbance changed by about 8%, while at 2.00% H₂ it changed by about 25%. The MoO₃ coated sensor had higher H₂ absorbance and recovery, as well as advanced compromise differences. Three cycles of 2.00% H₂ were used to test the repeatability of the MoO₃ coated based sensor. Overall, the MoO₃ coated sensor demonstrated a strong and stable absorbance response and excellent repeatability towards H₂.

The absorbance change in the MoO₃ layer can be explained with the following mechanism. During H₂ adsorption onto the MoO₃ sensing layer, the H₂ molecules dissociated onto Pd, resulting in the generation of H⁺ ions and electron. Ions of H⁺ spilled over the MoO₃ nanostructures layer which then react with chemisorbed oxygen (O⁻ and O²⁻), thereby producing H₂O molecules. The generated electrons reduced the transparent Mo⁶⁺ in the center of MoO₃ crystal lattice to Mo⁵⁺ (blue color). The change in sensing layer properties has altered the absorption of light, hence the change in absorbance magnitude. Upon exposure to synthetic air at elevated temperature, the adsorbed oxygen as well as the desorbed H⁺ ions in/out of the sensing layer which returns the absorbance spectrum to its original baseline. The stoichiometry of the MoO₃ is restored from Mo⁵⁺ to Mo⁶⁺ [6].

Figure 7a shows the absorption versus H₂ concentration for MoO₃ coated based sensors. The MoO₃ coated based sensors had a sensitivity of 11.96/vol% and a linearity slope of 98%. When measuring gas sensing properties, selectivity is an important factor to consider. Selectivity is the most critical parameter of the sensor properties. The fabricated sensor with different gases such as ammonia (NH₃) and methane (CH₄) at a concentration of 1.00% was investigated. The MoO₃ coated based sensor had a highly NH₃ absorption response but a substantially lower response for the other gases. Furthermore, the adsorption of MoO₃ based materials was highly selective for polar molecules such as NH₃, whereas sensitivity was low for non-polar molecules such as H₂ and CH₄ [22].

Stability is an important parameter which specifies the durability for all sensors [23]. The fabricated MoO₃ coated based sensors have been tested towards 2.00% H₂ gas concentration in synthetic air at room temperature for 14 days, and the response changed nominally by 2% (as shown in Figure 7c). The finding indicates that among the fabricated gas sensors, MoO₃ coating based sensors present excellent long-term stability.

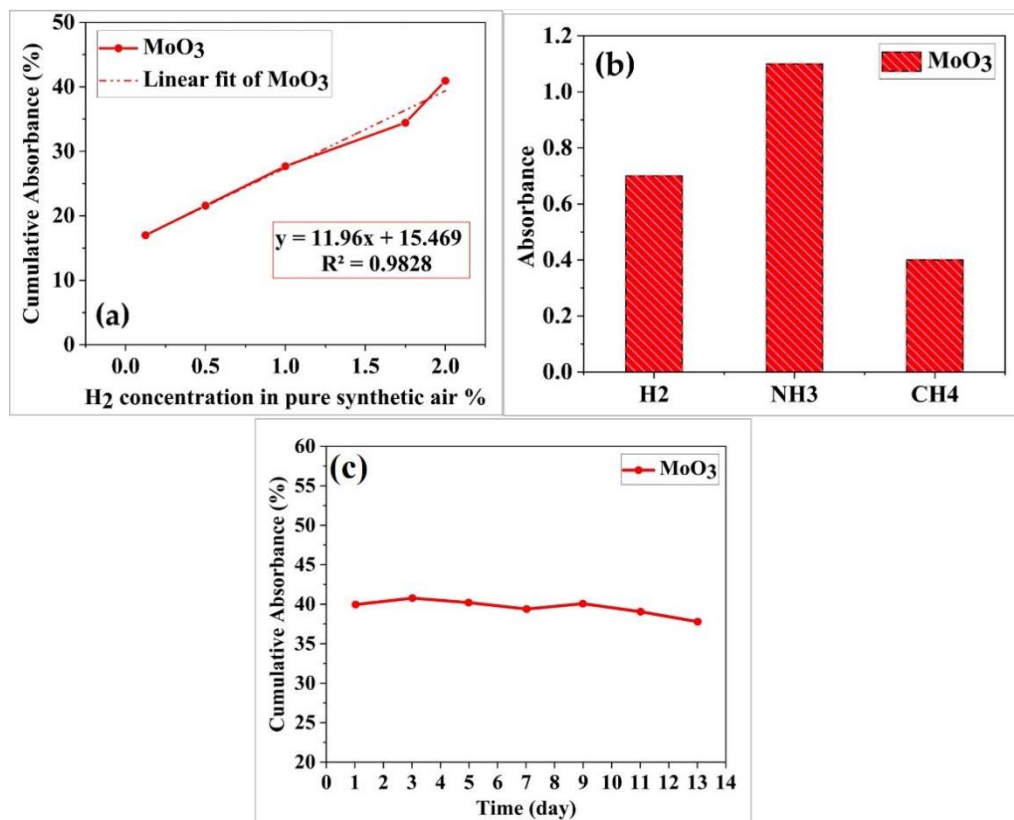


Figure 7. (a) Absorbance changes for MoO₃ coated based sensor at various H₂ concentrations, (b) selectivity of MoO₃ coated based sensor, and (c) stability of MoO₃ coated based sensor.

4. Conclusions

In the present study, molybdenum oxide was deposited on tapered optical fiber using the drop-casting technique for hydrogen sensing decoction. The H₂ gas sensor is fabricated of the as-deposited structure, which is exposed to various concentrations (0.125–2.00%) at room temperature. According to the findings, the MoO₃ coated based sensor enhanced its absorption response by 25% when exposed to 2.00% H₂ in synthetic air. The response and recovery times of the developed sensor were 220 s and 200 s, respectively. The selectivity investigation indicates that the MoO₃ based optical sensor responds strongly towards ammonia, methane, and hydrogen chemicals. The findings suggest an affordable and accessible methodology which may be utilized to enhance an effective, accurate, and repeatable H₂ sensor in real-world atmospheric conditions.

Supplementary Materials: The following are available online at <https://www.mdpi.com/article/10.3390/ecsa-8-11315/s1>.

Author Contributions: Conceptualization, M.M.A. and M.H.Y.; methodology, M.M.A., S.H.G. and M.H.Y.; writing—original draft preparation, M.M.A.; review and editing, M.H.Y., M.A.M., S.P. and N.A. All authors have read and agreed to the published version of the manuscript.

Funding: Universiti Putra Malaysia funded this research, grant number GP-IPS/2019/9674900.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Gahleitner, G. Hydrogen from renewable electricity: An international review of power-to-gas pilot plants for stationary applications. *Int. J. Hydrogen Energy* **2013**, *38*, 2039–2061. [CrossRef]
2. Moradi, R.; Groth, K.M. Hydrogen storage and delivery: Review of the state of the art technologies and risk and reliability analysis. *Int. J. Hydrogen Energy* **2019**, *44*, 12254–12269. [CrossRef]

3. Gurz, M.; Baltacioglu, E.; Hames, Y.; Kaya, K. The meeting of hydrogen and automotive: A review. *Int. J. Hydrogen Energy* **2017**, *42*, 23334–23346. [\[CrossRef\]](#)
4. Sabri, N.; Aljunid, S.A.; Salim, M.S.; Fouad, S. Fiber optic sensors: Short review and applications. In *Springer Series in Materials Science*; Springer: Berlin/Heidelberg, Germany, 2015; Volume 204, pp. 299–311. [\[CrossRef\]](#)
5. Wang, H.; Jiang, L.; Xiang, P. Improving the durability of the optical fiber sensor based on strain transfer analysis. *Opt. Fiber Technol.* **2018**, *42*, 97–104. [\[CrossRef\]](#)
6. Yaacob, M.H.; Yu, J.; Latham, K.; Kalantar-Zadeh, K.; Wlodarski, W. Optical hydrogen sensing properties of nanostructured Pd/MoO₃ films. *Sens. Lett.* **2011**, *9*, 16–20. [\[CrossRef\]](#)
7. Singh, G.; Singh, R.C. Highly sensitive gas sensor based on Er-doped SnO₂ nanostructures and its temperature dependent selectivity towards hydrogen and ethanol. *Sens. Actuators B Chem.* **2019**, *282*, 373–383. [\[CrossRef\]](#)
8. Lavanya, N.; Sekar, C.; Fazio, E.; Neri, F.; Leonardi, S.G.; Neri, G. Development of a selective hydrogen leak sensor based on chemically doped SnO₂ for automotive applications. *Int. J. Hydrogen Energy* **2017**, *42*, 10645–10655. [\[CrossRef\]](#)
9. Kumar, G.S.; Xuejin, L.; Du, Y.; Geng, Y.; Hong, X. UV-light enhanced high sensitive hydrogen (H₂) sensor based on spherical Au nanoparticles on ZnO nano-structured thin films. *J. Alloys Compd.* **2019**, *798*, 467–477. [\[CrossRef\]](#)
10. Ren, Q.; Cao, Y.Q.; Arulraj, D.; Liu, C.; Wu, D.; Li, W.M.; Li, A.D. Review—Resistive-Type Hydrogen Sensors Based on Zinc Oxide Nanostructures. *J. Electrochem. Soc.* **2020**, *167*, 067528. [\[CrossRef\]](#)
11. Dai, J.; Li, Y.; Ruan, H.; Ye, Z.; Chai, N.; Wang, X.; Yang, M. Fiber optical hydrogen sensor based on WO₃-Pd₂Pt-Pt nanocomposite films. *Nanomaterials* **2021**, *11*, 128. [\[CrossRef\]](#) [\[PubMed\]](#)
12. Wang, G.; Qin, Y.; Dai, J.; Yang, S.; Ma, Y.; Zou, T.; Roths, J.; Yang, M. Performance-enhanced optical fiber hydrogen sensors based on WO₃-Pd₂Pt-Pt composite film with controlled optical heating. *Opt. Fiber Technol.* **2019**, *52*, 101979. [\[CrossRef\]](#)
13. Farzi-kahkesh, S.; Fattah, A.; Rahmani, M.B. Synthesis and optimum temperature determination of highly sensitive MoO₃-based heterojunction Schottky sensor for hydrogen detection. *Microelectron. Eng.* **2021**, *235*, 111453. [\[CrossRef\]](#)
14. Sajadi, M.; Ranjbar, M.; Rasuli, R. Two-step synthesis of Ag-decorated MoO₃ nanotubes, and the effect of hydrogen doping. *Appl. Surf. Sci.* **2020**, *527*, 146675. [\[CrossRef\]](#)
15. Yang, S.; Wang, Z.; Hu, Y.; Luo, X.; Lei, J.; Zhou, D.; Fei, L.; Wang, Y.; Gu, H. Highly responsive room-temperature hydrogen sensing of α -MoO₃ nanoribbon membranes. *ACS Appl. Mater. Interfaces* **2015**, *7*, 9247–9253. [\[CrossRef\]](#) [\[PubMed\]](#)
16. Alsaif, M.M.; Balendhran, S.; Field, M.R.; Latham, K.; Wlodarski, W.; Ou, J.Z.; Kalantar-Zadeh, K. Two dimensional α -MoO₃ nanoflakes obtained using solvent-assisted grinding and sonication method: Application for H₂ gas sensing. *Sens. Actuators B Chem.* **2014**, *192*, 196–204. [\[CrossRef\]](#)
17. Rahmani, M.B.; Keshmiri, S.H.; Yu, J.; Sadek, A.Z.; Al-Mashat, L.; Moafi, A.; Latham, K.; Li, Y.X.; Wlodarski, W.; Kalantar-zadeh, K. Gas sensing properties of thermally evaporated lamellar MoO₃. *Sens. Actuators B Chem.* **2010**, *145*, 13–19. [\[CrossRef\]](#)
18. Alkhabet, M.M.; Girei, S.; Paiman, S.; Arsad, N.; Mahdi, M.A.; Yaacob, M.H. Highly Sensitive Hydrogen Sensor Based on Palladium-Coated Tapered Optical Fiber at Room. In Proceedings of the 7th International Electronic Conference on Sensors and Applications, Online, 15–30 November 2020; pp. 3–8.
19. Dhanavel, S.; Nivethaa, E.A.K.; Dhanapal, K.; Gupta, V.K.; Narayanan, V.; Stephen, A. α -MoO₃/polyaniline composite for effective scavenging of Rhodamine B, Congo red and textile dye effluent. *RSC Adv.* **2016**, *6*, 28871–28886. [\[CrossRef\]](#)
20. Sau, S.; Chakraborty, S.; Das, T.; Pal, M. Ethanol Sensing Properties of Nanocrystalline α -MoO₃. *Front. Mater.* **2019**, *6*, 285. [\[CrossRef\]](#)
21. Puebla, S.; Mariscal-jim, A.; Munuera, C.; Castellanos-gomez, A. Optical-Based Thickness Measurement of MoO₃ Nanosheets. *Sensors* **2020**, *10*, 1272. [\[CrossRef\]](#) [\[PubMed\]](#)
22. Fattah, A.; Rahmani, M.B. Gas Sensing and Structural Properties of a Nano-structure MoO₃-based Hydrogen Sensor. *Iran. J. Energy Environ.* **2019**, *10*, 230–234. [\[CrossRef\]](#)
23. Rymarczyk, J.; Czerwosz, E.; Diduszko, R.; Kozłowski, M. The thermal stability of the carbon-palladium films for hydrogen sensor applications. In *Photonics Applications in Astronomy, Communications, Industry, and High Energy Physics Experiments*; International Society for Optics and Photonics: Bellingham, WA, USA, 2017; Volume 10445, p. 1044550.